




LIBRARY UNIVERSITY OF CALIFORNIA

> EARTH SCIENCES LIBRARY

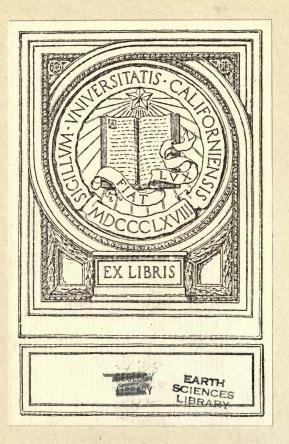

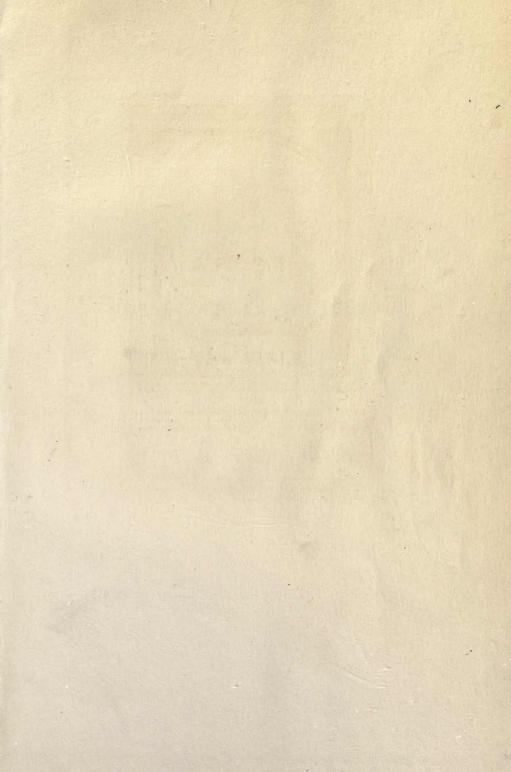

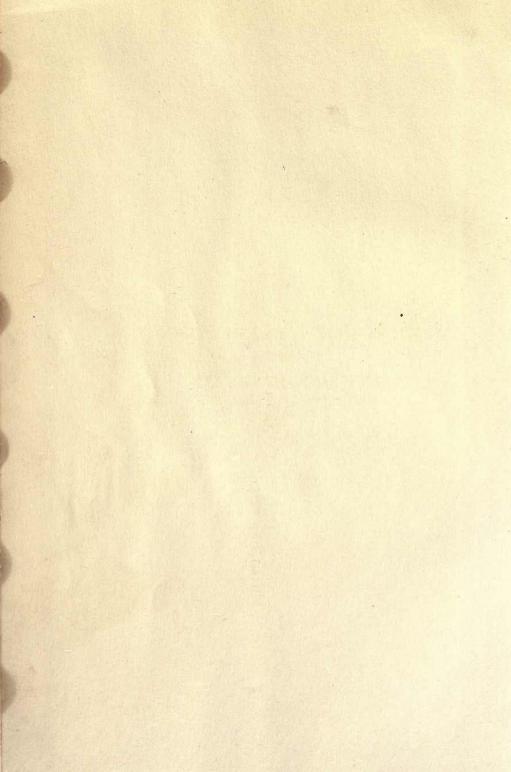

MICROSCOPIC EXAMINATION OF THE ORE MINERALS

Mc Graw-Hill Book Co. Inc.

PUBLISHERS OF BOOKS FOR

Coal Age

Electric Railway Journal

Electrical World

Engineering News-Record

American Machinist

Ingeniería Internacional

Engineering & Mining Journal

Power

Chemical & Metallurgical Engineering

Electrical Merchandising

MICROSCOPIC EXAMINATION

OF

THE ORE MINERALS

BY
W. MYRON DAVY

AND

C. MASON FARNHAM


FIRST EDITION

McGRAW-HILL BOOK COMPANY, Inc. NEW YORK: 239 WEST 39TH STREET LONDON: 6 & 8 BOUVERIE ST., E. C. 4 1920





COPYRIGHT, 1920, BY THE McGraw-Hill Book Company, Inc.



INTRODUCTION

The use of the reflecting microscope as a means of determining the identity, relationship, and significance of opaque minerals in ore deposits has been steadily increasing since William Campbell, 1 in 1906, first applied the methods then used by metallographers in the study of metals, to the examination of opaque minerals. Nearly a century ago Berzelius published the results of polishing a specimen of pyrrhotite and suggested the possibilities of examining opaque minerals in this way, but no practical methods resulted from his observations at that time. Even after Campbell's paper, mining and geological literature did not reflect any great interest in the subject until six or seven years had passed, when some admirable papers described the studies on particular types of ores. About this time the laboratories of mining geology at the Massachusetts Institute of Technology, Harvard University, and Leland Stanford University, as well as a few other investigators, were carrying on extensive researches in this field of study. In 1916, Dr. Joseph Murdoch² published the results of numerous microchemical tests, arranging them in a determinative table which was by far the most complete work on identification of minerals under the metallographical microscope, and his book deserves the credit for much valuable pioneer work. Several years have now passed and new ideas have originated as the result of further study along this line.

Work carried on steadily in the laboratories at the Massachusetts Institute of Technology on a wide range of ores, and at Harvard University on the original collection of minerals that formed the basis of Dr. Murdoch's book, justifies the following conclusions:

1. Fine distinctions in color value between the many so-called white minerals cannot be depended upon as a safe property on which to base the major classifications in making identity determinations. It has been found that hardly any two persons can

¹ Campbell, W. "The Microscopic Examination of Opaque Minerals." *Economic Geology*, Vol. 1, 1906, p. 751.

² Murdoch, J. "Microscopical Determination of the Opaque Minerals." Preface by L. C. Graton, John Wiley & Sons. 1916.

agree in the application of such terms as bluish white, pinkish white, creamy white, purplish white, etc. However, if two microscopes and a comparison eveniece are used, or if a standard mineral can be mounted adjacent to the unknown, most observers will agree in pronouncing the unknown to be lighter, darker, or the same as the standard; but at best this method is awkward. especially when the unknown mineral does not occur on the edge of the section. Some minerals change color after polishing, the kind of light used effects the colors seen, and a few cases have been observed where two freshly polished specimens of the same mineral differed so greatly in color as to fall into widely separated groups. The observed color of a mineral may be greatly influenced by the colors of other minerals in the field. for example, chalcopyrite is yellow when seen alone, but if seen adjacent to native copper it will appear to be a decided olive green. For these reasons the scheme of identification used in this book is independent of color distinctions which are only used in conjunction with many other properties as an ultimate means of separating the different minerals that fall into a final group.

- 2. Detailed descriptions of the way in which microchemical reactions proceed are in many cases valueless because of the fact that two specimens of the same mineral seldom yield exactly identical results. In nearly every case, however, they will check as far as reacting positively or negatively with a reagent is concerned, which is all that is needed for identification. Moreover, it has been found that slight differences in the character of the mineral surface, slight differences in the concentrations of the reagents, and sometimes even the crystallographic orientation of the polished section have an important influence upon the reactions.
- 3. The number of reagents which can be used advantageously throughout a determinative scheme is limited to four or five. Many others have been tried, but their application is very limited and as time goes on the tendency is more and more toward simplification. In this work no attempt is made to list all tests known to date, but only those supplementary ones are included which may be valuable in differentiating between two or more minerals falling in one final group. As emphasized in the following paragraph, in most cases an easily applied blowpipe test is convenient and adds far more confidence to the determination.
 - 4. As in the early application of new developments in all lines,

mineragraphy has been pushed beyond its natural limitations in displacing other determinative methods and now a slight reaction is setting in. This art gives us our most useful means for examining into the genesis of ore deposits, and is in itself a very valuable method of mineral determination; in certain cases, the best known method. But in the determination of the minerals in an average polished section of ore it is a handicap to restrict the examination to mineragraphic tests alone. One of a group of possible minerals can usually be run down quickly and confidently by gouging out from the edge of the section a small piece seen to contain the unknown, and treating it on charcoal before the blowpipe, or heating it in the open or closed tube, etc. objection has been raised that the unknown cannot be cleanly separated, but very often all the other minerals are known and the reactions vielded by them can usually be discounted. There is never any need to run through a blowpipe analysis as the microchemical reactions narrow the possibilities down to a few minerals, and one or two tests suffice. Consequently it has been found exceedingly helpful to include the characteristic blowpipe reactions for each mineral along with its other properties in the tables.

The foregoing considerations have largely influenced the arrangement of the tables and the choice of the material to be included in them.

The microchemical reactions listed are from various sources. The authors have independently studied one hundred and forty-three mineral species, thus covering all except a few of the rarest varieties; and as most of these species are also listed in Dr. Murdoch's book, it is believed that this triple check results in the accurate determination of the reactions.

Fourteen minerals not previously described in mineragraphy have been tested and included in this work. A few very rare and doubtful species and some mixtures described by Murdoch have been omitted as it is felt that their presence in the tables complicates and adds little of practical value for the average user. The impression must not be gathered, however, that the so-called rare minerals are unimportant for, although only the more common minerals are encountered in nine out of ten ores examined, it is of great importance to recognize the rarer ones when they do occur. Furthermore, these uncommon minerals are sometimes found in small quantities or as fine intergrowths

and their presence is never suspected until examined microscopically with vertical illumination; consequently they become less rare and take on a greater importance in mineragraphic study than has been the case with former mineralogical methods.

Mineragraphy is used throughout the book to designate the art of polishing, identifying, and examining the ore minerals under the metallographic microscope. Minera is late Latin meaning ore and graphy has been borrowed from the well established metallography. Whitehead¹ first used this name in print, and although mineragraphy as a word is not altogether pleasing, a name is much needed and it is here used with the hope that something better will be suggested.


It is believed that an infallible determinative table has never been devised on any subject, and the task is even more difficult in this case where the available material is at best new and littletried. The beginner, of course, must acquire familiarity with both the tables and the general appearance under the microscope of the more common minerals, and even the experienced mineralogist must serve a short apprenticeship in order to obtain good results. In preparing this book it was felt that a text was needed which could be used by both the profession and the student of mining and geology. Communications addressed to the laboratories of economic geology of the Massachusetts Institute of Technology indicate that the study of ore minerals in reflected light is to be introduced into the curriculum of several more of the country's larger institutions, and that a statement of the latest practice was desired. It is hoped that this rather brief review of the subject will serve such a practical purpose until such time as the combined experience and discoveries of many workers greatly increase our present knowledge along this line.

The authors wish to express their appreciation to Professor Waldemar Lindgren whose able and patient guidance has made the book possible, and to Professor L. C. Graton whose keen interest in this work has ever been a helpful inspiration.

¹ WHITEHEAD, W. L. "Notes on the Technique of Mineragraphy." *Economic Geology*, Vol. xii, No. 8, 1917, p. 697.

TABLE OF CONTENTS

	PAGE
Introduction	v
CHAPTER I	
Technique of Polishing and Examining the Specimen. Necessity for specialized polishing methods—Grinding—Polishing —Field preparation of a specimen by hand—Examination of the specimen—Microscope used—Optical principle involved—Con- struction and use of finder—Method of applying tests—Electrical conductivity of minerals—Electropotential of minerals—Concen- tration of reagents.	1
CHAPTER II	
PHOTOMICROGRAPHY OF POLISHED SECTIONS Equipment—Need for color filters—Methods of determining proper exposure—Exposure curves—Developing and printing.	12
CHAPTER III	
Use of the Determinative Tables. Procedure in making determinations—Abbreviations used in tables—Qutline of the tables—Determinative tables.	20
CHAPTER IV	
Supplementary Tests. Tabular arrangement of the minerals according to: Color of surface; Color of internal reflection; Color of powder; Electrical conductivity; Electro-potential—Tests for the elements with minerals arranged according to elements—Mirochemical qualitative reactions—Standard fusibilities—Heating on charcoal—Sublimates in the closed tube—Sublimates in the open tube—Bead colors with borax and salt of phosphorous.	120
Index	151

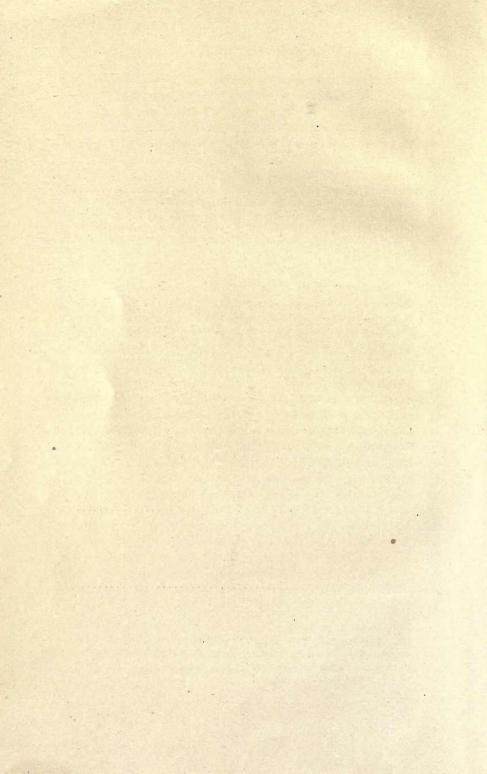

MICROSCOPIC EXAMINATION

OF

THE ORE MINERALS

CHAPTER I

TECHNIQUE OF POLISHING AND EXAMINING THE SPECIMEN

Preparation of the Specimen

The successful determination of the identity of minerals with the reflecting microscope depends primarily upon having all minerals in the section properly polished with little relief, free from scratches, pits, and vugs; and without having changed the chemical character of delicate sulphides during the grinding process. It has been observed, for example, that chalcopyrite if ground under pressure on a rapidly revolving dry lap will develop bornite and chalcocite; and that pyrite when treated likewise will develop limonite.

In 1917 W. L. Whitehead¹ pointed out the fact that mineragraphic sections require grinding and polishing treatment fundamentally different from that of metals for metallographic study. A metal specimen is usually one of uniform hardness and possesses far more ductility and toughness than an ore section which often consists of several minerals of widely differing hardness and of more or less brittleness. Pyrite, a mineral harder than almost any metal, is so universally present in ores that it often must be polished in the same section with a mineral so soft as to be scratched by the finger nail. When purely metallographic methods are used in polishing ores this difference in hardness presents formidable difficulties to good work. The soft broadcloth surface of the wheel swells outward and rapidly wears down the soft minerals, developing a relief so pronounced that it is

¹ WHITEHEAD, W. L. "Notes on the Technique of Mineragraphy." *Economic Geology*, Vol. xii, No. 8, 1917, p. 697.

impossible to focus upon two adjacent soft and hard minerals, especially at high magnifications.

In the laboratory, specimens are usually desired for two distinct purposes; first, for visual examination and second, for photomicrographs. Comparatively little effort is required in polishing sections for the former purpose, and while a badly scratched and pitted surface should never be tolerated, very fine and shallow scratches do not interfere with visual study at any magnification. However, these comparatively minute scratches and pits make photography difficult, and they require exhaustive and careful polishing for their elimination.

The following procedure is in use at the Massachusetts Institute of Technology and with minor variations can easily be adapted to any grinding and polishing equipment. First, a portion of the specimen is chosen which appears to represent all the important features present, an area of a square inch or less usually being sufficient. This may be carefully chipped or cut off with a diamond saw. The latter method is by far the best when such equipment is available, as it rapidly yields an approximately plane surface at any desired orientation and the opposite face of the cut can be made into a thin section if required. The saw used is 10 inches in diameter and is driven at 1600 R.P.M.

Any large inequalities in the surface chosen should be removed by grinding wet upon a steel lap wheel with 150 emery or alundum. A 10-inch horizontal wheel revolving at about 200 or 225 R.P.M. is used. After thorough washing of the hands and specimen the grinding is continued on an 8-inch horizontal glass wheel driven at 1800 R.P.M. and using the finest optical alundum (manufactured by Norton & Co., Worcester, Mass.) mixed to a very thin slime with water. This is perhaps the most important stage in the preparation. Considerable pressure may be exerted at first to quickly remove the scratches caused by the coarse abrasive; then grinding should be continued with light pressure until the surface is free of all except very fine scratches and pits. More than a minute or two is seldom required at this stage, but when needed more time should be taken, as a minute spent here saves ten minutes later.

The true grinding part of the operation is completed and from now on the purpose of the work is to obtain a final polish. The same preparation of finest optical alundum is next used on a high speed 8-inch wheel covered with tightly stretched coarse linen (about 15 threads per cm.). This wheel is horizontal and is driven at 1800 R.P.M. The specimen should be lightly held and constantly turned for 30 to 60 seconds, finishing up with about 30 seconds polishing without applying fresh alundum. The abrasive breaks down and developes a fine polish as seen by the naked eye.

This polish is improved by holding lightly for 30 or 60 seconds on a similar wheel covered with fine linen (30 threads to the cm.) using a slime of rouge and water. This wheel is an 8-inch horizontal lap wheel driven at 1000 R.P.M. After thorough washing and drying the final surtace is obtained on a wheel similar to the preceding, but covered with tightly stretched calf skin. A split calf skin with the grease removed and finished with a very short nap on the flesh side is used. Care should be taken here to prevent overheating with consequent altering of the sulphides and burning of the leather. With a little practice 10 minutes will suffice for the entire process of cutting and polishing a surface comparatively free from scratches and trouble-some relief, which can be satisfactorily studied even under the highest magnifications.

Out of a number of specimens studied from one deposit, two or three will usually be chosen for photographing, and these should receive additional preparation to eliminate the very fine scratches which cannot be avoided with the foregoing procedure alone. Chromic oxide has been found to yield the best results of all materials tried to date. Its use is introduced between the second optical alundum and the rouge wheels. The finest commercial chrome oxide is levigated to remove any coarse material and is used on a coarse linen wheel revolving at 1800 R.P.M. or faster. Careful treatment here eliminates the fine scratches produced by the optical alundum. The specimen, as before, is finished on the rouge wheel.

In discussing a method of polishing ore specimens no fixed rule can be formulated and the more work that is done the more evident it becomes that each type of ore requires specialized treatment to obtain the best surface for photography. On the other hand, as previously stated, only a small portion of the specimens studied need be so prepared and the standardized and rapid method first described produces excellent results when only visual studies are to be made.

The quality of the illustrations in many of the recent papers

4

on mineragraphic study proves that some of the laboratories have highly developed polishing methods and criticisms and suggestions from them should advance our knowledge of the subject.

FIELD PREPARATION OF A SPECIMEN BY HAND

The engineer studying or developing a prospect, or the geologist in the field usually lacks the necessary equipment as above described, yet it is often important and helpful to clear up certain points without waiting until the apparatus is available. In this case fairly satisfactory results can be obtained by hand with a supply of coarse and fine emery or alundum, rouge and leather. They should all be used on surfaces similar to those described under mechanical polishing methods. So valuable does this line of investigation promise to become for the examining engineer and geologist and so inexpensive is the microscopic equipment necessary that a supply of the requisite materials should be a part of every field outfit.

EXAMINATION OF THE SPECIMEN

A good microscope in common use is the Sauveur and Boyleston metallographic microscope manufactured by the Bausch and Lomb Optical Company, and illustrated in Fig. 1. It is very convenient for examination in daylight and with moderate magnifications. The objectives usually used are of the short mounted type and are of 16 millimeters and 4 millimeters focal length. Many types of microscopes, however, can be fitted with a vertical illuminating prism and be used for ordinary mineragraphic purposes. The simple optical principle involved is illustrated in Fig. 1. Light enters at and is reflected vertically downward by the prism, strikes the polished surface, and is reflected vertically upward. A thin plane glass illuminator is used in place of the prism at higher magnifications and with artificial illumination, as it gives a sharper image. The plane glass reflector, however, is unsuited for use with daylight as it does not give sufficient intensity. Recently a silvered reflector to replace the prism has been placed on the market and has proved satisfactory with all kinds of light.

A devise that gives the location of any particular feature in a polished section, and enables this feature to be brought again immediately into the field of the microscope, may be

easily constructed in a few minutes. (See Fig. 2.) A piece of metric cross-section paper ruled to millimeters is sealed between


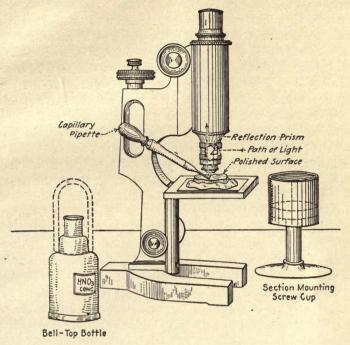


Fig. 1.

two thin pieces of glass which are about four and one-half centimeters long and two and one-half centimeters wide. (Glass slides used in mounting thin sections may be used.) To the under

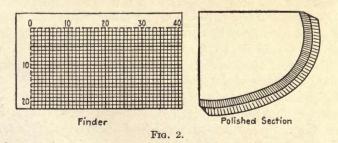

side, two narrow strips of wood are glued to two adjacent edges so that their intersection will form a perfect right-angled corner. The cross-section lines should be considered coördinate lines and the point directly above the intersection of the wooden strips be considered the 0-0 coördinate. It is necessary that two sides of the polished section be ground so as to form a right-angled corner. This rough grinding requires only a few minutes additional work on the section, and the edges thus produced allow all minerals at the edges to be compared directly with standard minerals. In subsequent polishing, these sharp edges will not injure the polishing cloth, provided the corner is pointed in the direction of revolution of the lap. When any feature in a polished section is to be located, the procedure is as follows: (1) raise the objective about a centimeter and gently place the finder upon the polished section, carefully fitting the corner of the section into the corner formed by the wooden strips on the finder; (2) focus upon the glass surface of the finder, using the 16-mm. objective, and place a minute drop of ink with a fountain pen in the center of the field; and (3) remove the finder and read directly the location as x millimeters to the right of, and y millimeters down from the coördinate 0-0. Relocation is made in reverse This method has been used on a large number of sections, and though rather crude, has been found to be simple and effective, and almost indispensable with the highest magnifications.

The specimen is mounted by being pressed into a lump of modelling clay on a glass slide or similar surface. The polished surface must be perpendicular to the axis of the microscope and probably the most convenient method of leveling it accurately is by means of a screw bottom cup also illustrated in Fig. 1. A piece of 2-inch pipe about 2 inches long is threaded on the inner side and fitted with a threaded plug bottom. The slide with the specimen pushed approximately level into the clay is placed inverted across the top of the cup. By adjusting the bottom the slide is made to just clear the rim and it is then pushed firmly down. The surface of the specimen is now parallel to the slide which will rest upon the stage and consequently will be perpendicular to the axis of the microscope.

For preliminary study and when applying reagents the 16 millimeter (low power) objective is always used. Focus upon the surface to be examined and adjust the vertical illuminator until the surface appears brightest. The opaque minerals will appear white or colored, while the transparent gangue minerals will be black or very dark gray. Tests for hardness, sectility, color of powder, chemical behavior, etc., may now be applied.

A fine sharp needle mounted in a small handle five or six inches long will serve to test for hardness or similar properties. The user should accustom himself to always holding it in about the same manner when testing for hardness in order to correctly compare results. Those minerals that scratch easily without pressure or with very light pressure are classified as of low hardness; those which scratch very slightly with light pressure or easily with heavy pressure are classified as of medium hardness; and those minerals which scratch very slightly or not at all with heavy pressure are classified as of high hardness. The opaque minerals range through a uniform gradation from the softest to the hardest, but after a short time it is not difficult to classify most of them readily. When a mineral is on the border line between two degrees of hardness it is usually found in both positions in the tables.

Sectility or brittleness determination is another convenient test which is sometimes of value. When testing for this property the needle is pushed across the mineral surface with a rotary motion; when the mineral is brittle the powder formed, if any, usually flies away from the edge of the scratch; if the mineral is sectile, little or no powder is formed and the needle penetrates more or less as in cheese.

When a heavy scratch is made by pushing the needle point across the mineral surface the color of the raised edge of the furrow or of the powder formed is very characteristic in the case of certain minerals and this property is an important aid in identification in these cases. See Table 9, page 122.

The microchemical tests are by far the most important in identifying the minerals and should consequently be applied with care and uniformity. The reagents are conveniently applied to the polished surface by the use of a pipette with a fine capillary opening fitted with a small rubber bulb. With such a fine pipette a very small drop of the reagent can be applied exactly where desired and great nicety of manipulation is easily possible. It has been found desirable to use a bell top bottle in which the pipette fits as a ground glass stopper, as the microscope is thus guarded from the acid fumes. A method of applying the reagents described by E. S. Bastin¹ has been found convenient in some cases, especially with the weaker reagents. In this method a small strip of blotting paper tapered at one end is used

¹ Economic Geology, Vol. xi, No. 7, 1916, p. 691.

for touching the surface with the reagent and another clean strip is used for removing it to stop the reaction when desired.

The tests should be watched under the microscope at all stages and the following points observed: (1) Is any effervescence produced? (2) Does the surface change color? (3) Is there any structure developed (cracks or cleavage, etc., made more prominent)? (4) Do the fumes of the reagent affect the mineral surface beyond the edges of the liquid? After the reaction has proceeded for ten seconds or up to a minute, depending upon rate of attack, the specimen may be removed from the stage and washed by directing a fine stream of water on the surface from a small wash bottle or dropping tube. The section is again examined under the microscope without rubbing and the following points noted: (1) Is the area covered by the liquid tarnished? (2) Is there any structure or etching developed in this area? (3) Is the area subjected to the fumes tarnished? The specimen is again removed from the stage, carefully dried, and rubbed lightly on a block covered with chamois skin, and again examined to determine whether or not the effects are persistent. Before rubbing, the surface is sometimes slightly dirty due to the evaporation of some of the liquid even though the reaction is entirely negative. This should not be mistaken for a slight positive reaction and may usually be avoided by carefully blotting the washed surface with a soft handkerchief or cloth.

Electrical conductivity, in many instances, may serve to distinguish minerals of similar physical and microchemical properties. The test for electrical conductivity is made under the microscope, using a 16-mm. objective, and the equipment must be adapted to mineral surfaces as small as two millimeters in diameter. Therefore steel needles had to be used for contacts. At first it was thought that these contacts would have to be placed a fixed distance apart in order to give constant readings, but experiment has shown that the difference between having the terminals a centimeter apart and very close together, is too small to be recorded. The apparatus consists of two Columbia dry cells No. 6, and a Weston D.C. voltmeter connected in series. The voltmeter had a resistance of 251 ohms, and read 150 with the circuit closed. As would naturally be expected the needle points introduce additional resistance; and differences in readings arise from varying pressure with which the points are pressed upon the mineral surface, the fact that soft minerals allow the points to penetrate further than do hard minerals; and that a rough surface will give a different reading from the same surface when perfectly polished. This method is, therefore, qualitative rather than quantitative, but does serve to arrange the minerals in a series in proper order, beginning with those that do not conduct electricity, and ending with those that conduct electricity as easily as copper. Only minerals that are found widely apart in this series may be definitely distinguished by this means. The mineral to be tested is brought into the center of the field of the microscope, the two steel needle points are placed upon the surface, and the voltmeter reading noted. The mineral will immediately give either a reading of zero, of 150, or an intermediate reading; thus, giving at once three groups: minerals apparently non-conductors, minerals with conductivity equal to or greater than copper, and minerals having electrical conductivity but with greater resistance than copper. Minerals belonging to these three groups will be found tabulated in Table 10, page 123. By this method plagionite may be distinguished from galena, stromeverite from argentite, tennantite from tetrahedrite, pentlandite from chalmersite, etc.

Electrolysis may be used to etch and bring out the structure of minerals in polished sections. After a drop of the reagent is placed on the polished surface under the microscope, it was found that the chemical action could be "speeded up" by the use of a weak electric current. The current used was furnished by one dry cell of the same type as used in determining the comparative electrical conductivity; and the terminals were a sewing needle and a piece of fine platinum wire; the former being connected to the carbon pole, and the latter to the zinc pole of the dry battery. The needle is placed on the polished surface just outside of the drop of reagent, and the platinum wire brought into contact with the top of the drop of reagent. Using a 20 per cent. solution of FeCl₃ a clot of metallic copper will be produced on the end of the platinum wire by algodonite, bornite, chalcocite, native copper, and covelite. With the same reagent a beautiful "wood grain" structure is developed on enargite, famatinite, and luzonite, which distinguishes them from tetrahedrite and tennantite. The effects of a weak current on the microchemical reactions may be generalized as follows: (1) a reagent that is negative when used alone may be strongly

reactive with the current; (2) any reagent that reacts alone will give a much more intense reaction with the current; and (3) if the reagent with the current gives no reaction, it is a good check that the reagent is truly negative.

The electro-potentials of minerals have been investigated not only as a possible means of identifying minerals, but also because of their important bearing upon the processes of enrichment of ore deposits. Although the results obtained cannot be considered as of general value for the purpose of identification, still a summary of the work thus far accomplished is suggestive and may well lead to further investigation. The method used in making the test is very simple. A small drop of dilute nitric acid is applied to the mineral while under the microscope. The polished section is then removed and a minute primary cell is established by bringing a standard electrode into contact with the top of the drop and completing the circuit, into which has been introduced a millivoltmeter, with a wire placed on the mineral surface near the drop. Eight standard electrodes, which are wires composed of a solid solution of copper and gold and containing, respectively, 100 per cent., 95 per cent., 90 per cent., 80 per cent., 70 per cent., 60 per cent., 50 per cent. and 40 per cent. of copper, are used to determine the direction and intensity of the electric potential difference. results of testing many of the minerals having high electrical conductivity are tabulated in Table 11, page 124, and indicate the position of the more common ore minerals in the electromotive series. These tests have emphasized the fact that when an active reagent is placed upon the contact of two electrically conductive minerals, the reagent becomes the electrolyte of a primary cell in which the minerals in contact are electrodes, and a weak current will be produced. The result is that the mineral of lower potential will dissolve more rapidly than normally, and this demonstrates the fact that microchemical tests should only be made upon pure material, and that the influence of impurities may give conflicting microchemical observations.

The following reagents have been used in this work and their effects are briefly described in the determinative tables. They are of the same strength as those used by Murdoch and thus it has been possible to compare directly the results obtained.

One part concentrated acid (sp. gr. = 1.42)
and one part water.
One part concentrated acid (sp. gr. = 1.19)
and one part water.
20 per cent. solution in water.
20 per cent. solution in water.
Saturated solution in water.
Saturated solution in water.

Care should be taken to use reagents of approximately the above strength as discordant results are otherwise often obtained. Care should be taken to confine the reagent to the surface of the mineral under examination also because reactions with soluble gangue substances sometimes confuse the results.

Finally, qualitative chemical tests for the elements can be applied under the microscope. They are of great value in certain special problems and the mineragrapher must more and more resort to them. As a rule two or sometimes three reagents only are required for such a test and, with very little practice, results of such nicety can be obtained that, once used, microchemistry will always hold its place. A condensed list of the microchemical tests for elements commonly found in the ore minerals is given in Table 12, page 145.

¹ See Chamot, E. M. "Elementary Chemical Microscopy." New York, 1915.

CHAPTER II

PHOTOMICROGRAPHY OF POLISHED SECTIONS

For the mining geologist, photographs of the ore minerals and the relations between them, as seen by vertical illumination are almost indispensable in preparing reports. A well-chosen illustration will establish a point more conclusively in the minds of the readers than pages of written description. For the student of ore deposits, such microphotographs are invaluable records to be preserved as reference material.

The arrangement is simple, there being a camera in which a microscope takes the place of the lens. Practically, however, good results require a high-grade specially designed microscope and strong artificial light. The procedure has been borrowed largely from metallography, except that metallographers seldom have to bring out color values by optical means, while in mineragraphy the variety of different minerals in one section calls for rather refined methods of color screening or filtering. The large Leitz metallographic microscope has been used by the writers, but any good instrument made on the same optical principles such as the Leitz type manufactured by Bausch and Lomb would serve equally well. A 5-ampere D.C. arc lamp is used as the source of light with this microscope. A description of the construction and specialized directions for the use of such apparatus are out of place here and are always supplied by the makers with the instruments. We are, however, concerned with many factors dealing with the choice of subject and the technique of photomicrography in general.

First, it is well worth the time to search carefully over all the polished sections available in order to locate an area which will best illustrate as many as possible of the important features in In too many microphotographs which have appeared in the literature the reader has to accept on faith the writer's statement that some relationship is established by the illustration. It is true that two people may not always interpret a particular structure in the same way, but it is a rare specimen which justifies positive conclusions and which does not show an area illustrating them.

When the subject for the photograph has been chosen care should be taken to adjust the reflector in such a way as to obtain uniform illumination over the entire field, otherwise a negative of uneven density will result.

The proper color screen to bring out the contrasts between the various minerals must now be selected. The sensitiveness of the photographic plate to light of different colors or wave lengths is very different from that of the human eye. Ordinary white light and light from most artificial sources is a mixture of lights of all wave lengths. The eve sees all of these colors through a rather wide range, while the photographic plate "sees" colors outside of the limits of this range and is "blind" to much that is within it. For example the eye registers red as a bright color, but the ordinary plate is unaffected by red light and in a picture all red objects would appear black. For a complete and interesting treatment of this subject the reader is referred to "The Photography of Colored Objects" by Dr. C. E. Kenneth Mees.¹ Certain dves have the property of absorbing light of certain wave lengths and by passing the light to be used through filters made with these dyes, color effects can be controlled upon the negative to a large extent. Table 1 lists the Wratten M filters supplied by the Eastman Kodak Company and indicates the approximate range of light transmitted by each.

Experience has shown that a filter should be used at all times as several optical difficulties arise when photography is attempted without them especially at magnifications greater than 100 diameters. For the average section with a variety of minerals clearly distinguishable by the eye the K3 yellow filter most nearly reproduces the true values as seen (that is when used with the Wratten M plate described below). In many cases, however, when strong contrast is required between two minerals it is necessary to select one of the special filters described in Table 1, or, sometimes, one of the combinations of two filters. This is done usually by trial, the contrast obtained with each mineral being observed upon the ground glass screen. visual trial method is only trustworthy when using a panchromatic plate which approximates the relative sensitiveness of the eye. The best panchromatic plate obtainable for this type of work is the Wratten M plate distributed by the East-

¹ Mees, C. E. Kenneth. "The Photography of Coloured Objects." Wratten and Wainwright, Ltd., London, 1913.

TABLE 11

TABLE 1			
Wratten filter	Visual color	Range of spectral transmission in $\mu\mu$ of wave length	
A	Scarlet	From 580 to red end	
B	Green	From 460 to 600	
C	Blue-violet	From 400 to 510	
D	Purple	From 380 to 460 and from 640 to red end	
E	Orange	From 560 to red end	
F	Pure red	From 610 to red end	
G	Strong yellow	From 510 to red end	
H	Blue	From 420 to 540	
K ₁	Pale yellow (very pale).	Wide range of lower spectrum	
K2	Pale yellow		
K ₃	Yellow		
D and H	Violet	About 450	
C and H	Blue	About 480	
B and C	Blue-green	About 500	
B and H	Bluish-green	About 520	
G and H	Pure green	About 535	
B and G	Yellowish-green	About 550	
B and E	Greenish-yellow	About 575	
A and D		About 660	

man Kodak Company. It has all the color sensitiveness of the true panchromatic plate, being even more sensitive to red light, and has an extremely fine-grained emulsion especially designed for microscopic photography. The worker along this line cannot do better than to use it exclusively. All of the data concerning proper filters and some of the factors for calculating exposures contained in this chapter are applicable only for use with the Wratten M plate.

Having chosen the proper filter, accurate focusing is the next important step. It is impossible to obtain sharp, clear cut negatives by focusing upon the ground glass screen alone. After an approximate focus is obtained on this screen it should be replaced by a plain glass screen upon which the final focus is made with the use of a lens. This screen should be very carefully removed and the photographic plate put in its place. Everything should now be ready for the exposure.

The data for calculating the proper exposure for different magnifications, sources of light, filters, etc., has been assembled

¹ From the booklet "Photomicrography" published by the Eastman Kodak Co.

by the Eastman Kodak Company and Tables 2 and 5 have been taken from their booklets.1 The formula for calculating exposures gives an approximate figure which should be tested experimentally for different types of subjects. The formula does not take this latter factor into consideration, but the same exposure obviously will not give equally good results on a section composed largely of white minerals and one in which dark gray minerals are dominant. The method of making the test exposure is as follows: If the formula indicates that an exposure of 20 sec, is about right, expose successive portions of the plate for 5, 10, 20, 40, and 80 sec, by pulling out the slide and then pushing it in one-fifth the width of the plate at the end of each of the above periods. The exposure should increase by geometric progression as indicated rather than by arithmetical progression such as 10, 15, 20, 25, and 30 sec., as the difference in density of negatives exposed 10 and 20 sec, respectively is twice as great as in those exposed 20 and 30 sec. respectively. With this test plate as a guide, the proper exposure can be easily determined.

In making the original exposure calculation the following formula is used:

Standard exposure × N.A. factor × source factor × magnification factor × filter factor = exposure in seconds.

The standard exposure used in the above empirical equation is taken as 10 sec.

The exposure varies inversely as the numerical aperture, N.A. of the objective. (The numerical aperture is an optical constant for a lens of given focal length.) The factors for the N.A. of the objectives are given in Table 2.

The source of light naturally is of the greatest importance in determining the length of exposure. In past publications the factors for the source of light have been adopted from data for transmitted light conditions. This has led to confusion because the polished surface does not reflect all of the light by any means, and consequently requires a longer exposure. Experience has shown that, on the average, the factor for reflected light is two to four times that for direct transmitted illumination. These factors for various sources of light are given in Table 3.

¹ "Photomicrography, Color Plates and Filters for Commercial Photography, and Reproduction Work with Dry Plates." Eastman Kodak Company, Rochester, N. Y.


TABLE 2

Focal length objective			
Inches	Millimeters	Average N.A.	Approximate ex posure factor
4	100	0.08	40
3	75	0.09	30
2	50	0.15	10
1	25	0.25	4
2/3	16	0.35	2
1/2	12	0.45	11/4
1/3	8	0.50	1
1/4	6	0.80	. 2/5
1/4 1/6	4	0.85	1/3
1/8	3	0.90	1/3
1/12	2	1.30	1/4

TABLE 3

Source of light	Exposure factor for M plate
Oil	3
Incandescent gas	1
Nernst lamp (1 amp.)	1/4
Acetylene	1/4
Direct current arc (5 amps.)	1/8
Direct current arc (10 amps.)	1/33
Direct current arc (30 amps.)	1/330

(It should be understood that the above factors are by nature very approximate, dependent entirely on arrangement and power.)

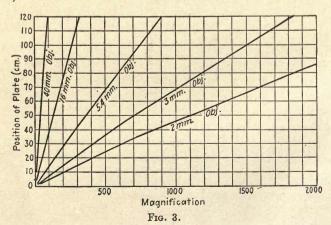

The greater the magnification, the longer is the required exposure. The degree of magnification depends upon the focal length of the objective, the projection eyepiece, the distance of the photographic plate from the objective, etc. It will be found convenient to prepare a set of curves for the instrument used, similar to those in Fig. 3, which have been calculated for the Leitz metallographic microscope.

In Table 4 the exposure factors for different magnifications are listed.

TABLE 4

Magnification	Exposure factor for M plate	Magnification	Exposure factor for M plate
10	1/100	600	36
25	1/16	750	56
50	1/4	900	81
100	1	1000	100
250	6	2000	400
500	25	2500	625

The factor for any magnification may be calculated on the basis that it increases with the square of the diameter.

The last variable in the exposure equation is the factor for the filter used. These factors are dependent upon the source of illumination since the different artificial lights have widely differing color values. Table 5 lists the multiplying factors for the filters, singly and in pairs, calculated for the open arc and the Wratten M plate.

TABLE 5

Filter	Factor (M plate and open arc)	Filter	Factor (M plate and open arc)
A	10	K ₂	. 3
B	18	K ₃	41/2
C	12	D and G	250
D	Only used in combination	A and D	240
E	8	B and E	250
F	15	G and H	1600
G	8	B and C	600
H	15	B and G	60
K_1,\ldots,K_n	11/2	D and H	60

The foregoing tables are used as follows: the approximate exposure for a photograph using a 16-mm. objective (Leitz

No. 3), a 5-amp. D.C. arc, magnification 50, and screen K₃ would be:

10 sec. $\times 2 \times \frac{1}{8} \times \frac{1}{4} \times \frac{9}{2} = 3$ sec. (approximately)


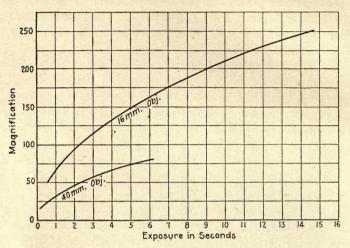


Fig. 4.

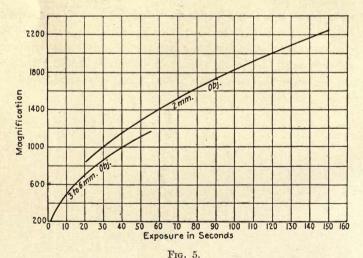

Figures 4 and 5 give the approximate exposures for an average specimen consisting, say, of galena, chalcopyrite, and sphalerite. These curves are calculated solely for the Wratten M plate. They are for the 5 amp. open arc, wide open stop, and without

filter. When a filter is used the value obtained from the curves should be multiplied directly by the filter factor taken from Table 5. These curves are plotted from theoretical values checked in practice and may be multiplied by a suitable factor when another light source is used.

The Wratten plate is very sensitive to red light and consequently must be opened and developed either in total darkness or in the light of the Wratten Safelight, series 3, a faint green light. With each box of plates an instruction sheet is enclosed giving the developing formula, proper temperatures, and times of development. These instructions, when followed, yield excellent results and should only be varied by the most experienced worker. In the course of the dark room treatment it will be found advisable to wash the carbon backing off the plates with a soft sponge while rinsing before placing in the fixing solution.

In preparing positives a glossy paper usually yields the most satisfactory detail and reproduces best. After developing and fixing the print should be pressed face down upon a ferrotype plate with a rubber roller and allowed to dry thoroughly, when they will peel off without sticking providing a sufficient amount of hardening solution has been used in the fixing bath. Small amounts of a special polishing solution can be used on the ferrotype plate when necessary and will eliminate sticking entirely. Such a solution is sold by Burke and James of Chicago, Ill.

CHAPTER III

THE USE OF THE DETERMINATIVE TABLES

The tables have been arranged with the idea of enabling the student to apply a uniform series of simple and positive tests at one time to all the different minerals present in appreciable amounts in the section. The following procedure in making determinations has been found to yield rapid and exact results. It must be appreciated that, as in all other things, experience and practice make for greater skill and, although it has been demonstrated that beginners can mechanically follow the tables with fair success, familiarity with the appearance and microchemical behavior of the common ore minerals naturally gives confidence to the worker. No one should attempt a serious application of this method of study to any problem without first applying it to a few of the common minerals.



Fig. 6.

The polished section of ore pictured in Fig. 6 has been chosen as an example. This particular ore is of value in this connection because it illustrates the variety of tests which go toward exact mineral determinations under the metallographic microscope.

The preliminary examination of the material should be done

systematically and the results recorded somewhat as in Table 6. The different minerals should be temporarily designated by number and a brief description of their appearance. The reagents used in the scheme of identification are preferably applied in their order in the tables and the reactions, if any, observed and recorded.

TABLE 6

1. Creamy white mineral 2. Yellow 3. Violet white with high relief HNO: Unaffected for some time, Neg. Slowly effervesces and but slowly tarnishes turns bluish brown with very slow effervescence HC1 Neg. Neg. Neg. KCN Neg. Neg. Neg. Medium High to medium Hardness Very high FeCl₃ Neg. Neg. Neg. (Pyrite) (Chalcopyrite) (Polydymite)

In first running down the unknown it is often most convenient to use the outline of the determinative tables, especially if the worker is familiar with the more common minerals by sight, because larger groups of minerals are seen at one time and slight uncertainties as to the results of one or more tests can be eliminated. (1) Readily falls out as pyrite, (2) as chalcopyrite, and (3) is limited to a small group of minerals. Of these, arsenopyrite, willyamite, kallilite, and niccolite all contain arsenic or antimony. Blowpipe tests applied to a small piece of the material gouged from the edge reveal neither of these elements and polydymite is indicated by a process of elimination.

However, since the mineral was dissolved readily by nitric acid, a qualitative microchemical test for nickel should be easily applied. (See Table 12, page 145, for list of these tests.) After a drop of nitric acid has remained on the supposed polydymite for a minute or two a drop of tartaric acid is added to keep iron in solution when a drop of concentrated ammonium hydroxide is next added to make the solution alkaline. If a drop of a solution of dimethyl glyoxime in alcohol is now added, a beautiful scarlet-red crystalline precipitate appears under the microscope. This proves the presence of nickel in the unknown and leads to the conclusion that it is polydymite.

The foregoing illustrates the general method to be followed in making identity determinations. All reactions and properties are utilized when necessary and the individual must be the judge as to how much evidence is needed in each case before reaching a decision. This in turn is dependent upon the individual's experience and familiarity with the properties of the different minerals as seen under the microscope in reflected light.

ABBREVIATIONS USED IN THE TABLES

B.B. = Before the blowpipe.

C. = Color seen megascopically.

Fus. = Fusibility.

HNO₃-E = Reacts with HNO₃ with effervescence.

HNO₃ = Visible reaction such as tarnish, etc. (Without effervescence in the case of HNO₃.)

HNO₃ -N = No visible reaction with HNO₃.

H = Hardness high.

L = Hardness low.

M = Hardness medium.

Microchem. = Microchemical tests.

O.F. = Oxidizing flame.

R.F. = Reducing flame.

S.Ph. = Salt of Phosphorus.

Str. = Streak.

OUTLINE OF THE DETERMINATIVE TABLE Effervesces with HNO₂

				Color	Mineral	Formula I	Page
HCl	KCN	M	FeCl ₂	Cream Creamy white Grayish white	Whitneyite Huntilite Cuprite	Cu ₉ As Ag ₃ As Cu ₂ O	33 33 33
		L	FeCl ₃	Creamy white Creamy white Purple Pink Bluish white Galena white	Chilenite Domeykite Rickardite (Native copper) ¹ (Chalcocite) (HESSITE)	Ag ₆ Bi Cu ₂ As Cu ₄ Te ₃ Cu Cu ₂ S Ag ₂ Te	35 35 35 51 51 66
			FeCl ₃ -N	Creamy white	(Aikinite)	3(Cu ₂ Pb)S.Bi ₂ S ₃	63
	KCN-N	н	FeCl ₃ -N	White (violet)	(Polydymite)	Ni ₄ S ₅	57
-		м	FeCl ₃ -N	Grayish white	ALABANDITE	MnS	41
		L	FeCl ₃	White White Creamy white Creamy white Creamy white Galena white Galena white	Naumannite Altaite Native silver Native bismuth Tapalpaite Plagionite (Galena)	(Ag ₂ Pb)Se PbTe Ag Bi 3Ag ₂ (STe).Bi ₂ - (STe) ₂ 5PbS.4Sb ₂ S ₃ PbS	43 43 43 43 43 77
			FeCl ₃ -N	Galena white White Galena white Galena white Grayish white Grayish white Galena white	Semseyite (Aikinite) (Plagionite) (Dognacskaite) (JAMESONITE) (ALABANDITE) (Horsfordite)	7PbS.3Sb ₂ S ₃ 3(Cu ₂ Pb)S.Bi ₂ S ₃ 5PbS.4Sb ₂ S ₃ Cu, Bi, and S 2PbS.Sb ₂ S ₃ MnS Cu ₆ Sb	45 63 43 63 62 41 63
HCl-N	KCN	н	FeCl ₃ -N	White	(Polydymite)	Ni ₄ S ₆	57
		М	FeCl ₃	Pink	(Native copper)	Cu	51
		L	FeCl ₃	Pink Bluish white Pinkish brown	Native copper Chalcocite (Bornite)	Cu Cu ₂ S Cu ₅ FeS ₄	51 51 53
			FeCl ₃ -N	Pinkish brown Creamy white Galena white	Bornite (Aikinite) (Stibnite)	Cu ₅ FeS ₄ 3(PbCu ₂)S.Bi ₂ S ₂ Sb ₂ S ₃	53 63 87
	KCN-N	Н	FeCl ₂	Creamy pink Pinkish white White	Niccolite Maucherite Smaltite	NiAs Ni ₂ As ₂ CoAs ₂	55 55 55

¹ Parentheses about a mineral indicate that it is not in its normal position.

Effervesces with HNO3

		Color	Mineral	Formula	Page
	FeCl ₃ -N	White	Arsenopyrite	FeAsS	57
	312	Violet white	Polydymite	Ni ₄ S ₆	57
		White	Willyamite	(CoNi)SbS	57
	48 489	White	Kallilite	Ni(SbBi)S	57
		Creamy white	Pyrite	FeS ₂	57
		Creamy white	Marcasite	FeS ₂	57
		Creamy pink	(Niccolite)	NiAs	58
M	FeCl ₃	Creamy white	Cosalite	Pb ₂ Bi ₂ S ₅	59
		Galena white	Native arsenic	As	59
L	FeCl ₃	Cream	Melonite	Ni ₂ Te ₃	61
		Creamy white	CALAVERITE	AuTe2-Ag	6:
		White	Native tellurium	Te	6
	1	Galena white	Rezbanyite	4PbS.5Bi ₂ S ₃	6
		Galena white	Tetradymite	Bi ₂ (Te, S) ₃	6
		Creamy white	(KRENNERITE)	AuTe2-Ag	6
		Creamy white	(Native silver)	Ag	4:
		Galana white	(Plagionite)	5PbS.4Sb ₂ S ₃	4
		Grayish white	(Petzite)	(Ag, Au) ₂ Te	9
	FeCl ₃ -N	Creamy white	KRENNERITE	AuTe2-Ag	6
	TO STORY	Creamy white	Emplectite	CuBiS ₂	6
		Creamy white	Chiviatite	Pb ₂ Bi ₂ S ₁₁	6
		Creamy white	Aikinite	3(PbCu ₂)S.Bi ₂ S ₃	6
	Lenga 5	Galena white	Dognacskaite	Cu, Bi, and S	6
	7	Galena white	Boulangerite	3PbS.Sb ₂ S ₃	6
	1.15%	Galena white	Horsfordite	Cu ₆ Sb	6
		Galena white	Bismuthinite	Bi ₂ S ₃	6
		Grayish white	REALGAR	AsŞ	6
25 27 27		Grayish white.	JAMESONITE	2PbS.Sb ₂ S ₃	6
	1000	Grayish white	Zinkenite	PbS.Sb ₂ S ₃	6
		Bluish Gray	Tungstenite	WS ₂	6
A TORING		White	(Native tellurium)	Te	6
(P = 1 / 1 / 1 / 1 / 1 / 1 / 1 / 1 / 1 / 1	100 - 50	Galena white	(Stibnite)	Sb ₂ S ₃	8

Reacts with HNO3-does not Effervesce

				Color	Mineral	Formula	Page
HCl	KCN	М	FeCl ₃ -N	Creamy white Galena white	Sulvanite (Guejarite)	Cu ₃ VS ₄ Cu ₂ Sb ₄ S ₇	65 83
		L	FeCl ₃	Creamy white Galena white	Dyscrasite Hessite	Ag ₃ Sb, Ag ₆ Sb, e Ag ₂ Te	66
	•0			Grayish white	Argentite Stromeyerite	Ag ₂ S (Ag,Cu) ₂ S	67 67
				Grayish white	Jalpaite	3Ag ₂ S.Cu ₂ S	67
				Brown	(Pyrolusite)	MnO ₂	101
			FeCl ₃ -N	Bluish white	Brongniardite	PbS.Ag ₂ S.Sb ₂ S ₃	69
	KCN-N	н	FeCl ₃ -N	Gray	PSILOMELANE	H ₄ MnO ₅	71
		М	FeCl ₃	Grayish white	TENORITE	CuO	73
			FeCl ₃ -N	Gray	Cuprodescloizite	(PbZnCu)4V2Os	
		-		100		H ₂ O	75
				Gray Grayish white	(Sphalerite) (Tenorite)	ZnS CuO	94 73
				Gray ISIT WILLIE	(IENORIE)	Cuo	
300	44	L	FeCl ₃	Purple	Umangite	Cu ₃ Se ₂	77
			1 N 130	White	Clausthalite Galena	PbSe	77
				Galena white	Lillianite	PbS 3PbS.Bi ₂ S ₃	77
	1			Grayish white	Teallite	PbSnS ₂	77
				Grayish white	Cylindrite	Pb6Sb2Sn6S21	77
				Grayish white	Aguilarite	Ag ₂ S.Ag ₂ Se	76
	W 100 200			White	(Native antimony)	Sb	96
				Creamy white	(Native silver)	Ag	43
			FeCl ₃ -N	Galena white	Meneghinite	4PbS.Sb ₂ S ₃	79
				Galena white	Geocronite	5PbS.Sb ₂ S ₃	79
				Grayish white	Franckeite	Pb ₅ Sn ₂ Sb ₂ S ₁₂	79
			1	White Grayish white	(Eucairite) (Cylindrite)	Cu ₂ Se.Ag ₂ Se Pb ₆ Sb ₂ Sn ₆ S ₂₁	97 77
		_					
HCl-N	KCN	M	FeCl ₃	Grayish white	(POLYBASITE)	Ag ₉ SbS ₆	87
		7	FeCla-N	Pinkish white	Luzonite	Cu ₃ AsS ₄	83
			1 3	Brownish white		Cu ₃ AsS ₄	83
				Pinkish white Galena white	FAMATINITE Guejarite	Cu ₂ SbS ₄ Cu ₂ Sb ₄ S ₇	83 83
24.5	L.		8	Grayish white	Freibergite	(Cu, Ag)8Sb2S7	
140				Yellow	(Chalcopyrite)	CuFeS ₂	117
SE S	S. E. S.			Creamy white	(Sulvanite)	Cu ₃ VS ₄	65
77 - 9	-	.1		Grayish white	(Tennantite)	Cu ₈ As ₂ S ₇	117
-				Grayish white	(Tetrahedrite)	Cu ₈ Sb ₂ S ₇	117
15	*	L	FeCl ₃	Grayish white	Pearcite	Ag9AsS6	85
17 311	IS IT			Grayish white	(Argentite)	Ag ₂ S	67
= = = =				Grayish white	(POLYBASITE)	Ag ₉ SbS ₆	87
	THE PARTY	7	3-1	Grayish white Bluish white	(Jalpaite) (Polyargyrite)	3Ag ₂ S,Cu ₂ S Ag ₂₄ Sb ₂ S ₁₅	67 109
			1	Didish white	(L organggine)	WESTONSOIS	109

Reacts with HNO3-does not Effervesce

						Page
		FeCl ₃ -N	Galena white	Stibnite	Sb ₂ S ₃	87
The second second			Galena white	KERMESITE	Sb ₂ S ₂ O	87
			Grayish white	POLYBASITE	AgoSbS6	87
			Galena white	(Livingstonite)	HgSb ₄ S ₇	111
KCN-N	н	FeCl ₃	White	Chloanthite	NiAs ₂	89
			White	Rammelsbergite	NiAs ₂	89
			White	GERSDORFFITE	NiAsS	89
		FeCl ₃ -N	White	Löllingite	FeAs ₂	91
			White	Ullmannite	NiSbS	91
			Creamy white	Linnæite	Co ₃ S ₄	91
1000000			Pinkish white	GLAUCODOT	(Co,Fe)AsS	91
			Cream	Hauchecornite	(NiCo)7(SSbBi)8	
	-		Cream	(Pyrrhotite)	$FeS(S)_x$	95
			Creamy white	(Pyrite)	FeS ₂	57
			White	(Chloanthite)	NiAs ₂	89
0.00			White	(GERSDORFFITE)	NiAsS	89
			White	(Willyamite)	(CoNi)SbS	57
	M	FeCl ₃ .	Pink	Breithauptite	NiSb	93
		FeCl ₃ -N	Pale yellow	MILLERITE	NiS	95
- 1		4 TO 31	Cream	Pyrrhotite	$FeS(S)_x$	95
			Cream	Chalmersite	CuFe ₂ S ₃	95
		(- L	Creamy white	PENTLANDITE	(Fe,Ni)S	95
			Creamy white	Wittichenite	Cu ₃ BiS ₃	95
Contract of	3		Galena white	Andorite	PbAgSb ₃ S ₆	95
			Grayish white	BOURNONITE	(PbCu ₂) ₃ Sb ₂ S ₆	94
		1	Grayish white	Stylotypite	3(Cu ₂ Ag ₂ Fe)- S.Sb ₂ S ₃	94
			Grayish white	Stannite	SnCu ₂ FeS ₄	94
		C - 200	Grayish white	Crookesite	(CuTlAg) ₂ Se	94
-7			Grayish white	Hauerite	MnS ₂	94
	30		Gray	Sphalerite	ZnS	94
			Yellow	(Chalcopyrite)	CuFeS ₂	117
			Creamy white	(Sulvanite)	Cu ₃ VS ₄	65
10 11 11 11	1		Pinkish white	(FAMATINITE)	Cu ₃ SbS ₄	83
	200		Gray	(Voltzite)	Zn ₅ S ₄ O	116
			Grayish white	(Tennantite)	Cu ₆ As ₂ S ₇	117
	L	FeCl ₂	White	Berzelianite	Cu ₂ Se	97
			White	Eucairite	Cu ₂ Se.Ag ₂ Se	97
			White	Native antimony	Sb	96
AT DESIGN	100		Creamy white	Kalgoorlite	HgAu2Ag6Te6	97
	-		Grayish white	Petzite	(Ag,Au) ₂ Te	97
A STATE			Grayish white	Coloradoite	HgTe	97
	30	10. 185	Grayish white	Molybdenite	MoS ₂	97
	1		Creamy white	(Native silver)	Ag	43
10-18-18			Galena white	(Plagionite)	5PbS.4Sb ₂ S ₃	43
			Grayish white	(Aguilarite)	Ag ₂ S.Ag ₂ Se	76

Reacts with HNO3—does not Effervesce


	Color	Mineral	Formula	Page
FeCl ₃ -N	Pale brown	Sternbergite	AgFe ₂ S ₃	99
	Galena white	Lengenbachite	Pbs(AgCu)2Ass	S13 99
	Galena white	Rathite	Pb(AsSb)S	99
	Galena white	Jordanite	Pb4As2S7	99
	Galena white	Guitermanite	3PbS.As ₂ S ₃	99
	Galena white	Epiboulangerite	Pb ₃ Sb ₂ S ₈	99
	Galena white	Galenobismutite	PbBi ₂ S ₄	98
	Galena white	Beegerite	Pb ₆ Bi ₂ S ₉	98
	Galena white	Freieslebenite	(PbAg2)5Sb4S11	98
THE RESIDENCE OF STREET	Galena white	Nagyagite	Au2Pb10Sb2Te6S	15 98
	Creamy white	Sylvanite	AuAgTe ₂	98
	Creamy white	Guanajuatite	Bi ₂ Se ₃	98
	White	(Eucairite)	Cu2Se.Ag2Se	97
	White	(Berzelianite)	Cu ₂ Se	97
	Creamy white	(Emplectite)	CuBiS ₂	63
	Galena white	(Stibnite)	Sb ₂ S ₃	87
THE PLANT OF THE PARTY OF THE P	Galena white	(Geocronite)	5PbS.Sb ₂ S ₃	79
	Galena white	(Andorite)	PbAgSb ₂ S ₆	95
	Grayish white	(Crookesite)	(CuTlAg)2Se	94
	Grayish white	(Regnolite)	Cu7A82S12	119
	Grayish white	(JAMESONITE)	2PbS.Sb ₂ S ₃	62

Does not React with HNOs

				Color	Mineral	Formula	Page
HCl	KCN	L	FeCl ₃	Grayish white Brown Grayish white Bluish white	STEPHANITE Pyrolusite (Jalpaite) (Proustite)	Ag ₅ SbS ₄ MnO ₂ 3Ag ₂ S.Cu ₂ S Ag ₃ AsS ₃	101 101 67
	KCN-N	 M	FeCl ₃ -N	Grayish white	Delafossite	CuO, Fe ₂ O ₃	103
HCI-N	KCN		FeCl ₂	Grayish white	(POLYBASITE)	Ag ₉ SbS ₆	87
					1 1 1 1 1 1 1 1 1 1 1 1 1 1 1 1 1 1 1		
			FeCl ₃ -N	Yellow Brownish white Grayish white	(Chalcopyrite) (Enargite) (PYRARGYRITE)	CuFeS ₂ Cu ₃ AsS ₄ Ag ₃ SbS ₃	117 83 111
		L	FeCl ₃	Bluish white Bluish white Grayish white Grayish white Grayish white	Proustite Polyargyrite Cerargyrite (Jalpaite) (Pearcite)	Ag3AsS3 Ag24Sb2S16 AgCl 3Ag2S.Cu2S Ag9AsS6	109 109 109 67 85
			FeCl₃-N	Blue Yellow Galena white Bluish white Grayish white Grayish white Grayish white Grayish white Bluish white Grayish white	Covellite Native gold Livingstonite Onofrite PYRARGYRITE Miargyrite Argyrodite ORPIMENT (Proustite) (POLYBASITE)	CuS Au HgSb4S7 Hg(SSe) Ag3SbS3 Ag5bS2 Ag6GeS6 As2S3 Ag3AsS3 Ag9SbS6	111 111 111 111 111 110 110 110 109 87
	KCN-N	н	FeCl ₃	Gray	Uraninite	UOa, etc.	113
			FeCl ₃ -N	White Pinkish white Creamy white Grayish white Gray (variable) Gray White	Sperrylite Cobaltite Hematite Magnetite Illmenite Rutile Franklinite Manganese Oxides Wolframite Rare earths Cassiterite Limonite Chromite (Löllingite)	PtAs ₂ CoAsS Fe ₂ O ₃ Fe ₃ O ₄ FeTiO ₃ TiO ₂ (FeZnMn)O. (FeMn) ₂ O ₃ (FeMn)WO ₄ SnO ₂ 2Fe ₂ O _{3.3} H ₂ O FeCr ₂ O ₄ FeAs ₂	115 115 115 115 115 115 115 114 114 114


Does not React with HNO3

			Color	Mineral	Formula	Page
	м	FeCl ₃ -N	Yellow	Chalcopyrite	CuFeS ₂	117
		- 22	Galena white	Chalcostibite	CuSbS ₂	117
			Galena white	Berthierite	FeSb ₂ S ₄	117
			Grayish white	Baumhauerite	Pb4As6S13	117
100		S 277	Grayish white	Tetrahedrite	Cu ₈ Sb ₂ S ₇	117
			Grayish white	Tennantite	Cus As2S7,	117
		10000	Gray	Voltzite	ZnsS4O	116
			Gray	Erythrozincite	(MnZn)S	116
			Pale yellow	(MILLERITE)	NiS	95
			Cream	(Pyrrhotite)	FeS(S)z	95
			Cream	(Chalmersite)	CuFe ₂ S ₃	98
			Creamy white	(PENTLANDITE)	(Fe, Ni)S	95
26			Grayish white	(Bournonite)	(PbCu ₂) ₃ Sb ₂ S ₆	94
	L	FeCl ₃ -N	Galena white	Dufrenoysite	Pb ₂ As ₂ S ₅	119
		F.E. 1912	Galena white	Matildite	AgBiS2	119
		- 1	Galena white	Lehrbachite	PbSe + HgSe	119
		THE B	Bluish white	Tiemannite	HgSe	119
			Bluish white	Vrbaite	TlAs2SbS5	119
			Bluish white	Stützite	Ag4Te	119
2/47	100		Grayish white	Regnolite	Cu7A82S12	119
		1	Grayish white	Seligmannite	CuPbAsS ₃	119
	100		Grayish white	Cinnabar	HgS	118
3			Grayish white	Metacinnabarite	HgS	118
	100		Grayish white	Patronite	VS ₄	118
		I EELVE	Gray	Lorandite	TlAsS2	118
			Galena white	(Freieslebentie)	(Pb, Ag2) 6Sb4S	11 98
			Galena white	(Berthierite)	FeSb ₂ S ₄	117
		WE -50	Galena white	(Lengenbachite)	Pb6(AgCu)2As4	
			Galena white	(Rathite)	Pb4(AsSb)S	99
S - 100			Grayish white	(Baumhauerite)	Pb4A86S13	117
			Grayish white	(Molybdenite)	MoS ₂	97
250	186	1800	Gray .	(Erythrozincite)	(MnZn)S	116

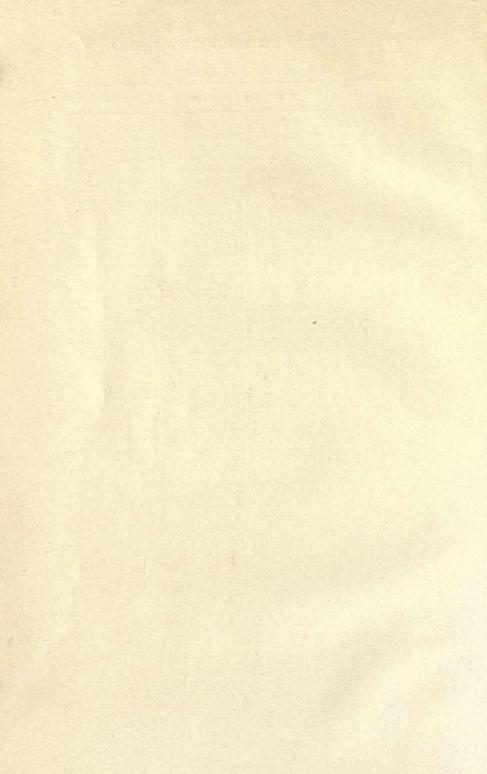

DETRESIDEATIVE TARGET

in meaning of reactives of experiences and distances such page to leave standard ballion below too.

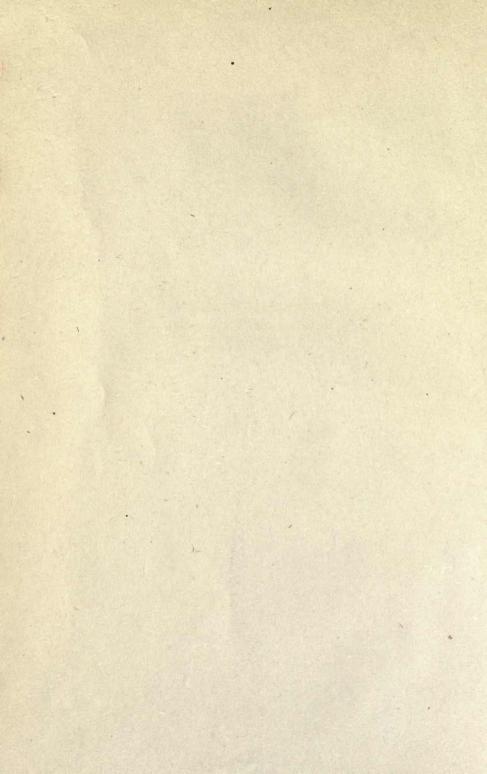

The state of the s

See summary of reactions at upper right hand corner of each page to locate minerals between thumb tabs.

See swampy of reactions at upper right hand corner of each page to locate major cladworn think tota.

CuaAs (Very Rare) Whitnevite Microchem. HNO₃, Effervesces and turns brown; rubs gray. HCl, Tarnishes and rubs to faint gray showing structure. KCN, Tarnishes Tarnishes and rubs to faint gray showing structure. KCN, Tarnishes brown; rubs gray with structure. FeCl₃, Quickly blackens; rubs to gray. HgCl₂, Quickly blackens with structure; rubs light brown with structure. KOH, Tarnishes faintly.

Hardness, Medium. 3.5. Very Sectile, Gray powder when scratched. Description. C. and Str.—Silver-white. Usually massive.

B.B. Yields arsenic coat on charcoal (Chap. IV, 2, a) and mirror in closed tube (IV, 2, c). Gives a guestly a general place course reliable general flame with

closed tube (IV, 2, c). Gives azure-blue copper chloride flame with HCl (IV, 6, b). Fus.—2.

CREAMY WHITE Huntilite¹ Ag₃As (very lease)
Microchem. HNO₃, Effervesces and quickly blackens; rubs to roughened

FeCl₃, Tarnishes iridescent; rubs to faint iridescence. KOH, Neg. Hardness, Medium. KCN, Slowly turns dark; rubs to clean roughened

Description. C.—Dark gray to black. Described from Silver Islet.

Lake Superior, as massive in occurrence.

B.B. Yields arsenic coat on charcoal (IV, 2, a) and mirror in closed tube (IV, 2, c). When reduced with the fluxes yields metallic silver (IV, 18, a).

GRAYISH WHITE Cuprite Cu₂O Microchem. HNO₃, Effervesces and forms a deposit of metallic copper; washes to coat of metallic copper; rubs gray. Fumes tarnish. HCl, Quickly darkens, forming a white coating as seen by inclined light; rubs faint. Fumes tarnish. KCN, Develops structure; rubs grayish. FeCl₃, Tarnishes; rubs to iridescence. Fumes tarnish. HgCl₂, Neg. KOH, Neg.

Hardness, Medium. 3.5-4. Slightly brittle, Blood red powder when scratched. Internal reflection seen by inclined light is deep red.

Description. C.—Red to nearly black. Str.—Shades of red or brown. With metallic copper it is found in the oxidized zone of all copper deposits.

B.B. In R.F. on charcoal yields metallic copper and colors the flame an emerald-green. Fus.-3.

¹ The microchemical reactions for minerals marked with an asterisk are from Murdoch, Joseph. "The Microscopical Determination of the Opaque Minerals." John Wiley & Sons. 1916.

Microchem, E.N.C., Effectedest und datas brownt ruits grav. 1813.
Themshose and rube to laint gray abouting atraction. CON, Tamishos brown; rube arry with structure. Tells. Onicity bisolated rails of proving the structure. And the structure with structures. Hard, Onicity that structure with structure. GOE, Themshos tainty.

Hardness Medium. L.S. Very Bortlin, Conv. poweder when sensished.

Description. C. and Six—Silver-while. Onest manager.

B.B. Very Season on charge of Conv. 19. 2 of and railroi in the structure of the charge of the structure structures structure structure structures stru

Lake Surgetor, as classive in occurrence.

B.B. Vields covered conductor (IV, 2. a) and mirror in closed tube (IV. 2. c). When reduced with the flower yields metallic of yer

Hardness Medium, 2.5-4. Shahily bristle Blood red powder when stratched, Internal reflection seem by applied light to deep red. Description, C.—Sied to nearly block. Str.—Shades of ned or brown. With metallic copper it is found in the auditsed zone of all copper de-

The migrospenies reactions for minerals marked with an asserial are from Murropen, Josepha. "The Microscopinal Entermination of the Operace

HNO-E HCI KCN Low FeCI.

CREAMY WHITE Chilenite* Ag₆Bi (Very Rare) Microchem. HNO, Effervesces and blackens; rubs to roughened surface. HCl, Turns brown; rubs to iridescent roughened surface. KCN, Turns

brownish; rubs clean. FeCl3, Tarnishes iridescent; rubs gray. KOH.

Hardness, Low.

Description. C.-Silver-white, tarnishing to yellowish. Described as amorphous and granular.

B.B. When reduced with the fluxes yields metallic silver (IV, 18, a). With KI & S flux yields brick-red bismuth coat (IV, 3, a).

CREAMY WHITE Domeykite Cu₃As (Very Rare)
Microchem. HNO₃, Quickly effervesces and blackens. HCl, Most specimens develop structure. KCN, Some portions tarnish faintly, some practically negative. FeCl₃, Quickly tarnishes; rubs to rough-

ened surface. HgCl2, Tarnishes brown; rubs faint. KOH, Quickly tarnishes; rubs clean.

Hardness, Low to medium. 3-3.5.

Description. C.—Steel gray. Str.—Gray. Occurs reniform, botroidal, massive, and disseminated.

B.B. Yields arsenic coat on charcoal (IV, 2, a). Gives azure-blue copper chloride flame with HCl (IV, 6, b).

Microchem. HNO₃, Blackens with violent effervescence. HCl, Turns pale bluish and dissolves to pitted surface. KCN, Bleaches to a pale tint. FeCl₃, Bleaches to brownish. HgCl₂, Bleaches to bluish-green. KOH, Tarnishes iridescent.

Hardness, Low. 3.5. Brittle.

Description. C. and Str.—Purple. Massive; fracture irregular.

B.B. On charcoal fuses easily to a brittle globule, yielding a pale azureblue flame tinged with green, and a white tellurium coat. Fus.-1.

PINK Native Copper See page 51.

BLUISH WHITE Chalcocite See page 51.

GALENA WHITE HESSITE See page 66.

Canasar Wurre Chilemis And (Very Rere) Microphem, MNO, Pilerwages and blackens, rubs to roughoned carlago. drownish; rubs clean, PoCL Tamishes indesecut; rubs grav, ECH.

Description, C .- Silver-white, tarnishing to yellowish. Described as B.B. When reduced with the flages violat mosalile edges (IV, 18, a)

With KI & S flux yields briefs and bianuth deal (IV. 8, a).

Cenasty Werrs: Designis Ou. As (Very Rare)
Alterochem. HNO, Quickly efferesses and blackers. HCl. Most
specimens develop structure. HCM, Some portions tarnish faintly,
some preciment develop structure. HCL, Quickly tarnishes; rubs to rosenened surface. HgCl., Tarnishes brown; rubs Isint. KOH. Quickly

Hardness, Low to medium. 3-3,5.
Description. "C.—Skeel gray. Str.—Gray. Occurs resiform, botroids). betweenest bas , syleson

B.B. Yields arrente coal on charcoal (IV, 2, c); Gives acure-blue coppor chloride flame with HOR (IV, 6, b).

there Mickerijis CulTes (Very Ram)
Microchem, HNO, Blackmas with violent ellervescence HCl, Turns
pais bluich and discover to pitted surface. KCN, Blacches to a pais
tint. FoCl, Bisaches to brownish. HgCl, Blacches to kinish-green.
KOH, Turnishes irribacent.
Hardness, Low, 2.5. Britis.
Description. Claud Str.—Furple. Massive, fracture irregular.

S.R. On charroal first easily to a brittle globule, violating a pain asureblue flame tinged with group, and a white tellurium cont. Tun-1,

Native Copper

HNO;-E HCl KCN Low FeCl;-N

CREAMY WHITE Aikinite See page 63.

HOPE HOPE THOUSE THOUSE

CREAMY WHITE Ablaits for page 53.

The control of the co

HNO-E HCl KCN-N High FeCl-N

VIOLET WHITE Polydymite See page 57.

HCI-M HCI-M HCI-M HCI-M

VIOLET WRITE Polydyndie (See mage 57.

HNO-E HCI KCN-N Med. FeCl_N

ALABANDITE MnS GRAYISH WHITE

Microchem. HNO₃, Effervesces and tarnishes; rubs gray, showing solution pits. Fumes tarnish brown. HCl, Nearly the same as with HNO₃. KCN, Neg. FeCl₃, Neg. HgCl₂, Fumes tarnish faintly; washes to pale brown; rubs clean. KOH, Neg. Hardness, Medium. 3.5–4. Sectile, but slightly brittle. Olive green

powder when scratched.

Internal reflection seen by inclined light is green.

Description. C.—Iron black. Str.—Green. Has perfect cubic cleavage. B.B. Shows manganese with the sodium carbonate bead (IV, 11, a). Fus.—3.

The Control of the Co

Conven Water Alapaners Mac.

Microbian HIVO, Elierwoose and famishes; tale gray, showing solution pits. Purces tarnish feners. HCL Nearly the same as with HIVO.

KCN Nec. FeCh, Ner. HcCl. Funes tarnish faintly; washes to pale hown; robe elson. KCH, Nag.

Macdanas, Maisten. S.b.s. Beetle, but slightly british. Office green

WHITE Naumannite* (Ag₂Pb)Se (Very Rare) Microchem. HNO₃, Quickly effervesces and blackens; rubs to roughened surface. HCl, Tarnishes slowly to iridescence. KCN, Neg. FeCl,, Tarnishes slowly brownish; rubs clean. KOH, Neg.

Hardness, Low. 2.5.

Description. C.-Iron-black. Str.-Black. Massive with cubic cleav-

Selenium odor and coat on charcoal (IV, 17, a and b). With KI & S flux yields lemon-yellow lead coat on charcoal (IV, 10, a). Yields silver button on cupellation (IV, 18, a). Fus.—2.

PbTe Altaite (Very Rare)

Microchem. HNO3, Effervesces and quickly darkens, developing crystals and tree-like forms resembling microlites; rubs to grayish etched surface. Fumes tarnish iridescent. HCl, Quickly browns; rubs to pale brown with white patches. KCN, Neg. FeCl₃, Quickly tarnishes brownish iridescent; rubs to gray, roughened surface. HgCl2. Neg. KOH, Neg.
Hardness, Low. 3. Sectile. Gray powder when scratched.
Description. C.—Tin-white. Str.—Gray. Has cubic cleavage.

B.B. Yields tellurium flame and coat on charcoal (IV, 20, a). Wi KI & S flux gives a lemon-yellow lead coat on charcoal. Fus.—1.5.

Native Silver CREAMY WHITE Ag Microchem. HNO₃, Effervesces slightly for a moment; rubs to gray, roughened surface. Fumes tarnish. HCl, Fumes tarnish slightly; rubs clean. KCN, Neg. FeCl₃, Tarnishes iridescent; rubs to iridescence. HgCl₂, Tarnishes gray; rubs to brownish gray. KOH, Neg. Hardness, Low. 2.5–3. Very sectile.

Description. C.—Silver-white. Str.—Silver-white. Usually in arbor-

escent, sheet, and wire forms.

B.B. Fuses easily on charcoal and yields a brown coat of silver oxide. (For other tests see IV, 18, a.) Fus.—2.

CREAMY WHITE

Microchem. HNO₃, Quickly effervesces and darkens; rubs to brownish gray. HCl, Slowly darkens; Fumes tarnish brown. KCN, Neg. FeCl₃, Darkens quickly. HgCl₂, Slowly deep brown; rubs to brown. KOH, Neg.

Hardness, Low. 2-2.5. Very Sectile.

Description. C.-Reddish silver-white. Str.-Silver-white. Arbores-

B.B. On charcoal fuses easily and volatilizes completely, yielding yellow sublimate. With KI & S flux gives brick-red coat on charcoal.

CREAMY WHITE Tapalpaite* 3Ag₂(STe).Bi₂(STe)₃? (Very Rare) Microchem. HNO₃, Quickly effervesces and darkens; rubs to dark, rough surface. Fumes tarnish. HCl, Faintly tarnished; rubs clean. Fumes same. KCN, Neg. FeCl₃, Quickly darkens; rubs to gray, roughened surface. KOH, Neg.

Hardness, Low.

Description. C.—Pale steel-gray. Str.—Gray. Massive.

B.B. Yields tellurium flame and coat on charcoal (IV, 20, a). With KI & S flux gives brick-red bismuth coat on charcoal (IV, 3, a). Fus.—1.

5PbS.4Sb₂S₃ GALENA WHITE Plagionite (Very Rare)

Microchem. HNO₃, Slowly darkens with slight effervescence; rubs to light gray. HCl, Acid negative, but fumes tarnish bright brown. KCN, Neg. FeCl₃, Turns brown; rubs pale brown. HgCl₂, Neg. KOH, Slowly iridescent; rubs clean.

Hardness, Low. 2.5. Brittle. Gray powder when scratched.

Description. C.—Blackish gray. Str.—Black.

B.B. Yields antimony coat and sublimates (IV, 1, a-d). With KI & S flux gives lemon-yellow lead coat (IV, 10, a). Fus.—1.

Galena GALENA WHITE See page 77.

Weigner Newmanning (Ag-Ph)Se-Mimochem, RIVO, Guloldy effectivenessind blankens; rule to requirement wireless, RC3, Textishes storic to indescence, RCN, Neg. 1eCl., Tornishes storic brownish; rule clean, ROR, Neg.

Hardness, Law, 2.5.
Description, C. Iron-black, Str.—Black, Massive with subjective.

B.B. Selections odor and coat on charcoal (IV, 27, e and b). With MI & N first yields formon valley lead outs on thereford (IV, 10, v). Yields silver button on outsilizion (IV, 18, a). Fus - 2

Microshena, 1100, Phorocox and quakly darkets, developing on a sortage. Finnes tarnish indexcent. BCl. Quickly browns; robe to paid brown with white patches. BCN, Neg. 30 Cl. Quickly tarnishes browned indexcent; rubs to gray, roughood surface. HgCl. Neg. KOH, Neg.

Haviness, Low 3, Swella Cray powder when scratched.
Description. C.—Tra-white, Six—Grey. Has cuffic alegence.
B.B. Vields tellursup flates and rost on obsercal (IV, 20, a), With

CHESAY WHITE- Native Silver Misser that the matter alvest Age moments where the second management of the managem

Care ar Warra Notice Bismuth Bi (Very Rare)
Microchem, HNO, Chielly efferences and darkens; rubs to brownish
grac, HC, Slowly clarkens; Punes tarnish brown, KLV, Neg. Darkens quickly. HgCla Slowly deep brown; inbe to brown.

Hardness Low. 2-2.5. Very Seetlle.

B.B. On charcoal finess couly and volatilizes completely, yielding yellow sublimate. With EL & S flux gives blick-red coak on chargons.

CREAMY WRITE Topologists SAge(STe), His (STe) 27 (Very Rare) Microschem, HNO, Quickly effervesses and devices; rubs to lank, rough author, Funes tarnish, HCl. Fainty tarnished rubs of en. Tunes same, ECV, Veg. Folk, Quickly darkins; rubs to gray roughened

C.—Pale steel-gray. Str.—Gray. Massive. B.S. Yields tellurage flame and cost on charged (IV, 20, a) With KI S.S. flam gives breezest bismuch cost on charcont (IV, 20s). France Granns Where Pingionits 5158 150,88 (Very Rare)

Microchem, 1100, Slowly darkens with slight effert escence; rate to light eras, HCl. teld negative, for tumes tarnish itsight brown, RCV, Neg. Fed., Turns trown; rubs pale brown, HgCl. Neg.

Hardnes, Lew J.A. British Conv. powder when stratehed.

Description, C.—Blackish grav., For—Black.

B.E. Yields satismass coat and sublimates (R. E. a.-d.). With El & S.

for gives leaven-reliew lead coat (R. 10 a.-d.). With El & S.

HNO-E HCI KCN-N Low FeCl₂-N

DETERMINATIVE TABLES

GALENA WHITE Semseyite 7PbS.3Sb₂S₃ (Very Rare) Microchem. HNO₃, Slowly effervesces and blackens; rubs gray. Fumes tarnish brown. HCl, Slowly faint brown; rubs clean. Fumes tarnish. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Some specimens unaffected; others faintly tarnish brown. Hardness, Low. Brittle. Gray powder when scratched.
Description. C.—Gray. Str.—Black. Tabular.
B.B. Yields antimony coat and sublimates (IV, 1, a-d). With KI & S flux gives lemon-yellow coat (IV, 10, a). Fus.—1.

WHITE	Aikinite	See page 63.
GALENA WHITE	Plagionite	See page 43.
GALENA WHITE	Dognacskaite	See page 63.
GRAYISH WHITE	JAMESONITE	See page 62.
GRAYISH WHITE	ALABANDITE	See page 41.
GALENA WHITE	Horsfordite	See page 63.

Garria Wirter Seneglis Trbil 38biS. (Very linte)
Microchem, HNO, Slowly offerseens and itseless rubs gist. Forces
farmish brown, HNS, Slowly filest brown, rubs drain, Xunes neithele
farmish brown, HNS, Slowly filest brown, rubs drain, Xunes neithele
HCC, Fulk TeCl. Nog. (1gCh. Neg. 1gCh. rubse spontanea must
lested, others musty targets from
Hardman Kow. Frith: Mary provider when seterated.

Hardman Kow. Frith: Mary provider when seterated.

Descripting. C. Gray Shr.—Hast. Tabulan.

Like Trbilla and soon goest and subfinition (IV, 1, re.). With KL & S
flat gives isomory cluw cost (IV, 30, a). Fus.—1.

HNO₃-E HCl-N KCN High FeCl₃-N

VIOLET WHITE Polydymite

See page 57.

DEFERMINATIVE TARLES

VESTET WHITE Polydemile See page 57.

HNO₃-E HCl-N KCN Med. FeCl₂

PINK Native Copper See page 51.

HAON MCM MCM MAL MAL MCM MCM MCM

MELENTE TABLES

Programme Copper ... See page 51.

Native Copper Cu PINK Microchem. HNO₃, Effervesces without tarnishing; rubs to roughened surface. HCl, Neg. (Sometimes tarnishes faintly.) KCN, Slowly browns; rubs to clean roughened surface. FeCl₃, Quickly darkens and dissolves. HgCl₂, Quickly blackens; rubs to iridescence. KOH, Slowly turns brown to bluish; rubs bluish.

Hardness, Medium. 2.5-3. Sectile. Pink when scratched. Description. C.—Copper-red. Str.—Shining. Malleable, ductile. Shows arborescent and irregular structures. Occurs in oxidized zone of all copper deposits.

B.B. Easily fusible, yielding an emerald-green flame in the O.F. On

charcoal becomes black after fusion.

BLUISH WHITE Chalcocite Cu₂S Microchem. HNO₃, Effervesces vigorously, turning blue, and developing cracks or cleavage; rubs same. HCl, Tarnishes very slightly. KCN, Quickly blackens; rubs to etched surface, with structure. FeCl₃, Tarnishes slightly. HgCl₂, Tarnishes slightly. KOH, Neg. Hardness, Low. 2.5–3. Very Sectile. Gray powder when scratched. Description. C. and Str.—Dark lead-gray, tarnishing to blue on ex-

posure. Occurs in zone of secondary enrichment in all copper deposits.

B.B. Fuses easily and boils with spirting. Powdered and roasted without fusing, then heated in R.F., yields metallic copper. Fus.-2-2.5.

PINKISH BROWN Bornite See page 53.

B.E. Fashy fusible, violding an emorald-green flame in the G.R. On charcoal becomes blook after fusion.

Barren Finera Chalcodita Ong.

Microbona, RNO, Effervence vicescole, turning blue, and developing cracks or cleavage; rubs same. M.G. ternishes were slightly. M.C., Goledy bindices: rubs to exceed surface, with attacture. P.G., Tarnishes slightly. HgCla, Tarnishes slightly. HgCla, Tarnishes slightly. HgCla, Tarnishes slightly. MgCla, Tarnishes slightly. MgCla, Tarnishes slightly. MgCla, Tarnishes slightly. MoR. Nec. Handles and the Carn. powerier when consistent. Death of the Occurs in tone of secundary enrashment in all copper deposits. Occurs in tone of secundary enrashment in all copper deposits.

HNO-E HCI-N KCN Low FeCl -N

PINKISH BROWN Bornite CusFeSa

Microchem. HNO₃, Effervesces and turns yellowish brown; rubs to brown etched surface. Fumes tarnish. HCl, Neg. KCN, Browns; rubs to dark etched surface. Fumes tarnish. FeCl₃, Neg. HgCl₂, Neg. KOH, Neg.

Hardness, Low. 3. Sectile. Golden-brown powder when scratched. Description. C.—Copper-red to brown; purplish bronze from tarnish. Str.—Grayish black. Massive. Common in most copper deposits.

B.B. Fuses easily on coal in the R.F. to a magnetic globule. Roasted and reduced with sedium carbonate, yields malleable conner buttons. and reduced with sodium carbonate, yields malleable copper buttons (IV, 6, a). Fus.—2.

CREAMY WHITE Aikinite See page 63.

GALENA WHITE Stibnite See page 87. DETERMINATIVE TARKER

N-IOE N-IOE NO.

Premiest Burers Bernite (Jugeps)
Microchem Hillo, Ediarveness and furns reliewed frown; rules to
here stained surfaces. Former families. HCM, New HCM, browner,
roles to dark etched surface, France targists. LuCh, New Hillo,
New LOH, New Leavest

Canadar White Adducts Simple 68.

Garana Warris Silbuite Dec page 87.

CREAMY PINK Niccolite NiAs

Microchem. HNO₃, Effervesces and tarnishes with etching; rubs to gray, etched surface. Fumes tarnish. HCl, Neg. KCN, Neg. FeCl₃, Slowly tarnishes brown; rubs to pale brown. (Some specimens show this reaction very weakly.) HgCl₂, Tarnishes brown; washes to persistent brown. KOH, Neg.

Hardness, High. 5-5.5. Very brittle. Gray powder when scratched.

Description. C.—Pale copper-red. Str.—Brownish. Occurs massive

and disseminated.

B.B. Fuses easily on coal to brittle globule, yielding arsenical odor and possibly a white coat of oxide. With dimethyl glyoxime gives a red precipitate (IV, 14, b).

Maucherite NiaAs2 (Very Rare) PINKISH WHITE

Microchem. HNO₃, Effervesces and blackens quickly; rubs to gray, rough surface. HCl, Neg. KCN, Neg. FeCl₃, Slowly tarnishes brownish; rubs faint. HgCl₂, Faintly browns; rubs clean. KOH,

Hardness, High. 5. Very brittle. Gray powder when scratched.

Description. C.—Reddish silver-white, tarnishing gray copper-red. Str.—Blackish gray.

B.B. Same as niccolite. (Note: Temiskamite is not a mixture, but a homogeneous mineral identical with Maucherite.)

Smaltite CoAs₂

Microchem. HNO₃, Quickly effervesces and darkens; rubs to gray, showing lath structure. Fumes tarnish. HCl, Neg. KCN, Neg. FeCl₃, Slowly tarnishes brownish, showing structure; rubs pale. (This reaction is not always decisive.) HgCl2, Slowly browns; rubs clean. KOH,

Hardness, High. 5.5-6. Brittle.

Description. C.—Tin-white. Str.—Gray-black. Occurs massive. B.B. Easily fusible on charcoal, yielding a magnetic globule and an arsenical odor; may yield a white arsenic coat. With borax shows a persistent cobalt blue (IV, 5, a). Fus.—2.5.

(Safflorite is the same as smaltite.)

CHEVARY PINK Wiccolffs Wide Stricture with obding; side to Manyochien, HWO, Maryesons and tarticles with obding; side to

Hardanes High. N. 3.8. Very brittle. Gray powder as has sensitived.

Description. C.—Pale copper-red. Rer.—Brownish. Goods massive and disserringsed.

B.R. Frame satily on onal to builtie globule, yielding atsocial oder and possibly a white cost of exide. With discount glybung gives a red

Printed Warth Mandardie Night, (Very fight)
Microciam, HNO, Effect seem and blackens quickly table to the,
touch surface, HCl, Neg, HCN, Neg, Fold, Slowly taroubles
brownels, substant, HgCl, Feintly browns, rube date, ROld,

Hardness, Mark. & Teer brittle. Oncy powder when extratehed

(Norm: Teministrative is not a mixture, but a homogeneous mixeral

Winter Smallite CoAs.
Microchem, 4100, Calcidy effervences and darkens; robe to gray, showing larg lath structure. Primes tarsish, 4101, Nog., MCM, Nog. Facility Story tarnishes brownish, showing structure; rube nule. (This resolute

Description, C.-Turwhite, Str.-Grav-black, Occurs massive B.B. Tasily ratiols on charroul, redding a manneste globule and na areanical odor; may yield a white preente cost. With horex above a MITE Arsenopyrite FeAsS
Migrochem. HNO₃, Slowly effervesces and quickly tarnishes through
iridescence to deep brown; rubs to roughened surface. HCl, Neg.
KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Neg.
Hardness, High. 5.5-6. Brittle. Gray powder when scratched.
Description. C.—Silver-white to steel-gray. Str.—Grayish black. Oc-

curs as orthorhombic crystals, massive, granular, or compact.

B.B. On charcoal fuses easily to brittle magnetic globule and evolves arsenic odor. In the closed tube it yields first an arsenious sulphide sublimate and then an arsenic mirror. Fus.-2.

VIOLET WHITE Polydymite Ni₄S₅ (Very Rare)
Microchem. HNO₂, Slowly effervesces and turns to brownish or bluish;
rubs to brown or blue, showing structure. HCl, Neg. (Acid turns
green, but surface washes clean.) KCN, Neg. FeCl₃, Neg. HgCl₂,
Neg. KOH, Neg.

Hardness, High. 4.5. Brittle. Description. C.—Steel-gray. Str.—Grayish black.

B.B. With dimethyl glyoxime yields red precipitate (IV, 14, b). Fus.—

Willyamite* (CoNi)SbS (Very Rare) WHITE Microchem. HNO₃, Slowly effervesces and turns dark brown; rubs gray, showing etching. HCl, Neg. KCN, Neg. FeCl₃, Neg. KOH, Neg. Hardness, High. 5.5.

Description. C.—Tin-white to steel-gray. Str.—Grayish black. Perfect cubic cleavage. Massive. B.B. Tests for cobalt, nickel, and antimony in Chapter IV.

Kallilite* Ni(SbBi)S? (Very Rare) WHITE Microchem. Like Willyamite. Hardness, High to medium. Description. C.-Light bluish gray. Str.-Black. Massive. B.B. Tests for nickel, antimony, and bismuth in Chapter IV.

CREAMY WHITE Pyrite FeS2 Microchem. HNO3, Very slowly effervesces and faintly browns; rubs to faint brown. Fumes tarnish slowly. Other reagents negative. Hardness, High. 6-6.5. Cannot be scratched. Description. C.—Light brass-yellow. Str.—Greenish to brownish black. Pyrite is the most common of all sulphides and usually the oldest. B.B. Becomes magnetic on charcoal in the R.F. Fus.—3.

CREAMY WHITE Marcasite FeS2 Microchem. Like Pyrite. Hardness, High. 6-6.5. Description. Like Pyrite except in crystal form and in occurrence. It occurs always as a secondary mineral. B.B. Like Pyrite.

CREAMY PINK Niccolite See page 55.

Warrs Arsenopyrite Felics, and enighty is righes through redescence to dues from the to remede a device. MCL Aug. RCN Res. Beck, Nec. McCl. Nr. ROB No. Harden Aleb. 5.5-8. 19646. One powder when contained Description. C.—Silvers hills to steel-crs. Res.—Crayler hills. On

Victor William Polydentts M.St. (Very Rate)
Microchem. HWO, Slowly offerwasses and burns to brownish or bloken rates to bround or blus, showing attractive. HCL Neg. (Acid terries group, but envises washes about, 2 4ClN, Meg. 18Ch, Neg. HgCl.,

Carager Whith Frethe Feb.

Microchem. HNOs, Very slowly effected and laintly browner pulse to faint brown. HNOs, Very slowly effected and laintly browner pulse. It faint brown. Forces tarned blowly. Other reagents negative.

Discription. C.—Light break-vellow, till.—Greenish to movemels black.

Exite as the reast common of all sulphides and usually the oldest.

HNO-E HCI-N KCN-N Med. FeCl.

Microchem. HNO₃, Instantly effervesces and blackens; rubs to dark gray. Fumes tarnish. HCl, Neg. (Sometimes slowly faint tarnish; rubs clean.) KCN, Neg. FeCl₃, Very slowly faint brown; sometimes appears negative. HgCl₂, Fumes tarnish; rubs clean. KOH, Tarnishes brown to iridescent CREAMY WHITE

nishes brown to iridescent. Hardness, Medium to low. 2.5–3. Brittle. Gray powder when scratched.

Description. C.—Lead-gray. Str.—Grayish black.

B.B. With KI & S flux shows both lead and bismuth (IV, 3 and 10). Fus.-1.5.

GALENA WHITE Native Arsenic As (Very Rare)
Microchem. HNO₃, Instantly blackens with slow effervescence; rubs to
brownish gray. HCl, Neg. KCN, Neg. FeCl₃, Quickly darkens
to persistent brownish. HgCl₂, Slowly tarnishes pale brown; rubs
faint. KOH, Neg.

Hardness, Medium to low. 3.5. Sectile, but slightly brittle. Gray

powder when scratched.

Description. C.—Tin-white. Str.—Gray. Has a basal cleavage. B.B. Yields white arsenic oxide coat on coal and easily volatilizes without fusion.

Electrical Proof Section 1991

Electrical English Control Proof Section 1992

Electrical Control

HWO. E HCJ-W KCH-W Met. FeCh

Cerxar Wirrs Couric Philips, (Very Rate)
Microthem HNC, instably efferences and blackers; role to dark
gray. Funce turned, HCl, Neg. (Sometimes slowly faint careable
rubs ofens.) HCN, Neg. FeCs. Very Slowly faint brown; concetting
spreads negative. HgCl, Phines termini; rubs clean. KOH, Carmakes brown to rich secon.

Hardrey Middlant to turn. 25-2. Brittle. Gray pawder whom secretabled.

Description of C. Lead-gray. Str. - Gray pawder whom secretabled.

B.R. With KH & State story soon load and bismoin (IV, 2 and 10).

B.B. With KI & S the shows both load and bismuth (IV, 3 and 10). Fus.—1.5.

Garma White Notice Arrests As (Very Rare)
Memochem, HNG, Instantiv blankens with stow after exercice, rubs to
brownish gray, HCl, Neg. HCN, Neg. FaCls, Quickly darkens
to presistent brownish, the HCN, Neg. FaCls, Quickly darkens
faint. HCH, McH, McCls, Routy tarnishes pale brown; rubs
faint McH, McH, McH, Low, S.A., Sentile, but slightly brittle. Gray
powder when sensebite.
Description, C.—Tim-white, but —Gray, Has a least cleavage,

Description, vi.—The white, the —tray time a mass steayage, B.B. Vields white actoric oxide cost on cost and easily vulnatures without fusion.

HNO3-E HCI-N KCN-N Low FeCl.

Microchem. HNO₃, Quickly effervesces and blackens; rubs gray. HCl, Neg. KCN, Neg. FeCl₃, Slowly tarnishes; rubs faint. KOH, Neg. Hardness, Low.

B.B. Easily fusible, but not entirely volatile, yielding white coat on charcoal and coloring flame bright green (IV, 20, a). With dimethyl glyoxime gives a red precipitate (IV, 14, b).

CREAMY WHITE CALAVERITE Au Te₂ + Ag
Microchem. HNO₃, Slowly effervesces and turns brown; rubs to lighter
brown with etching. HCl, Neg. KCN, Neg. FeCl₃, Slowly tarnishes
brown; rubs to faint brown.

HgCl₂, Neg. KOH, Tarnishes pale
brown; rubs to faint brown.

Hardness, Low. 2.5. Brittle. Gray powder when scratched.

Description. C.—Silver-white. Str.—Gray.

B.B. Gives white coat on charcoal and colors flame bright green.

Roasted and reduced with sodium carbonate, yields gold and silver;

sometimes reduces to gold bead easily without soda. Fus.—1.

HITE Native Tellurium Te (Very Rare)
Microchem. HNO₃, Quickly effervesces and blackens; rubs to gray,
rough surface. HCl, Neg. KCN, Neg. FeCl₃, Slowly tarnishes WHITE iridescent. KOH, Neg. ardness, Low. 2-2.5.

Hardness, Low. Somewhat sectile. Gray powder when scratched.

Description. C.—Tin-white. Str.—Gray. Has prismatic cleavage. B.B. Easily fusible and volatile, yielding a white coat on charcoal and coloring the flame bright green (IV, 20, a). Fus.-1.

GALENA WRITE Rezbanyite 4PbS.5Bi₂S₃ (Very Rare)
Microchem. HNO₃, Effervesces and tarnishes iridescent; rubs to gray
etched surface. Fumes tarnish. HCl, Neg. KCN, Neg. FeCl₃,
Slowly faint brown. HgCl₂, Neg. KOH, Neg.
Hardness, Low. 2.5-3. Brittle. Gray powder when scratched.
Description. C.—Lead-gray. Str.—Grayish black. Massive.
B.B. With KI & S flux shows both lead and bismuth (IV, 3 and 10).

May be isomorphous with small amounts of copper and silver.

GALENA WHITE Tetradymite Bi₂(Te,S)₃ Microchem. HNO₃, Quickly tarnishes with vigorous effervescence; rubs iridescent. HCl, Neg. KCN, Neg. FeCl₃, Tarnishes slightly, developing scratches. HgCl₂, Neg. KOH, Neg. Hardness, Low. 1.5–2. Slightly sectile.

Description. C.—Steel-gray, splendent. Str.—Gray. Perfect basal cleavage. Soils paper.

B.B. On charcoal fuses, gives white fumes and entirely volatilizes; tinges the R. F. bluish-green; coats the charcoal at first white and finally orange yellow

CREAMY WHITE KRENNERITE See page 63. Native Silver CREAMY WHITE See page 43. GALENA WHITE Plagionite See page 43. GRAYISH WHITE Petzite See page 97.

Galena White Bismuthinite Bi₂S₃ (Very Rare)
Microchem. HNO₃, Blackens with slow effervescence; rubs to gray, roughened surface. HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Tarnishes brown; rubs to faint brown. KOH, Neg. Hardness, Low. 2. Slightly brittle. Gray powder when scratched. Description. C.—Lead-gray.
B.B. With KI & S flux gives a brick-red bismuth coat on charcoal (IV, 3, a). Fus.—1.

REALGAR ASS Grayish White Realgar AsS

Microchem. HNO₃, Effervesces without visible change. HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Tarnishes brown to black with solution. Hardness, Low. 1.5-2.

Internal reflection seen by inclined light is orange.

Description. C.—Dark orange-red. Str.—Lighter. Occurs with anti-

mony, arsenic, and silver ores.

B.B. On charcoal in the O.F., burns, yielding arsenic odor and no residue when pure. In closed tube yields cherry-red sublimate of arsenic sulphide. Fus.-1.

JAMESONITE 2PbS.Sb₂S₃ GRAYISH WHITE

Microchem. HNO3, Quickly brown to black with very slow effervescence (Eff. often not detected); rubs to iridescent gray. HCl, Neg. Fumes tarnish slowly; rubs faint. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Slowly develops grain structure; some grains are iridescent, others gray.

Hardness, Low. 2-3. Brittle. Gray powder when scratched. Description. C.—Steel-gray. Str.—Grayish black. Perfect basal cleav-

age. Occurs fibrous or massive. B.B. Yields antimony and lead coat on charcoal (IV, 1 and 10). With KI & S flux gives lemon-yellow lead coat on charcoal (IV, 10, a).

Zinkenite PbS.Sb₂S₃ (Very Rare) GRAYISH WHITE Zinkenite PbS.Sb₂
Microchem. Like Jamesonite.

Hardness, Low. 3-3.5. Description. C. and Str.—Steel-gray. Occurs in columnar crystals, striated lengthwise, also fibrous and massive.

B.B. Like Jamesonite.

BLUISH GRAY

Microchem.

Microchem.

Microchem.

Microchem.

HNO₃, Does not change color, but effervesces after a few moments.

HCI, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Quickly tarnishes brown; rubs clean. KOH, Neg.

Hardness Low 25

Hardness, Low. 2.5.
Description. C.—Dark lead-gray. Str.—Dark gray. Marks paper.

B.B. See tests for tungsten (IV, 25).

WHITE Native Tellurium See page 61.

Stibnite GALENA WHITE See page 87.

KRENNERITE AuTe₂ + Ag CREAMY WHITE Microchem. HNO₃, Slowly effervesces and turns brown; rubs to lighter brown with etching. HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Tarnishes pale brown; rubs to faint brown.

Hardness, Low to medium. 2.5. Sectile, but slightly brittle. Grav

powder when scratched.

Description. C.—Silver-white. Str.—Gray. Has perfect basal cleavage. (Calaverite lacks this perfect cleavage.)

B.B. Gives white coat on coal and colors flame bright green. Roasted

and reduced with sodium carbonate yields gold and silver; sometimes reduces to gold bead easily without soda. Fus.—1.

CREAMY WHITE Emplectite

Microchem. HNO₃, Effervesces slightly and tarnishes pale brown; rubs clean. Fumes tarnish faintly. HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Tarnishes very slowly brown; rubs clean. Hardness, Low. 2. Slightly brittle. Gray powder when scratched.

Description. C .- Grayish white. Str.-Black.

B.B. Yields azure-blue copper chloride flame with HCl (IV, 6, b). With KI & S flux gives brick-red bismuth coat on charcoal (IV, 3, a). Fus.—1.

CREAMY WHITE Chiviatite* Pb2Bi2S11 (Very Rare)

Microchem. HNO₂, Slowly effervesces and turns iridescent to gray; rubs to clean, somewhat roughened surface. HCl, Neg. KCN, Neg. FeCl₃, Neg. KOH, Neg.

Hardness, Low.

Description, C.-Lead-gray, Str.-Grayish black, Commonly foliated.

With KI & S flux shows both lead and bismuth (IV, 3 and 10).

3(PbCu₂)S.Bi₂S₃ (Very Rare) CREAMY WHITE Aikinite

Microchem. HNO3, Effervesces and blackens; rubs to heavy gray. Fumes tarnish brown. HCl, Neg. KCN, Neg. (Some specimens very slowly browned; rubs clean.) FeCl₃, Neg. HgCl₂, Neg. KOH, Neg. Hardness, Low. 2-2.5. Brittle. Gray powder when scratched.

Description. C.-Lead-gray. Str.-Grayish black.

B.B. Gives azure-blue copper chloride flame with HCl (IV, 6, b). With KI & S flux shows both lead and bismuth (IV, 3 and 10). Fus.-

GALENA WHITE Dognacskaite Cu, Bi, and S (Very Rare)
Microchem. HNO₃, Quickly effervesces and turns iridescent to black;
rubs to gray, roughened surface. Fumes tarnish. HCl, Neg. Fumes tarnish brown; rubs to pale brown. KCN, Neg. FeCl₂, Neg. HgCl₂, Neg. KOH, Neg. Hardness, Low. Very Sectile. Gray powder when scratched. Description. C.—Gray, tarnishing on exposure to the air.

B.B. Same as Emplectite.

GALENA WHITE Boulangerite 3PbS.Sb₂S₃ (Very Rare) Microchem. HNO3, Effervesces and blackens; washes to etched structure. Fumes tarnish light brown. Other reagents negative.

Hardness, Low. 2.5-3. Sectile, but slightly brittle. Gray powder when

scratched.

Description. C.—Bluish lead-gray. Str.—Black. Occurs fibrous, granular, or compact.

B.B. Like Jamesonite.

GALENA WHITE Horsfordite Cu₆Sb (Very Rare) Microchem. HNO₃, Slightly effervesces and quickly blackens; rubs to faint gray. HCl, Practically negative; some specimens turn very slowly faint brown and rub to very faint gray. KCN, Neg. FeCl₃, Neg. HgCl₂, Tarnishes a brown rim which rubs clean. KOH, Slowly tarnished faintly.
Hardness, Low. Very Sectile. Gray powder when scratched.
Description. C.—Silver-white. Occurs massive.

B.B. Reacts for antimony and copper. Fus.—1.5.

HCI-IV KON-W wo.l FeCl. W

ORENY WHERE ARRESTED AND AND STREET AND STREET AND ASSESSED AS A LICENSE OF THE STREET AND ASSESSED AS A LICENSE OF THE ASSESSED AS year to H. Carrishes pale signery subs to talet browns

rierdness, alow to medium 2.6. Section and similar latelly distribution

and reduced with sodium carbonate yights sold and alver, somesimes reduces so gold boad masks without source. Fussy is

Constant Statement Statement County and the constant of the Statement of the County Statement of the C

CREARY Wifty Streets STROMS OF BLICK (Very Second Creary Wifty Streets and Market Streets and Market Streets Streets and Market Streets Street

CALES A WHITE Department Co. H. sud S. (Very Ran)
(Incention, "HNO, (Scient) effectives and wres indepent to thick,
rubs to gray roughment cornect futions tank HGI, Reg. Funces
tarnish brawn, rubs to pain trown. HGN Neg. FeCi. Neg.
HgCl, Neg. KOH, Neg.
Charlenes, Lot. Very Seculo, Kirk poster whith scratched.
Charlenes, Lot. Very Seculo, Kirk poster which scratched.
Charlenes of the seculosistic of the action of the security of the security of the security of the seculosistic of the security of the seculosistic of the se

CALERA Herry Boulangovile Sites Street Rarel

deroutem HNCs, Enerveses and blackens westin to stelled struct side, former minish light block, After respective registers. Hardman, Low. 2.5-8. Sectile, but slightly birth. Unit; powder when

sera tehed. Description. C.—Hittish listd-gray. Str.—Black. Occurs fibrous; glants-

CusSb (Very Bare) LINK WHITE Horstordie Calco (very lier)
Microchem, HVO, Silghtly offervesces and quicky hackens; rules to
faint error, HCI, Practically asgative; some spoolmens term very
slowly think brown and rule to very limit gray. ICON, Neg. TeOS,
Veg. HgCl., Tarnishes a brown rim which rube clean. HCH, Slowly
tarnished faintly.

Hardman Low Your Settle. Oray powder when scratched.

Description. C.—Silver/white. Orang massive.

HNO. HCI KCN Med. FeCl-N

CREAMY WHITE Sulvanite Cu₃VS₄ (Very Rare) Microchem. HNO₃, Neg. Fumes tarnish; rubs clean. HCl, Neg. Fumes tarnish; rubs clean. KCN, Neg. Fumes tarnish; rubs clean. KCN, Neg. Fumes tarnish; rubs clean. FeCl₃, Neg. HgCl₂, Neg. KOH, Neg.
Hardness, Medium. 3.5. Brittle. Gray powder when scratched Description. C.—Bronze-yellow. Occurs massive. (South Australia.)
B.B. Roasted and reduced with sodium carbonate and borax yields cop-

per buttons. Gives vanadium bead with the fluxes (IV, 27, a).

Hardness June 2-25 Employed with the warter at a

GALENA WHITE Guejarite See page 83. FUR.—I. S.A. CHARLES SAN CHARLES STORY OF THE STORY DELICATION OF THE STORY OF THE

M-10am

Galena White Hessite Ag₂Te

Microchem. HNO₃, Slowly tarnishes iridescent to brown; rubs to roughened surface. (Sometimes slowly effervesces.) HCl, Tarnishes iridescent; rubs faint or clean. (Sometimes nearly negative.) KCN, Slowly tarnishes. FeCl₃, Tarnishes iridescent; rubs faint to clean. HgCl₂, Tarnishes brown; rubs clean. KOH, Very slowly tarnishes slightly; rubs faint.

Hardness, Low. 2.5–3. Quite sectile.

Description C.—Steelgray Str.—Gray Occurs crystalline massive.

Description. C .- Steel-gray. Str.-Gray. Occurs crystalline, massive,

B.B. Coat and flame are not decisive. Shows tellurium with concentrated H₂SO₄. Reduced with sodium carbonate, yields silver buttons. Fus.-1.

Pyrolusite See page 101. BROWN

Dyscrasite Ag₃Sb, Ag₆Sb, etc. (Very Rare) CREAMY WHITE Microchem. HNO3, Tarnishes and develops differential etching. HCl, Slowly tarnishes with development of differential etching. KCN, Slowly and faintly etches differentially. FeCl₃, Differential iridescent tarnish. HgCl₂, Tarnishes to brownish iridescence with structure; rubs same. Fumes tarnish light brown. KOH, Neg.

Hardness, Low. 3.5-4. Exceedingly sectile.

Description. C.—Silver-white, sometimes tarnishing vellow or blackish.

Str.—Silver-gray.

B.B. Easily fuses to a globule, coating the charcoal with white antimony trioxide, and finally leaving a globule of pure silver. Soluble in nitric acid. Fus.-1.5.

GRAYISH WHITE Argentite Ag₂S

Microchem. HNO₃, Slowly tarnishes light brown; rubs clean. Fumes tarnish brown. HCl, Sometimes slowly tarnishes faint brown, but often almost negative. KCN, Tarnishes brown; rubs to faint gray. Fumes tarnish brown. FeCl₃, Slowly brown to iridescent; rubs to very faint iridescence. HgCl₂, Tarnishes brown; rubs to pale brown. KOH, Neg. Blackened by short exposure to unscreened strong electric are light.

Hardness, Low. 2-2.5. Exceedingly sectile. Black powder when

scratched.

Description. C.—Lead-gray. Str.—Shining gray. Common in many silver deposits and also occurs in disseminated small crystals in silver bearing lead minerals, etc.

B.B. Fuses with intumescence in the O.F. on charcoal, emitting sulphur

dioxide odor and a globule of pure silver. Fus.—1.5.

GRAYISH WHITE Stromeyerite (Ag,Cu)2S (Very Rare)

Microchem. HNO₃, Tarnishes slightly with etching; rubs to rough gray. Fumes tarnish. HCl, Slowly very faint brown. (Sometimes practically negative.) Fumes tarnish. KCN, Tarnishes brown; rubs to FeCl₃, Quickly tarnishes brown or iridescent with strucfaint gray. ture; rubs to brownish iridescence. HgCl2, Tarnishes brown; rubs to pale yellowish. KOH, Neg.
Hardness, Low. 2.5–3. Very sectile. Black powder when scratched.
Description. C. and Str.—Dark steel-gray. Prismatic, massive, com-

pact.

B.B. Fuses in the O. F. on charcoal to a semi-malleable globule, which reacts for copper (IV, 6) and cupelled with lead yields a silver button. Soluble in nitric acid. Fus.—1.5.

GRAYISH WHITE Jalpaite 3Ag₂S.Cu₂S? (Very Rare) Microchem. HNO3, Acid has no effect, but the fumes tarnish slowly brown; rubs clean. HCl, Acid turns green and surface is slightly roughened, but the reaction often appears negative. KCN, Tarnishes brown very slowly; rubs clean. FeCl₃, Tarnishes and rubs to faint greenish iridescence. HgCl₂, Tarnishes brown; rubs to faint spot. Fumes tarnish. KOH, Neg.

Hardness, Low. Specimen from Tres Puntas, Chili is brittle and has a

blood red powder when scratched. Internal reflection seen with in-

clined light is blood red.

Description. C.—Blackish lead-gray. B.B. Like stromeyerite.

REARY WRITE Dysometh AgeS, AgeSts of Very Reservators of the Continuent of Microslam RIVO, Tennishes and develope differential contagn [17] stowly straighted with development of development of the contagn of the State of the Continuent of the Con

str. Silver-grav to Easily turns to a globule weating the charmal with where as imony

sateles brown rates, sometimes sower ranges rank to rank to the gray, often almost negative. ACN, Translates brown, rubs to rain to recy.

Planes termials brown. Prof., Slowly tiff a to includently, rum to recy.

Limb indessence the Cl., Tarnishes brown; rate to pale brown.

KOH, Neg., 'Blockened by short oxpoints to insertenced strong also-

Hardness I nw. 2-2 5 Exceedingly seedle. Black powder

Altreat on the Altro, Tarnishes signific with stehing; rubs to rough grav.

Numes tarnish, HC, Stewly vary laint brown. (Somethines oraclically negative.) Pumes tarnish, KCN, Tarnishes brown; rubs to laint grav. FeCls. Quickly tarnishes brown or indescent with structures.

paie veilowish, KOH, Neg.

Hardness, Low., 2.5-3, Very sectile. Black powder-when someched.

Description. C. and Str.—Dark steel-gray. Presuntis, massive, com-

B.S. Puses in the O. F. on charcool to a semi-realicable globule, which reacts for copper (IV, 8) and capelled with lead yields a silver lutton. Soluble in sittic acid. Fas.—L.S.

Microsham. HNO, Acid has no effect, but the finnes tarnish slowly brown; rubs clean. HCL Acid turns grown and surface is abshily roughened, but the reaction often appears acgative. MCA, Ternishee brown vory slowly; rubs clean. FoCl. Tarnishee and rubs to faint greensh indescence. Herds Tamishes brown; miles to faink spot. Frans tamish. KOH Neg. Provestions, Low. Specimen from Tres Pontas. Chili is brittle and has a ...

blood red powder when somtohed. Internal redection seen with in-

HNO₃ HCl KCN Low FeCl₃-N

Bluish White Brongniardite* PbS.Ag₂S.Sb₂S₃? (Very Rare) Microchem. HNO₃, Slowly tarnishes pale brown; rubs clean. HCl, Slowly tarnishes faint brown; rubs clean. KCN, Slowly tarnishes faint brown; rubs clean. FeCl₃, Neg. KOH, Tarnishes iridescent; rubs to clean etched surface.

Hardness, Low. 3+. Description. C. and Str.—Grayish black. Massive.

B.B. On charcoal, decrepitates, fuses easily, and gives off sulphur dioxide vapors. Upon roasting yields an impure globule of silver and a yellow coating of lead oxide. In the closed tube yields a faint orange sublimate. In the open tube, fuses, and yields a sublimate of white antimony trioxide. Fus.—1.

Billings Warrs Brongslandist Ph.S. Ap. E. St. 2. (Very Ranc)
Microchem. H.NO., Slowly tartishes yells brown, rule yimm. U.C.,
Slowly tarnishes raint brown, rules closs. A.O., Slowly tarnishes taring
brown, rules closs. PcCl., Neg. KOH. Tarnishes indescent; rains closs of the chief days face.

Mardanes, Low, 5 + Description. C. and Sux—Cray'sh black. Massive. B.B. On charcoal, decopping to a visco casily, and gives of support dioxide. vapors. Upon roasone veids an impure globale of silver sad a relion costing of lead oxide. In the closed tube yields a faint orange sub-innate. In the open tabe, fases, and yields a sublimate of white antimony growide, Fus .- 1.

HNO3 HC1 KCN-N High FeCl₃-N

RAY PSILOMELANE H₄MnO₅?

Microchem. HNO₃, Acid tarnishes faintly; fumes strongly. Rubs nearly clean. HCl, Tarnishes and rubs faint brown. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Neg.
Hardness, High. 5-6. Brittle.
Description. C.—Iron-black. Str.—Shining brownish black. Massive, botroidal, reniform, and stalactitic.
B.B. Infusible. In the closed tube yields water. Yields a green bead with sodium carbonate (IV, 11, a). Soluble in HCl with evolution of chlorine. May contain enough iron to become magnetic when roasted.

MCN-M

Gray Pencentars Hidno.

Microchem, HNOs, Acid tetrishes fainfly; furnes strongly. Rubs
nearly clean. HCl. Tarmsines and rubs faint brown. ICON, Neg.
FeCh, Neg. HgCl. Neg. KOH, Neg.
Hardness, High. 5-6. Brittle
Description. C—Iron-black. Str.—Strining brownish black. Massive,
B. H. Leinebla. In the allowed state with the control of the clean of the control of the c

B.B. Infusible. In the closed tube yields water. Yields a green bend with sodium exchange (IV, 21, a). Soluble in HCl with evolution of oblorice. May contain enough iron to become magnetic when renaited.

HIII U2 HC1 KCN-N Med. FeCla

GRAYISH WHITE Tenorite CuO (Very Rare) Microchem. HNO3, Acid without effect, but fumes tarnish; washes clean. HCl, Tarnishes and deposits a mass of white acicular crystals; rubs to faint gray. Fumes tarnish. KCN, Neg. FeCl₃, Tarnishes pale brown very slowly; rubs clean. HgCl₂, Neg. KOH, Neg. Hardness, Medium. 3-4. Slightly brittle.

Description. C.—Iron-gray to black. Str.—Black. Occurs massive, crusted, in minute crystals, and scales. Found in oxidation zone in

some Cu deposits.

B.B. Like cuprite (page 33).

HONE Median

Grayma White Teorris CoO (Very Rare)

Microckers, RNO, had without effect, but furner tamish; markes clean.

MCJ. Termines and disposite a mass of white private crystals; rake to
take prov. Jeness tarness KCN, Meg. 1eCl. Involves pair
brown very slowly; rules clean. HgCl. Neg. 1eCl. Involves pair
Hardness, Medium. 3-4. Shighly brittle.

Description. C.—Iron gray to cleak. Str.—Eleck. Occurs massive,
creased, in minute crystals, and scales. Found in oxidation voice in
some Cardeports.

Some Cardeports.

HC1 KCN-N Med. FeCl₃-N

Microchem. HNO₂, Blackens; rubs to roughened surface. Fumes tarnish brown. HCl, Tarnishes with structure, acid turning yellow; rubs to slightly roughened surface. Fumes tarnish. KCN, Neg. FeCl₂, Neg. HgCl₂, Neg. KOH, Neg. Hardness, Medium. 3.5. Brittle. Reddish yellow powder when scratched. Internal reflection as seen by inclined light is greenish or

yellowish brown, but may not always be noticeable.

Description. C.—Dull green to greenish black or yellowish brown. Usually in crusts or reniform masses with mammillary surface and

columnar structure.

B.B. In the closed tube yields water. Will test for constituents in the formula above as well as for arsenic and other impurities. (See Chap.

GRAYISH WHITE TENORITE See page 73.

Gray Sphalerite See page 94. RAY Sphalerite See page 94.

Harmonia Dire. 3-8. Processing C. Herbich gray. For eligible This Supplies talks Noted bound through

The control of the co

Aguilarite Ag₂S.Ag₂Se GRAYISH WHITE (Very Rare) Microchem. HNO₃, Slowly tarnishes brown; rubs clean. Fumes tarnish. HCl, Acid without effect, but fumes often tarnish brown; rubs to faint

brown. KCN, Neg. FeCl₃, Slowly tarnishes iridescent; rubs to faint iridescence. HgCl₂, Tarnishes brown to iridescent; rubs to iridescence. KOH, Neg.

Hardness, Low. 2.5. Extremely sectile.
Description. C.—Iron-black. Str.—Black.
B.B. On charcoal yields a white coat with metallic-like luster, also a selenium odor and blue flame. Heated slowly in the open tube yields metallic silver. Fus.—1. B.B. In the closed tube visids water.

HNO; HCI KCN-N Low FeCla

Microchem. HNO₃, Turns blue; rubs same. HCl, Same as HNO₃.-KCN, Neg. FeCl₃, Same as HNO₄. KOH, Slowly tarnishes brown; rubs blue.

Hardness, Low. 3.

Description. C.—Cherry-red, tarnishing to violet-blue. Str.—Black. Massive.

B.B. Roasted and reduced with sodium carbonate on charcoal, yields copper buttons. Also yields a white coat with metallic-like luster, a selenium odor, and colors the flame blue (IV, 17, a). Fus.—1.5.

Clausthalite* PhSe (Very Rare) WHITE

Microchem. HNO₃, Forms brick-red coating; rubs off to brown surface. HCl, Slowly tarnishes brown; rubs clean. KCN, Neg. FeCl₃, Slowly tarnishes, forming bluish and yellowish coating. KOH, Neg. Hardness, Low. 2.5–3.

Description. C.—Lead-gray. Str.—Black: Granular masses; cubic

cleavage.

B.B. Decrepitates in the closed tube. Gives all tests for lead and selenium. (See Chap. IV, 10 and 17.) Fus.—2.

GALENA WHITE Galena PbS

Microchem. HNO₃, Quickly blackens; rubs black, with rough surface. (In some specimens shows effervescence.) HCl, Tarnishes brown; rubs to gray. Fumes tarnish. KCN, Neg. FeCl₃, Tarnishes brown to iridescent; rubs brown. HgCl₃, Neg. KOH, Neg. Hardness, Low. 2.5–2.75. Sectile, but slightly brittle. Gray powder. Description. C. and Str.—Pure lead-gray. Perfect cubic cleavage. B.B. Yields all tests for lead (IV, 10). Fus.—2.

3PbS.Bi₂S₃ GALENA WHITE Lillianite* (Very Rare)

Microchem. HNO₃, Quickly tarnishes iridescent; rubs clean. HCl, Slowly tarnishes pale brown; rubs clean. Fumes tarnish. KCN, Neg. FeCl₃, Slowly tarnishes iridescent; rubs clean. KOH, Neg.

Hardness, Low.

Description. C.—Steel-gray. Str.—Blck. Massive, also crystalline. B.B. With KI & S flux shows both lead and bismuth (IV, 3 and 10). Fus.—1-1.5.

GRAYISH WHITE Teallite* PbSnS₂ (Very Rare) Microchem. HNO2, Tarnishes brown to iridescent; rubs clean. HCl, Slowly tarnishes light brown; rubs clean. Fumes tarnish. KCN, Neg. FeCl2, Slowly tarnishes faint brown. KOH, Same as FeCl3.

Hardness, Low. 1-2.
Description. C.—Blackish gray. Str.—Black. Thin flexible folia.

Perfect basal cleavage.

B.B. Yields all tests for lead and tin. (See Chap. IV.)

GRAYISH WHITE Pb6Sb2Sn6S21 (Very Rare) Cylindrite Microchem. HNO₃, Slowly tarnishes brown; rubs to iridescence. Fumes tarnish iridescent. HCl, Acid is without effect, but fumes tarnish brown; rubs to very faint gray. KCN, Neg. FeCl₃, Tarnishes brown; rubs to very faint brown. HgCl₂, Neg. KOH, Tarnishes brown to

iridescent; rubs to faint gray.

Hardness, Low. 2.5-3. Very sectile. Gray powder when scratched.

Description. C.—Blackish gray. Str.—Black. Massive; also in cylindrical forms separating into distinct shells under pressure.

B.B. See Chapter IV for tests for antimony, tin, and lead. Fus. -1.5.

CREAMY WHITE Native Silver See page 43. WHITE Native Antimony See page 96.

Nervolena, HEO, Turns blue; rule some, HCl. Some as HNO. KCN, New 2001. Store translates brown;

White and Christman Price Trade and States of Softward and an Administration of Softward and an Administration of Softward and an Administration of Softward and Administration of Softwar

Hardness, Low. 15-3. Description. C. Lead-gray. Set.s-Racks Countles moneyer color-

Calena Warra Gaiena Pos

Microchem, H.Wo, Junckly blackens; robe cleak, with rough surlace,
(In some specimens shows effectively UCI Tartishes brown
robe to gray. Funcasaruish, h.C.N. No. 1983. Tartishes brown
to indescent robe brown. HeCL, No. 1983. No.

Martines, Low. 2.5-2.75. Sectile but signify bright Gray gooder.
Description. C. and Sr. -1 to be description. Carrier could cleave,

B.R. Yields all sects for real CV. 10. Fire. C. 1984.

LERMA WHITE Libraries 3PhS Bigs, (Very Marc)
Microphem, HNGs Quickly farmishes instancent; rubs clean, HCI,
Showly tarmishes pulle brown; rubs clean, Tunne tarmish, MCN, Neg
Verla, showly tarmishes independ; rubs clean, KOH, Nog. CARRINA WHITE

Charies Warrs Toulite Posts Microchem, HNO, Tambeles brown to indescent; rubs close, HCl.

2.3. Yields all tests for lead and till. (See Carpell).

(Instrum Warrer. Cylendria. Ph.NbiShoff. (Very Rays).

Marcohem. (NO. Short) saraishes brown substitutioned. Planes.

Marcohem. (NO. Short) saraishes brown substitution but funce tartish frown; with the tower saraish showing with the test saraishes brown. The saraishes brown rules to now there brown. March. Now. 1904. Navishes brown rules to now there brown. March. Now. 1904. Navishes brown to trainers from the saration.

Hariners flow. 2.6.6. Very sactile. Other powder when according the saration. It samption. C. Charles the rest. Six-stillark. Marches abstitution. Other forms when according the distinct shall synder pressure.

H. Sice Charles of the costs for animony, in said lead. Fig. -1.5.

Sac page 100.

GALENA WHITE Meneghinite* 4PbS.Sb₂S₃ (Very Rare)
Microchem. HNO₃, Quickly tarnishes and blackens; rubs to gray, rough
surface. HCl, Very slowly faint brown to almost negative. KCN,
Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Tarnishes very slowly.
Hardness, Low. 2.5. Brittle. Gray powder when scratched.
Description. C.—Blackish gray. Str.—Black. Pinacoidal cleavage.
Slender prismatic crystals; also massive, fibrous, and compact.

B.B. Decrepitates and fuses very easily. Yields antimony flame and coat on charcoal (IV, a). With KI & S flux yields lemon-yellow lead iodide coat (IV, 10 a). Fus.—1.

GALENA WHITE Geocronite 5PbS.Sb₂S₃ (Very Rare) Microchem. Same as Meneghinite. Except KOH is negative. Hardness, Low. 2.5. Brittle. Gray powder when scratched. Description. C. and Str.—Light lead-gray to grayish blue. Usually massive, granular, or earthy. B.B. Like Meneghinite.

Franckeite PbsSn2Sb2S12 GRAYISH WHITE (Very Rare) Microchem. HNO₃, Tarnishes brown, then iridescent; rubs faint iridescent. HCl, Usually tarnishes faint brown. Fumes tarnish slightly. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Practically negative, but sometimes faintly tarnishes and rubs clean.

Hardness, Low. 2.75. Extremely sectile. Gray powder when scratched. Description. C.—Blackish gray. Str.—Black. One perfect cleavage.

Massive.

B.B. See Chapter IV for tests for lead, tin, antimony, etc. Fus.—1.

WHITE Eucairite See page 97.

GRAYISH WHITE Cylindrite See page 77.

WOL W-13×8

There were the state of the sta

B.B. Decreptages and times very easily. Yields antimoty fame and coat on charcoal (IV, a). With MI & S flux yields lemon-yellow land iodide coas (IV 10 c). For --1

Gratian White, Promokelly Ph. Sug-Sh. Sig. (Very Rais)
Microslam, HNO, Tolombes brown, then interesting rules faint indexcont. HCL Usually taxuative (aint brown, found taxuals slightly,
HCN, New, Following, HgCls, Neg. HgCls, Neg. KuH, Practically negative. but southernes taintly termishes and rubs clean.

Thirdness, Low. 2.75. Extremely sectific. Grey provider when senatebed.

Description. C.—Blackieb grey. Sec.—Black. Case perfect cleavene. B. R. See Chapter IV for truty for lead, his, anticong, etc., Fus.-1.

See page 98

Description Similar to be contains allowed to the contains a contain the contains allowed to the contains a contain the contains a contains a contain the contains a contain the contains a contains

Description. Similar to tetrahedobe.

HCI-N KCN Med. FeCl:

See page 87. GRAYISH WHITE POLYBASITE

Provided Configuration of the Section of the Sectio

DEPERMINATIVE TAXOBS.

HOLW Med. Med. FeCh

Grayish (Brownish) White Freibergite (Cu, Ag)₈Sb₂S₇ Microchem. HNO₃, Slowly tarnishes brown to iridescent; rubs pale. Fumes tarnish brown. HCl, Neg. KCN, Tarnishes brown to iridescent; rubs same. FeCl₃, Neg. HgCl₂, Neg. KOH, Neg. Hardness, Medium. 3-4.

Description. Similar to tetrahedrite.

B.B. Like tetrahedrite, but contains silver.

CRAYISH WEITS POLYBASITE NO BAYO ST.

Luzonite Cu.AsS. (Very Rare) PINKISH WHITE Microchem. HNO₃, Very slowly tarnishes faintly; washes clean. Fumes tarnish slightly. HCl, Neg. KCN, Slowly tarnishes. FeCl₃, Neg. HgCl₂, Neg. KOH, Neg.
Hardness, Medium. 3.5. Brittle. Gray or black powder when scratched. Description. C.—Dark reddish steel-gray. Str.—Black. Massive.

B.B. Like enargite.

BROWNISH WHITE Enargite Cu AsS Microchem. HNO₃, Very slowly tarnishes faint brown; rubs clean. Fumes slowly tarnish faint brown. HCl, Neg. KCN, Sometimes reacts very faintly, but quickly darkens some specimens, rubbing to a rough etched surface. FeCl₂, Neg. HgCl₂, Slowly tarnishes brown;

rubs clean. KOH, Neg. Hardness, Medium. 3. Brittle. Gray powder when scratched.

Description. C. and Str.-Grayish to iron-black. Often seen with prismatic planes vertically striated; also massive or disseminated. Colum-

nar cleavage.

B.B. In the closed tube decrepitates, yielding a sublimate of sulphur. At a higher temperature it fuses and yields a sublimate of arsenic sulphide (IV, 2, c). Roasted and reduced with sodium carbonate, yields a malleable copper button.

PINKISH WHITE Famatinite Cu₃SbS₄
Microchem. HNO₃, Very slowly tarnishes brown; rubs to brown.
Fumes tarnish faintly. HCl, Neg. KCN, Slowly tarnishes brown with etching; rubs to pale etched surface. (Some specimens are practically negative.) FeCl₃, Neg. HgCl₂, Neg. KOH, Neg.
Hardness, Medium. 3.5. Brittle. Gray powder when scratched.

Description. C.—Gray with tinge of copper-red. Str.—Black.

In the closed tube decrepitates, yielding sublimate of sulphur, and on higher heating, a sublimate of antimony sulphide (IV,1, c). Reduced with fluxes, yields metallic copper and, when moistened with HCl, yields a blue copper chloride flame (IV, 6). Fus.—1-1.5.

Microchem. HNO₃, Tarnishes dark; rubs to gray. HCl, Neg. (Some specimens tarnish very faintly and rub clean.) KCN, Slowly tarnishes brown; rubs to a faint brown. FeCl₃, Neg. HgCl₂, Tarnishes faint GALENA WHITE brown; rubs clean. KOH, Quickly tarnishes; rubs to deeply etched surface.

Hardness, Medium. 3.5. Sectile, but slightly brittle. Gray powder when scratched.

Description. .C.—Steel-gray with tinge of blue. Str.—Black. Prismatic crystals. Good pinacoidal cleavage.

B.B. Like Famatinite.

YELLOW Chalcopyrite See page 117. Tennantite See page 117. GRAVISH WHITE GRAYISH WHITE Tetrahedrite See page 117. CREAMY WHITE Sulvanite See page 65. 83

mersu White Samainale Ca.SbS.

Miscronium. HNCo, Yery slowly increases brown; ruits to known.

Figures tarnish Isanti, 1001, Neg. KCS. Slowly tarnishes brown with excising; rubs to pair, 1001, Neg. KCS. Slowly tarnishes brown with excising; rubs to pair ordered. Some appointment are practically negative.) FeCl., Neg. HgCls, Neg. KOH, Neg.

Hearington, C.—Carsy with times of trapper-red. Sts. Hand.

B. H. In the closed nine decrentities, yielding enhance of sulphur, and on higher bearing, a subtunate of antonory sulphilite (IV.1, d). He dueed with finges, yields metallic copper and, when mollanes with HCl, yields a blue copper chievide figure (IV.6). Fig.—1-15.

Tennantite

KCN Low FeCl:

Grayish (Greenish) White Pearcite Ag₉AsS₆ (Very Rare) Microchem. HNO₃, Acid without effect, but fumes tarnish and wash clean. HCl, Neg. KCN, Quickly blackens; rubs to gray, roughened surface. FeCl₃, farnishes iridescent; rubs to very faint gray. (Sometimes rubs clean.) HgCl₂, Tarnishes brown; rubs to iridescent brown. KOH, Neg.

Hardness, Low. 3. Sectile.

Description. C. and Str.—Black. Tabular crystals and massive.

B.B. Yields arsenic odor and white coat on charcoal (IV, 2, a). Roasted and reduced with sodium carbonate yields silver buttons. Fus.—1.

BLUISH WHITE Polyargyrite See page 109.

GRAYISH WHITE Argentite See page 67.

GRAYISH WHITE Jalpaite See page 67.

GRAYISH WHITE POLYBASITE See page 87.

Ton HOI-W

Chayun Khumunga) Waren Provide Agusas (Very Hang)
Marschem, HVO, Acid military wheel, but inner taxuen and weel
clean, HVI Veg KCE, Cadelly blankens; rails to gray, congluent
endage, 1 oCl, flarmener railsseem; rails to very lain, and, (Somecones rails olean) rights Taxuenes brown; rails to independ howe.

Hardman, Low, M. Rodlin,
Description, O, and Str.—Black, Tabular crystals read massive,
B.R. Yinds macril odor and white suction charged (IV, 2 n). Ronaled
and reduced with section embousity visits allow buttons. Tus.—I.

Brinsa Winta Folgarypus See page 104.
Granish Winta Argenthe, See page U7.
Granish Winta Johnsts See page S7.
Granish Whith Formasius See page S7.

GALENA WHITE Stibnite Sb₂S₃
Microchem. HNO₃, Tarnishes dark brown; rubs to gray. HCl, Neg. KCN, Dissolves, bleaches, and roughens surface, but does not tarnish. FeCl₃, Neg. HgCl₂, Neg. KOH, Tarnishes brown and shows yellow coating; rubs to roughened surface often showing patches of yellow.

Hardness, Low. 2. Slightly brittle. Gray powder when scratched.

Description. C. and Str.—Lead-gray. Crystals are long prisms with striations parallel to elongation. Highly perfect "b" pinacoidal cleavage.

B.B. Yields antimony flame and coat on charcoal (IV, 1, a). When pure volatilizes entirely. Fus.-1.

GALENA WHITE KERMESITE Sb₂S₂O

Microchem. HNO₃, Tarnishes light brown; rubs pale brown. HCl, Neg. KCN, Slowly tarnishes pale brown; rubs faint. FeCl2, Neg. HgCl2, Neg. (?). KOH, Tarnishes iridescent and is coated with yellow; rubs clean.

Hardness, Low. 1-1.5. Very sectile. Red powder when scratched.

Internal reflection as seen by inclined light is red.

Description. C.—Cherry-red. Str.—Brownish-red. Usually in needle-

like crystals.

B.B. In the closed tube blackens, fuses, and at first yields a white sublimate of antimony trioxide; after strongly heating yields the usual black or dark red antimony sublimate in closed tube. Otherwise like stibnite. Fus.-1.

GRAYISH WHITE POLYBASITE Ag SbS Microchem. HNO3, Some specimens practically negative. Others tarnish very slowly; rubs to faint gray etched surface. HCl, Neg. KCN, Develops scratches and tarnishes dark brown; rubs to gray etched surface. FeCl₂, Practically negative, but some specimens tarnish faint brown; wash clean. HgCl2, Quickly tarnishes brown to black; rubs to faint brown. KOH, Neg.
Hardness, Low. 2-3. Sectile, but slightly brittle. Gray powder when

scratched. Internal reflection as seen by inclined light is red. (Not

always detected.)

Description. C.—Iron-black, in thin splinters cherry-red. Str.—Black. B.B. On charcoal fuses with spirting to a globule, yielding antimony flame and coat (IV, 1, a). Reduced with sodium carbonate yields silver (IV, 18, a). Fus.—1.

GALENA WHITE Livingstonite See page 111.

Stibnite Ships

New, theorems, because and imposes strates, our force and terrain restricted to the strate and strate or sellow contract of the showing paraties of subject that the strategy when contribute. One possess when contribute. Description. C and Sar,—Leadigns, Cristals are long gaines with strations parallel to elongation. Highly period "b" pithecoidal strations parallel to elongation. Highly period "b" pithecoidal

Microchem, HNO, Parcishes light brown; rubs pale brown, MC, Neg, KCN, Sowly samishes pale brown; rubs faint. PcCl, Neg. HyClarker (2), 100H. Tamislas bidesent and is corted with vallow

Pardness, Low. 1-1.5. Very sectile. Red powder when accatched, interpal reflection as seen by inclined light is red.

Description. C.—Cherry-red. Str.—Brownish-red. Usually in needle-

3. H. In the closed tube blackers, fuses, and at first yields a white sub-

WHITE

HITE Chloanthite NiAs₂
Microchem. HNO₃, Slowly tarnishes faint brown; rubs to pale gray.
Fumes tarnish. HCl, Neg. KCN, Neg. FeCl₃, Slowly tarnishes faint brown, but is often almost negative. HgCl₂, Neg. KOH, Neg.

Hardness, High. 5.5-6. Brittle. Gray powder when scratched. Description. C.—Tin-white. Str.—Gray-black.

B.B. Fuses easily to a globule and yields an arsenic odor and perhaps a white arsenic coat on charcoal. Yields a red precipitate with dimethyl glyoxime (IV, 14, b). Gives a cobalt reaction with borax usually due to impurities of that element. Fus.—2.

Rammelsbergite NiAs₂ (Very Rare) Like chloanthite in all properties except crystal system.

GERSDORFFITE WHITE NiAsS

Microchem. HNO₃, Tarnishes brown, then black; rubs to rough gray surface. Fumes tarnish brown and develop structure. HCl, Mineral unaffected, but acid turns bright yellow. KCN, Neg. FeCl₃, Slowly tarnishes faint brown. (Sometimes practically negative.) HgCl₂, Tarnishes brown; rubs clean. KOH, Neg. Hardness, 5.5. Brittle.

Description. C.—Silver-white, tarnishing to gray. Str.—Grayish black. Good cubic cleavage.

B. B. Decrepitates in the closed tube and yields a vallowish brown who

B.B. Decrepitates in the closed tube and yields a yellowish brown sub-

limate (IV, 2, c). Otherwise like chloanthite.

Manufacture Off.

High

Merochem, HNO, Slowly tarnishes faint brown; subset pale gray.

Frames carnish, HCL, Neg. ICCN, Neg. FeCh. Slowly famishes
faint brown, but is offen almost negative. HgCl, Neg. ICCH, Neg.

Hardness, High. 5.3-6. Britis. Cirar powder when savatshed.
Description. C. The while. Sit.—Grav-black.
B. R. Trees castly to a globule and yields an arsenic odor and parhaps a white amenic rost on charcal. Yields a red promptate with dimethyl givenime (IV, I4, b). Gives a cobalt reaction with borns usually due to impurities of that element. Fig.—2.

Like chlosechite in all proporties except orystel system.

HgClg Termsber brown; rubs clean. KOH, Neg. Hardness, 5.8. Britis. Description. C.—Silver-white tarbishing to cres

B.B. Decrepitates in the closed tube and yields a yellowish brown sub-

limate (IV, 2, a). Otherwise like chicanthite.

WHITE

Microchem. HNO₃, Slowly tarnished faint brown. Fumes tarnish. HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Neg. Hardness, High. 5-5.5. Brittle.

Description. C.—Silver-white. Str.—Black.

B.B. Fuses to strongly magnetic globule in R.F. on charcoal. Gives arsenic coat and odor; also sublimate and mirror in open and closed the representatively. tube respectively. Fus.-2.

WHITE Ulmannite* NiSbS (Very Rare)

Microchem. HNO₃, Tarnishes brown to iridescent; rubs to iridescent gray. HCl, Neg. KCN, Neg. FeCl₃, Neg. KOH, Neg. Hardness, High. 5-5.5. Brittle.

Description. C.—Silver-gray. Str.—Grayish black. Perfect cubic

cleavage.

B.B. On charcoal in the R.F. fuses easily to a globule, boils, and yields an antimony coat (IV, 1, a). Yields a red precipitate with dimethyl glyoxime (IV, 14, b). Fus.—1.5.

CREAMY WHTE Linnwite Co₃S₄ (Very Rare)
Microchem. HNO₃, Tarnishes very faint brown. Fumes tarnish brown
very slowly. HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Tarnishes iridescent brown. KOH, Neg.
Hardness, High. 5.5. Brittle.
Description. C.—Pale steel-gray, tarnishing copper-red. Str.—Black.

Imperfect cubic cleavage.

B.B. On charcoal fuses to a magnetic globule. The roasted mineral yields with the fluxes reactions for nickel, cobalt, and iron usually. Fus.—2.

GLAUCODOT (Co,Fe)AsS PINKISH WHITE (Rare)

Microchem. HNO₃, Slowly tarnishes; rubs to rough gray surface. HCl, Neg. KCN, Neg. FeCl₂, Neg. HgCl₂, Neg. KOH, Neg. Hardness, High. 5. Brittle.

Description. C.—Gray. Str.—Black. Usually prismatic crystals or massive.

B.B. Yields arsenic odor and coat on charcoal, etc. (IV, 2). In the R.F. fuses to a feebly magnetic globule, black on the surface, but a light bronze in color when freshly fractured. Fus.—2-3.

Microchem. HNO₃, Very slowly tarnishes brown; rubs to very pale brown. Fumes tarnish slightly. HCl, Neg. KCN, Neg. FeCl₂, Neg. HgCl₂, Slowly tarnishes brown; rubs clean. KOH, Neg.

Hardness, High to medium. 5. Very Brittle. Steel-gray powder when scratched.

Description. C.-Light bronze-yellow. Str.-Black.

Yields common reactions for constituents indicated in formula. (See Chapter IV.)

WHITE GERSDORFFITE See page 89. WHITE Chloanthite See page 89. WHITE Willyamite See page 57. CREAMY WHITE Pyrite See page 57. CREAM Pyrrhotite See page 95.

gree Lidinger Frag. (Very Rare)
Aleccohem HAND, Slowly tarnshed faint brown. Sures tarnish.
HOU Nes. KCN Nes. Fecha Nes. HgCk, Nes. KOH, Nes.
Hardness, Hugh. 5-5 a. British
Description. C.—Sirvi-white. Str.—Black.
B.R. Frace to strongly magnetic globule in R.F. on chargest Caves
aresis cont and court place sublimate and mirror in open and closed

CHRAMF WETH LABRAGE COSS (Very Rare)
Thorselects. HNO, Tarmshos were family brown. Purious termish brown
cery slately. HNR, Neg. ECIN. Neg. Fulls. Neg. Hgt 2, Timnishes indesent brown. KOH, Neg.

Hardness, Buch, 5.5. Brittle.
Description, C.—Pele steel-gray, temperior, copper-red. Ser.—Higd. Imperiest value shavege.

B.B. (to charveal fusion a magnetic globule. The sussess mineral

Pixxisa Winte (accepted (Called And

Harishedownide (NE.Co) (S.EhdSl) Mistochem RNO, Very stavity tarmakes heave; rubs to very pate brown. Furnes berush slightly, HCl, Neg. NCN, Neg. ReCl., Neg. RCCl., Slowly tarmakes heave; rubs clean. ROH, Neg. Hugh to medium. 5. Very Brittle. Sheal-ares powder when

Hardnesty Mediaga to low: No-Sto Shightly helithown

WELLIST

B.B. In the closed title depoperates and gives a dark not athinate. Microchem. HNO₃, Blackens; rubs to dark gray. HCl, Neg. KCN, Neg. FeCl₃, Tarnishes; rubs to clean-pitted surface. KOH, Neg. Hardness, Medium to high. 5.5.? Brittle. Reddish-brown powder when scratched.

Description. C.—Light copper-red. Str.—Reddish brown. B.B. Yields antimony flame and coat on charcoal and with dimethyl glyoxime gives a red precipitate. (IV, 14, b). Fus.—1.5-2.

The Abertan for constructions in formula. Dist. 44.5.

Chargest Warre . Sounds . Sould finely . (Vor. Man)

Macrodian. HAVA. Threshes brown to indesent, table to yet faint brown. BCI. Nog. LKCN, Veg. 2 of the Neg. Backle, over . LOH.

Mardaess Medium, & Brutle Description C. Steeleres, Str. Rect. Massive graunter, or dis-

B.B. In the closed tube decepitates, giving a faint sublimate only.

8.B. In the closed tube decreptates, giving a faint sublimate only,
See Chapter IV for vertae for constituents of the margin.

(Rayren Warrs. Creates). (CaThag) to Ver Rare)
Microschem H. U. Sowit Jameshes Sharliwown; Tabe Siene. Lunce
jamesh. (EU. Neg., MCN. or FeCl., Neg. KOH. Neg.
Harlines, Medicina to low. 2.5-3. Britis.

Description. (Cathagray St.—Histor. Massivit Françaid.

E.B. Friese early vertaents bisses, shiring energel colonograms blue.
Rossivit and wares to be a state of the colonograms blue.

(IV 6, and 18.) Fra.-1. Garriss Warrs Warrs.

Rossred and reduced with sodium carbonate yields copper and silver.

Microchem 1 H.VO. France tarniel brown very slowly; wester stead HCl. Not. HCM. New FeCH. Not. HCCl. New 160H. Next. HcCl. New 160H. Next. Hardness. Medium. 4 Britle. Brick-red powder when streamled. Description. C.—Brownish black. Htt. Reddish brown.

H.B. Hrasled unineral yields gweet head with sodium carbonals. For

Microchens, 1980, Tarakhel faintly prowns rube almay MCI, Nex MCN, Nogra Path, Nog. HgCl., Nog., MOH, Nog.

Description. G.—Shades of vallow, brown to black. Str.—Pais to colorless. Perfect dedecabrided elegants. Str.—Pais to B.it. Negry infusion. Refused with toda on charged yields white has des other the loss that is an another than the color of the color egain heated in the G.F. becomes green (IV, 28, ch.; Wurt ate is like mhalerite physically and migrochemically.

Chalcopyrite | See page 117 and sales

Internal reflection as seen by nothing digit is wellow an known and

Pane width in a property contract to the strategy with the

GRAYISH WHITE BOURNONITE (PbCu₂)3Sb₂S₆ (Rare) Microchem. HNO₃, Fumes usually tarnish slowly; rubs clean. HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Tarnishes faintly at edge of drop; rubs to very faint brown. KOH, Neg. Hardness, Medium to low. 2.5–3. Slightly brittle.

Description. C.—Steel-gray. Str.—Black.

B.B. In the closed tube decrepitates and gives a dark red sublimate. Yields antimony flame and coat on charcoal; with continued heating, yielding a lead coat. Residue reduced with sodium carbonate yields copper buttons. Fus.—1.
YISH WHITE Stylotypite 3(Cu₂Ag₂Fe)S.Sb₂S₃ (Very Rare)

GRAYISH WHITE Microchem. HNO₃, Tarnishes brown very slowly; rubs faint or clean. Fumes tarnish. HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Neg.

Hardness, Medium. 3. Brittle.

Description. C. and Str.—Iron-black.

B.B. Decrepitates and fuses easily, yielding a steel-gray, magnetic globule. Also tests for constituents in formula. Fus.—1.5.

RAYISH WHITE Stannite SnCu₂FeS₄ (Very Rare)

GRAYISH WHITE

Microchem. HNO₃, Tarnishes brown to iridescent; rubs to very faint brown. HCl, Neg. KCN, Neg. FeCl₂, Neg. HgCl₂, Neg. KOH, Neg.

Hardness, Medium. 4. Brittle.

Description. C.-Steel-gray. Str.-Black. Massive, granulur, or disseminated.

B.B. In the closed tube decrepitates, giving a faint sublimate only. See Chapter IV for tests for constituents of the mineral.

GRAYISH WHITE Crookesite* (CuTlAg)₂Se (Very Rare)

Microchem. HNO₂, Slowly tarnishes faint brown; rubs clean. tarnish. HCl, Neg. KCN, Neg. FeCl₂, Neg. KOH, Neg. Hardness, Medium to low. 2.5–3. Brittle.

Description. C.—Lead-gray. Str.—Black. Massive, compact. B.B. Fuses easily to greenish black, shining enamel, coloring flame blue. Roasted and reduced with sodium carbonate yields copper and silver.

(IV, 6, and 18.) Fus.—1. Grayish White Hauerite

Microchem. HNO₃, Fumes tarnish brown very slowly; washes clean.
HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Neg.
Hardness, Medium. 4. Brittle. Brick-red powder when scratched.
Description. C.—Brownish black. Str.—Reddish brown.

B.B. Roasted mineral yields green bead with sodium carbonate. Fus.

—3.

ZnS GRAY Sphalerite

Microchem. HNO₃, Tarnishes faintly brown; rubs clean. HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Neg. Hardness, Medium. 3.5-4. Brittle. Yellow or brown powder when

Internal reflection as seen by inclined light is yellow or brown.

Description. C.—Shades of yellow, brown to black. Str.—Pale to colorless. Perfect dodecahedral cleavage.

B.B. Nearly infusible. Reduced with soda on charcoal yields white zinc oxide coat, which when moistened with cobalt nitrate sol. and again heated in the O.F. becomes green (IV, 29, a).

Wurtzite is like sphalerite physically and microchemically.

YELLOW Chalcopyrite See page 117. CREAMY WHITE Sulvanire See page 65. PINKISH WHITE FAMATINITE See page 83. GRAY Voltzite See page 116. PALE YELLOW MILLERITE NiS (Rare,

Microchem. HNO3, Acid is without effect, but fumes tarnish brown; rubs to very faint brown. HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Tarnishes brown; rubs clean. KOH, Neg. Hardness, Medium. 3-3.5. Brittle. Grayish yellow powder when

scratched.

C.—Bronze-yellow, Str.—Greenish black, Commonly Description. occurs as hair-like crystals or botryoidal crusts. At least two perfect cleavages.

B.B. On charcoal in the R.F. the roasted mineral gives a coherent metallic mass, slightly magnetic. As well as yielding reactions for nickel, most varieties also show copper, cobalt, and iron. Fus.—2.

FeS(S)x Pyrrhotite

Microchem. HNO2, Tarnishes very slowly faint brown: almost negative: rubs clean. Fumes tarnish brown. HCl, Neg. (Fumes sometimes tarnish faintly.) KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Slowly tarnishes brownish or iridescent; rubs to brownish iridescence.

Hardness, Medium. 3.5-4.5. Brittle.

Description. C.-Bronze-yellow. Str.-Grayish-black. Usually massive or disseminated. Naturally magnetic.

B.B. In the R. F. on charcoal blackens and becomes strongly magnetic.

Fus.—2.5-3.

Chalmersite CREAM CuFe₂S₃ (Very Rare)

Microchem. HNO₃, Fumes tarnish slightly; washes clean. HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Neg. Hardness, Medium. 3.5. Slightly brittle.

Description. C.—Pale yellow. Str.—Grayish or greenish black.

Strongly, though variably magnetic.

B.B. In the R.F. on charcoal fuses to a strongly magnetic globule. Well roasted and reduced with sodium carbonate on charcoal yields copper (IV, 6, a).

CREAMY WHITE PENTLANDITE (Fe, Ni)S (Rare)
Microchem. HNO₃, Slowly tarnishes very faint brown; rubs to very
faint brown. HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Neg.

Hardness, Medium. 3.5-4. Brittle.

Description. C.-Light bronze-yellow. Str.-Bronze. Non-magnetic. Massive.

B.B. Fuses readily to a magnetic globule on charcoal and yields a red precipitate with dimethyl glyoxime (IV, 14, b). Fus.—2.

CREAMY WHITE Wittichenite Cu₂BiS₂ (Very Rare)
Microchem. HNO₃, Tarnishes light brown; rubs to gray. Fumes
tarnish. HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH,
Slowly tarnishes faint brown; rubs clean.

Hardness, 3.5. Slightly brittle.

Description. C.—Steel-gray. Str.—Black.

B.B. On charcoal fuses easily, at first throwing out sparks, and yielding a bismuth oxide coat (IV, 3, a). The roasted material, moistened with HCl yields a strong blue copper chloride flame. Fus.—1.

GALENA WHITE Andorite PbAgSb₃S₆ (Very Rare)
Microchem. HNO₃, Slowly tarnishes brown or iridescent; rubs faint or clean. Fumes tarnish slowly. HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Slowly tarnishes to pale brown; rubs to faint brownish iridescence.

Hardness, Medium to low. Brittle.

Description. C.—Steel-gray. Str.—Black.

B.B. Shows lead and antimony as in bournonite, but when cupelled yields silver. Fus.—1.

GRAYISH WHITE Tennantite See page 117. WHITE Native Antimony Sb Microchem. HNO3, Tarnishes brownish or iridescent; rubs same. HCl, Neg. (Sometimes appears to tarnish very faintly.) KCN, Neg. FeCl₃, Tarnishes slowly brown; rubs to pale brown. HgCl₂, Slowly

Pars Values Manastra V. Nis of Ram. of the larger targes brown; Microchem. H.NOgrafick without affect, but farmer targes brown; rubs to very laist brown with New Add New 1885, New 1865, New 1860, Personal Republic New 1865, New 1865,

tarnishes faintly brown; rubs nearly clean. KOH, Neg.
Hardness, Low. 3.3-5. Very brittle.
Description. C. and Str.—Tin-white. Perfect cleavage.
B.B. On charcoal yields a white coat in both R.F. and O.F.; with intermittent blowing the globule is finally crusted over with prismatic crystals of antimony trioxide.

B.B. In the R.F. on charcoal taxes to a strongly magnetic globule. Well

REARY WRITE PRETICEPING (P. Ni)8 - (Rais) and Anthon Microshum HNO, Slowly totaled year from brown; rule to year tant brown. HOL Neg. KON, Keg. Parts Neg. Hgch. Neg.

B.B. Frees seadily to a magnetic globals on charcoal and yields a red

CREAMY WRITE Willichmance Challing (Very Rare)
Alternation, HWO, Tarnishes Refa. Rown; rule to gray Paines tamish, HCl, Neg. ICCN, Neg. FeCh. Neg. HgCl, Neg. 14OH, Slowly agraciate from contradication.

H.S. On checoal frees cashe, at first throw our spurits, and pushing a biguint exile cost (IV, 3, a). The extend material, quite and with

HgCla Neg. NOH, Slowly tarnishes to pele brown; rubs to faint

See page 43.

Hardness, Medicon. 3. Description - C.—Bro. CREAMY WHITE Native Silver See page 43.

Plagionite B. in the R. Con See page 76. GRAYISH WHITE Aguilarite GRAYISH WHITE Aguitatue See page 70.

GALENA WHITE

Hardness, Madium to low. Brittle Description. C.—Steel-gray Str.—Black.

KCN-N Low FeCl:

WHITE Berzelianite Cu2Se (Very Rare)

Microchem. HNO₂, Tarnishes iridescent; rubs to iridescent greenish gray. HCl, Neg. KCN, Neg. FeCl₂, Tarnishes very light brown; rubs clean. HgCl₂, Tarnishes very light brown; rubs clean. KOH, Neg.

Hardness, Low. Very sectile.

Description. C.—Silver-white, soon tarnishing. Str.—Shining. Occurs

in thin dendritic crusts and disseminated.

B.B. In the open tube gives a red sublimate of selenium, with white crystals of selenium dioxide. On charcoal yields white coat, selenium odor, and blue flame; with soda in R.F. gives metallic copper. Fus .-1.5.

WHITE

MITE Eucairite Cu₂Se.Ag₂Se (Very Rare)
Microchem. HNO₃, Tarnishes black and shows orange coating; rubs to rough gray. Fumes tarnish slightly. HCl, Neg. KCN, Neg. FeCl₃, Practically negative. (Sometimes tarnishes very slowly faint brown.)
HgCl₂, Neg. KOH, Neg.
Hardness, Low. 2.5. Very sectile.
Description. C.—Silver-gray. Str.—Shining. Massive and granular.

B.B. Like berzelianite except that silver is shown on reduction.

Kalgoorlite HgAu2Ag6Te6? · CREAMY WHITE (Very Rare) Microchem. HNO₃, Very slowly tarnishes faint brown; rubs almost clean. HCl, Neg. KCN, Neg. FeCl₃, Tarnishes iridescent; rubs to rough brownish surface. HgCl, Neg. KOH, Neg. Hardness, Low. Sectile, but slightly brittle.

Description. C. and Str.—Iron-black. Occurs massive.

B.B. Yields tellurium flame and coat on charcoal (IV, 20, a). Roasted and reduced with sodium carbonate yields gold and silver. With soda in a closed tube gives metallic mercury.

Grayish White Petzite (Ag, Au)₂Te (Very Rare)
Microchem. HNO₃, Tarnishes brown to black; rubs gray. (Some specimens effervesce.) HCl, Neg. KCN, Neg. FeCl₃, Tarnishes brown; rubs clean. HgCl₂, Tarnishes light brown; rubs faint. KOH,

Hardness, Low. 2.5–3. Very sectile.

Description. C.—Iron-black. Str.—Gray. Granular to compact.

B.B. Yields a bright green tellurium flame and white coat on charcoal (IV, 20, a). Roasted and reduced with soda on charcoal yields gold and silver button. Fus.—1.5.

AYISH WHITE Coloradoite HgTe (Very Rare)
Microchem. HNO, Slowly tarnishes iridescent; rubs clean. HCl, Neg. GRAYISH WHITE KCN, Neg. FeCl₃, Tarnishes very faint brown; rubs clean. HgCl₂, Neg. KOH, Neg.
Hardness, Low. 3. Very sectile.
Description. C.—Iron-black. Str.—Black. Massive; granular.

B.B. Easily volatile on charcoal. In the closed tube slightly decrepitates, fuses and yields metallic mercury, also tellurium oxide in drops, and next to the assay metallic tellurium. Fus.-1.

GRAYISH WHITE

Microchem. HNO₃, Slowly very faint tarnish; rubs clean. tarnish faint. (Reaction is often practically negative.) HCl, Neg. KCN, Neg. FeCl3, Practically negative, but sometimes tarnishes very faint brown; washes clean. HgCl2, Neg. KOH, Neg.

Hardness, Low. 1-1.5. Very sectile. Description. C.—Lead-gray to bluish black. Str.—Bluish gray. Marks paper. Laminæ are flexible, but inelastic. Perfect basal cleavage. B.B. Infusible, but yields a green flame, also a white coat in O.F. on

charcoal (IV, 13).

Galenobismutite* GALENA WHITE PbBi₂S₄ (Very Rare) Microchem. HNO₃, Tarnishes brown to black; rubs same. HCl, Neg. KCN, Neg. FeCl₃, Neg. KOH, Neg.

Hardness, Low. 3-4.
Description. C.—Lead-gray to tin-white. Str.—Grayish black.
B.B. With KI & S flux shows both lead and bismuth (IV, 3, and 10).

Beegerite* Pb6Bi2S9 (Very Rare) GALENA WHITE Microchem. HNO₃, Tarnishes; rubs to faint gray. Fumes tarnish.

HCl, Neg. KCN, Neg. FeCl₃, Neg. KOH, Neg.

Hardness, Low.

HCLM KCH-N

Description. C.—Gray. Str.—Grayish black.

B.B. Like galenobismutite.

GALENA WHITE Freieslebenite (Pb,Ag₂)₅Sb₄S₁₁ (Very Rare)
Microchem. HNO₃, Tarnishes dark; rubs to rough gray. One fairly
reliable specimen of this mineral was negative with HNO₃. HCl,
Neg. KCN, Neg. FeCl₂, Neg. HgCl₂, Neg. KOH, Neg.

Hardness, Low. 2-2.5. Brittle.

Description. C.—Steel-gray. Str.—Black. Vertically striated prisms.

B.B. Yields antimony flame and coat on charcoal (IV, 1, a). With KI & S flux shows lead (IV, 10, a). Reduced with soda and cupelled shows silver. Fus.-1.

GALENA WHITE Nagyagite Au₂Pb₁₀Sb₂Te₆S₁₅? (Very Rare)
Microchem. HNO₃, Slowly tarnishes iridescent; rubs gray. HCl, Neg.
KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Neg.
Hardness, Low. 1-1.5.
Description. C.—Gray. Str.—Black. One perfect cleavage. Thin laming are flexible. Tabular crystals; also granular massive.

B.B. Complex, but yields tests for constituents of formula. (See Chap. IV.)

CREAMY WHITE Sylvanite AuAgTe₂ (Very Rare)
Microchem. HNO₃, Tarnishes brown; rubs to deep brown, sometimes
developing cleavage. HCl, Neg. KCN, Neg. FeCl₂, Neg. HgCl₂, Neg. KOH, Neg.

Hardness, Low. 1.5-2. Slightly brittle.

Description. C.—Yellowish steel-gray. Str.—Gray. Perfect pinacoidal cleavage. Usually crystalline.

B.B. Yields bright green tellurium flame and coat on charcoal (IV, 20, a). Roasted and reduced with soda yields both gold and silver. Fus.-1.

CREAMY WHITE Guanajuatite Bi₂Se₃ (Very Rare)
Microchem. HNO₃, Quickly tarnishes iridescent; rubs practically clean. Fumes tarnish brown: HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Slowly tarnishes brown; rubs clean. KOH, Neg. Hardness, Low. 2.5–3.5. Sectile to slightly brittle.

Description. C.—Bluish gray. Str.—Black.

B.B. Yields blue selenium flame, odor, and coat on charcoal (IV, 17, a). With KI & S flux yields a brick-red bismuth iodide coat (IV, 3). Fus.—1.5.

Chartier Warra Molybenite MoSs.
Microchem HNO, Mostr very faint tarnient rules ciesu. Fourer tarnien faint. (Rescuim is orien prostically negative, 14th Neg. KCN, Neg. Frida, Frenchist, negative, not sometimes anniches very faint brown; sustant steam, ligt la Neg. KOR, Neg. Hott brown; sustant steam, ligt la Neg. KOR, Neg. Hott brown; sustant steam, ligt la Neg. Kor.—Rhuch grav. Marks Description. Cl.—Land grav is bluste black. Str.—Rhuch grav. Marks

PALE BROWN Sternbergite* AgFe₂S₃? (Very Rare) HNO2, Tarnishes iridescent; rubs gray. HCl, Neg. KCN, Microchem. Neg. FeCl₃, Neg. KOH, Tarnishes brown; rubs clean. Hardness, Low. 1-1.5.

Description. C.—Bronze. Str.—Black. Perfect basal cleavage. Laminæ are flexible, like tin-foil. Marks paper. Tabular crystals.

B.B. Roasted on charcoal becomes magnetic and the surface of the globule shows separated metallic silver. Fus.—1.5.

GALENA WHITE Lengenbachite Pb6(AgCu)2As4S13 (Very Rare) Microchem. HNO₃, Practically negative, but sometimes tarnishes slightly; rubs to faint gray. HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Neg. Brittle.

Description. C.—Steel-gray. Str.—Brownish. Marks paper. B.B. Yields arsenic odor and coat on coal (IV, 2, a). See Chapter IV.

GALENA WHITE Rathite Pb(As.Sb)S? (Very Rare)

Microchem. HNO₂, Very slowly tarnishes brown; rubs to faint gray.

Sometimes practically negative. HCl, Neg. KCN, Neg. FeCl₃,
Neg. HgCl₂, Neg. KOH, Tarnishes brown; rubs to faint gray. Hardness, Low. Brittle.

Description. C.—Blackish lead-gray. Str.—Reddish brown. Prismatic

GALENA WHITE

B.B. Yields common tests for constituents in formula. (Chap. IV).

GALENA WHITE Jordanite* Pb₄As₂S₇ (Very Rare)
Microchem. HNO₃, Tarnishes slightly; rubs clean. HCl, Neg. KCN,
Neg. FeCl₃, Neg. KOH, Neg.
Hardness, Low. 3. Brittle.
Description. C.—Lead-gray. Str.—Black. Six sided crystals.
B.B. Decrepitates strongly yielding arsenic odor and white coat on char-

coal; also a yellow lead oxide coat near the assay. Fus.-1. GALENA WHITE Guitermanite* 3PbS.As2S2? (Very Rare)

Microchem. HNO₃, Quickly tarnishes iridescent; rubs clean. HCl, Neg. KCN, Neg. FeCl₃, Neg. KOH, Neg. Hardness, Low. 3.
Description. C.—Bluish gray. Str.—Black. Massive, compact.

B.B. Like jordanite.

GALENA WHITE Epiboulangerite* Pb₃Sb₂S₈ (Very Rare)
Microchem. HNO₃, Tarnishes black; rubs to gray. Sometimes shows
small white crystals after rubbing. HCl, Neg. (Fumes sometimes
tarnish slightly.) KCN, Neg. FeCl₂, Neg. KOH, Neg. Hardness, Low.

Description, C.—Dark bluish gray, Str.—Black, Striated prismatic needles.

Yields antimony flame and coat on charcoal (IV, 1, a); also yellow lead oxide coat near the assay. Fus.-1.

WHITE Eucairite See page 97. WHITE Berzellianite See page 97. CREAMY WHITE Emplectite See page 63. GALENA WHITE Stibnite See page 87. GALENA WHITE Geocronite See page 79. GRAYISH WHITE Crookesite See page 94. GRAYISH WHITE Regnolite See page 119. GRAYISH WHITE JAMESONITE See page 62.

Andorite

99

See page 95.

KCN-N Low

Pals Brown Microchem. HVO. Tarnishne iridescent; rubs grev. HTA Nego MCN. Neg. For I. Neg. KOH. Throwbes brown rubs cheans not -

Hardwee, Low of L. S. C. - Hard. Sycharches dearence Description of the Company o

ale shows repaired motallic silver. Ires-1.5.

Oxform Where Lemmandedia of Phichigh and Avery Rand)
Microcleria, HNO, Practically negatives but immediate tomisfies
signifyr, rubs to built gray tolled, Negative Negative Negative See Hells Nes ROH Nes

B.B. Yanda arsenie odor and coast on coal (17: 2, or , See Chapter 17

Grand Weiter Butte of Charles State (Very Rais) Aberochem, GING, Veryeslowly famished browns, mas no faintiguey, Sometimes practically intention, TILL Negoviko McNee, NeCl.

Neg. HgCla Neg. KOH, Tamishos brown; rubt to daint grave Hardense, Low, British

Hardson, Low British Colleges St. Hoddish-brown Prisms to

CALLY AVERT CONTINUES CHARLES VOICE PROPERTY

Microchemical IVO . Themishes slightly side clean. Hell, New MON. Nog. of Paul Nour 100 H. Nag. Liver over the

Hardness, Low. S. Brittle.
Description. C. Lead-gray. Str. Black. Six sided envirals. . B. H ... Descriptions strongly violeing arable oder and while cost on charcoal; also a yellow lend exide cost mear the real walley a cale; less

Galkina Where Contemporate SPbS. AssS. P. Sci Very Rand Microchem. HNO, Quickly targestes indecembly rules chem. HCL. Negl KON, Negl McH. Negl KOH, Negl.

(Very Hundy CALENA WHITE. Husboulangerite" Microclem, HWO, Tarnishes black; subs to gray. Sometimes shows small white erestals attentioning, HCL, Neg. (Func. squedimes tarnish Slightly.), RCN, Neg. 4-CL, Neg. - KOH, Neg. - ACH, N

Hardoney, Low. Description. C.-silvah bluish gray, 18tt —Biado. Sadared primitive negdles

Wolfest out and another and court and court and the V. W. T. and another W. H. and another wolfest and the W. T. and another and the W. T. and another wolfest and the W. T. and t

WELLEN. See make ur. STINW Sec page 95.

GRAYISH WHITE STEPHANITE AgsSbS4

Microchem. HNO₃, Neg. HCl, Fumes slowly tarnish brown to iridescent; rubs clean. KCN, Quickly tarnishes brown; rubs pale brown, developing cracks. FeCl₃, Slowly gives a speckled surface; rubs clean. HgCl₂, Quickly tarnishes brown; rubs to brown. KOH, Slowly tarnishes nishes deep brown; rubs clean.

Hardness, Low. 2-2.5. Slightly sectile to brittle. Description. C. and Str.—Iron-black.

B.B. In the closed tube decrepitates and fuses, after long heating giving faint antimony sublimate. On charcoal fuses easily with spirting, yielding a white coat which may become red with oxidized silver. Roasted and reduced with soda yields silver button.

Microchem. HNO₃, Practically negative. (Faintly tarnishes and dissolves in two or three minutes.) HCl, Tarnishes slowly; rubs pale. BROWN KCN, With 20 per cent. solution almost negative, but rapidly tarnishes with very dilute solution and is noticeable usually after washing. FeCl₃, Tarnishes dark brown; rubs pale. HgCl₂, Neg. KOH, Neg. Hardness, Low (Variable).

Description. C.—Dark steel-gray to iron-black. Str.—Black.

B.B. Infusible. Yields manganese reactions with the fluxes. Evolves chlorine when treated with HCl.

GRAYISH WHITE Jalpaite See page 67.

BLUISH WHITE Proustite See page 109. THE PROPERTY OF THE PARTY OF TH

WOL

Microshum, HNO, Nog. HC3, Punny stouly tarnish brown to indes-cent; rubs clean. KCN, Quickly tainshes brown; rubs pale brown, developing coxoks. PaCls, Slowly gives a speckled surface; rubs clean the C. (suigkly tarnishes brown) rubs to brown. ACH, Slowly tar-

Hg (mail) tarmanes brown prios to blown mans deep brown; rube dem;.

Hardmess Low 2 ± 5. Slightly sentile to brittle.

Description. C and Six—dron-black.

B.B. In the closed tube descriptions and lower after long heating giving laint antimony sublimate. On pharmonal tubes randy with notiting redding a white coast which may become see randy with exiding fiver. Rossied and reduced with sods yields alver buttom.

sows Pyrolusite MacO.

Microchem. HMCs Practically negative. (Faintly tamishes and dissolves in two or three minutes.) HCl. Tamishes slowly; raisy pate KCON, With 20 per cent, solution almost negative, but majedy sermables antibers rate where addended is notices stuff your district. YeCl. Tamishes dark brown rubs pale, digth, Neg. NOH, Neg.

Description, C. Dark steel-gray to true-black. Ser. Black Soils

R.B. Inforble, Visits manyaness reactions with the fluxes. Evolutes

BLUISH WHITE

Grayish White (Creamy) Delafossite CuO, Fe₂O₃? (Very Rare) Microchem. HNO₃, Neg. HCl, Tarnishes slightly and acid turns yellowish-green; rubs to etched surface. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Neg. Hardness, Medium. 2.5. Brittle.

Description. C.—Dark gray. Str.—Blackish gray. Cleavable into laminæ. Occurs in small crystalline plates.

B.B. Fusible with difficulty, coloring the flame green. Easily soluble in HCl.

Gravish White (Creamy) Delajornie Coll, Fe-D. (Very Rare)
Microchem, HNO, Neg. HCl, Ternishes slightly and said turns yellowish-green; rubs to etched surface. KCN, Neg. FeCls. Neg.
HgCls. Neg. KOH, Neg.
Description. C.—Data grav. Str.—Biackish gray. Clearable into
lamine. Occurs in small rejetable plates.

O. House. College in small rejetable plates.

R.H. Fusible with difficulty, coloring the firms green. Pasify solable

DETERMINATIVE TABLES

KCN Med. FeCl₃

GRAYISH WHITE POLYBASITE See page 87.

HON Mod Feet

CHAYTER WRITE POLYRABITE See page 87.

Laboral Construction of two 1 ft individual today in Article con The restriction of a particle of the second of the today of the second of the

YELLOW BROWNISH WHITE GRAYISH WHITE

Chalcopyrite Enargite COWNISH WHITE Enargite See page 33.
RAYISH WHITE PYRARGYRITE See page 111.

See page 117. See page 83.

MCN Med. PeCt. N

YMLLOW Chalcopyrite Scopage 117.
BROWNTH WHITE BRAYGE Sc. See page 55.
GRAYISH WHITE TYMAGGIRITH See page 111.

Microchem. HNO₃, Neg. HCl, Neg. Fumes sometimes tarnish faintly; rubs clean. KCN, Slowly tarnishes brown, developing scratches; rubs to faint brown. FeCl₃, Slowly tarnishes faintly; rubs clean. HgCl₂, Slowly tarnishes brown; rubs to brownish iridescence. KOH Ouisely tarnishes black rubs to be brownish iridescence. BLUISH WHITE cence. KOH, Quickly tarnishes black; rubs to pale brown. Hardness, Low. 2.5. Slightly brittle. Blood-red powers.

Blood-red powder when

scratched.

Internal reflection as seen by inclined light is bright red. Description.—C. and Str.—Scarlet. Commonly as elongated crystals. B.B. Yields arsenic odor and white coat on charcoal. Prolonged heating in the O.F. or reduction with soda in the R.F. yields silver. Fus.-1.

Polyargyrite* Ag24Sb2S15 (Very Rare) BLUISH WHITE Microchem. HNO₃, Neg. Fumes often tarnish slightly; rubs clean. HCl, Neg. KCN. Quickly tarnishes brown; rubs clean. FeCl₃, Tarnishes dark or iridescent; rubs clean. KOH, Neg. Hardness, Low. 2.5. Very sectile.

Description. C.—Iron-black to grayish black. Str.—Black. cleavage.

B.B. Fuses easily on charcoal to a black globule, giving antimony flame and coat, and finally a brittle globule of silver. Fus.-1.

Cerargyrite AgCl GRAYISH WHITE Microchem. HNO₃, Neg. HCl, Neg. KCN, Quickly tarnishes to reddish brown; washes to dark solution pit. FeCl₃, Quickly tarnishes dark brown; rubs same. HgCl2, Neg. KOH, Slowly tarnishes; rubs pale.

Hardness, Low. 1-1.5. Highly sectile.

Description. C.—Pearl-gray, various. Str.—Waxlike. B.B. Fuses in closed tube without decomposition. On charcoal gives a globule of metallic silver.

GRAYISH WHITE AgBr (Very Rare) Bromyrite Microchem. HNO₂, Neg. HCl, Neg. KCN, Tarnishes slightly; rubs nearly clean. FeCl₂, Tarnishes dark gray to brown; rubs same. HgCl₂, Slight tarnish? KOH, Tarnishes rapidly and forms whitish coating.

Hardness, Low. Sectile.

Description. C.—Bright yellow to grass or olive green. Str.—Yellowish

green. No cleavage.

B.B. On charcoal emits bromine vapors and yields a globule of metallic silver. In the closed tube reacts like cerargyrite.

Embolite, Ag(Cl, Br), and iodobromite, 2AgCl.2AgBr.AgI, are intermediate between cerargyrite, bromyrite and iodyrite in all chemical and physical properties as well as in composition. The differences in color on the polished surface are usually enough to distinguish between any two that may be present together, and the difference in the rates of reaction with any of the active reagents easily brings out contrasts between them.

GRAYISH WHITE Jalpaite See page 67. GRAYISH WHITE Pearcite See page 85.

(Very Rare) BLUISH WHITE

Microchem, Like pyrargyrite.

Hardness Low

Hardness, Low. 2-2.5. Brittle. Cherry-red powder when scratched. Internal reflection as seen by inclined light is deep red. Description. C.—Iron-black to steel-gray. Str.—Cherry-red. B.B. On charcoal fuses quietly, giving a white antimony coat and a gray bead, which after continued treatment in the O.F. leaves a bright globule of silver. Fus.—1.

Grayish White Argyrodite Ag₆GeS₆? (Very Rare)
Microchem. HNO₃, Neg. HCl, Neg. KCN, Tarnishes brown, developing scratches; rubs to very faintly etched surface. FeCl₃, Neg. HgCl₂, Tarnishes brownish iridescent; rubs to iridescence. KOH, Neg.

HCI-N wo.I

Hardness, Low. 2.5. Brittle.

Description. C.—Steel-gray on a fresh fracture, with a tinge of reddish

violet. Str.-Gravish black.

B.B. In the closed tube yields a brilliant black sublimate; in the open tube fumes of sulphur dioxide. On charcoal fuses to a bead, giving near the assay a faint white sublimate; after long heating, an orange-yellow sublimate and a silver globule. Fus.—1.5.

RAYISH WHITE ORPIMENT As₂S₃
Microchem. HNO₃, Neg. HCl, Neg. KCN, Tarnishes dark quickly;
rubs nearly same. FeCl₂, Neg. HgCl₂, Yellow coat, rubs clean.

KOH, Quickly tarnishes black.

Hardness, Low. 1.5-2. Sectile. Lemon-yellow powder when scratched.

Internal reflection as seen by inclined light is yellow.

Description. C.-Lemon-yellow. Str.-Pale yellow. Usually in foli-

ated or columnar masses. Perfect pinacoidal cleavage.

B.B. On charcoal fuses and volatilizes entirely, yielding arsenic odor. In the closed tube, fuses, volatilizes, and gives a dark yellow sublimate. Fus.—1.

GRAYISH WHITE Iodyrite AgI (Very Rare)
Microchem. HNO₃, Neg. HCl, Neg. KCN, Quickly dissolves and tarnishes to dark surface; rubs to gray, etched surface. FeCl3, Neg. HgCl₂, Tarnishes brownish to iridescent; rubs same or slightly lighter.
KOH, Very slowly yields slight tarnish.
Hardness, Low. Sectile. Internal reflection seen by inclined light is yel-

lowish to brownish.

Description. C.—Yellow to yellowish green, sometimes brownish. Str.—
Yellow. Perfect C cleavage.

B.B. In the closed tube fuses and assumes a deep yellow color, but re-

sumes its yellow color on cooling. On charcoal gives fumes of iodine and a globule of metallic silver. oroperties as well as in composition. The differences in color on the

polished surface are usually enough to distinguish between any two that may be present together, and the difference in the rates of reaction with any of the active reagents castly brings out contrasts between BLUE Covellite CuS

Microchem. HNO3, Neg. HCl, Neg. KCN, Quickly tarnishes purple; rubs to grayish, deeply etched surface. FeCl2, Neg. HgCl2, Neg. KOH. Neg.

Hardness, Low. 1.5-2. Slightly brittle.

Description. C.—Deep indigo-blue. Str.—Gray to black. Perfect basal cleavage; flexible in thin leaves. Common in smaller quantities as a secondary mineral in nearly all copper deposits.

B.B. On charcoal burns with a blue flame, fusing to a globule which reacts like chalcocite (IV, 6). Fus.—2.5.

Native Gold Microchem. HNO₃, Neg. HCl, Neg. KCN, Slowly blackens; rubs to brownish, rough surface. FeCl₃, Neg. (?). HgCl₂, Neg. KOH, Neg. Hardness, Low. 2.5–3. Sectile. Yellow powder when scratched. Description. C. and Str.—Gold-yellow. B.B. Fuses easily to yellow button. Not acted on by any of the fluxes.

ALENA WHITE Livingstonite HgSb₄S₇ (Very Rare)
Microchem. HNO₃, Neg. (?) HCl, Neg. KCN, Slowly tarnishes
grayish. FeCl₂, Neg. HgCl₂, Tarnishes to brownish iridescence; rubs GALENA WHITE Livingstonite grayish. FeCl₃, Neg. HgCl₂, Tarnishes to brow same. KOH, Neg.
Hardness, Low. 2. Red powder when scratched.

Internal reflection as seen by inclined light is deep red.

Description. C.—Lead-gray. Str.—Red. Usually in slender prismatic crystals.

B.B. Roasted on charcoal is completely volatile. Yields antimony flame and coat (IV, 1, a). With soda in the closed tube yields mercury (IV, 12, a). Fus.—1.

Bluish White Onofrite Hg (SSe) (Very Rare)
Microchem. HOO₃, Neg. HCl, Neg. KCN, Faintly tarnishes brown or bluish, differentially; rubs to faint brown. FeCl, Neg. HgCl, Neg. KOH, Neg. Hardness, Low. 2.5. Sectile to slightly brittle. Some flakes show yellow internal reflection as seen by inclined light.

Description. C. and Str.—Blackish gray. Massive; fine granular. B.B. In the closed tube decrepitates and gives sublimates of sulphur and mercury (IV, 12, a). On charcoal gives copious fumes with selenium odor and a sublimate with metallic-like luster which touched by the R.F. disappears, coloring the flame azure-blue.

GRAYISH WHITE PYRARGYRITE Ag₃SbS₃ Microchem. HNO₃, Neg. HCl, Neg. KCN, Tarnishes pale brown slowly; rubs to faint gray surface showing structure. FeCl₃, Neg. HgCl₂, Slowly tarnishes light brown; rubs clean. KOH, Tarnishes black; rubs to speckled yellowish gray surface. Hardness, Low. 2.5. Brittle. Blood-red powder when scratched.

Internal reflection as seen by inclined light is brilliant red.

Description. C.—Black to grayish black. Str.—Purplish red. B.B. On charcoal fuses with spirting to a globule, coats the coal white, and the assay is converted into silver sulphide, which, treated in the O.F., or with soda in the R.F., gives a globule of silver. Fus.—1.

Bluish White Proustite See page 109. (Very Rare)

GRAYISH WHITE POLYBASITE See page 87.

are I

brownish, rough surface. 1943, Nag. (7) Highla Neg. 16414, Neg. 16414, Neg. 16414, Neg. 16414, Neg. 16514, Neg. 16

Characte Witten descriptions of Health Committee and State to the contribute of the

The Company of the Co

- Britis Verents VII

Microscher, HND, Neg. HCl. Nog. W.M. Tarrish v rath home. the line slewly remedies had been enough as a College Carnania

when the element in the spiriting of a printing cost was it becomes all all the

RAY Uraninite Uranate of U,Pb, etc. (Very Rare)
Microchem. HNO₃, Neg. HCl, Neg. KCN, Neg. FeCl₃, Slowly
tarnishes to still darker brownish gray; rubs same. HgCl₂, Neg. KOH, Neg.

Hardness, High. 5.5. Brittle.

Description. C.—Pitch-black to greenish. Str.—Greenish brown to black. Usually massive and botryoidal.

B.B. Infusible. In the R.F. gives a green bead with both borax and salt of phosphorous (IV, 26, a). Many impurities are always present and any or all may yield reactions.

Mondain Nogury with all seageths

like Limbulto, but Turgits is very table lighter in order, when

and they seem the management of the seem o

GRAYISH WHITE WOLFRAMITE (FeMn)WO. Microchem. Negative with all reagents.

Hardness, High. 5–5.5. Brittle.

Description. C.—Dark brown to nearly black. Str.—Reddish or brownish to nearly black. Perfect pinacoidal cleavage. Crystals

commonly tabular, bladed, columnar, etc.

B.B. Fuses to a magnetic globule with a crystalline surface. With soda yields a green manganate bead (IV, 11, a). For tests for tungsten, see

IV, 25. Fus.—3. (Note. Hübnerite, MnWO4, and Ferberite, FeWO4, differ from Wolframite only in color.)

SnO2 GRAY CASSITERITE Microchem. Negative with all reagents.

Hardness, High. 6-7.

Description. C.—Brown to black; variable. Str.—Light. B.B. Infusible. Reduced with soda and borax on charcoal yields metallie tin buttons.

2Fe₂O₃.3H₂O(?) GRAY (VARIABLE) Limonite Microchem. Negative with all reagents.

Hardness, High. 5-5.5. Brittle. Yellow powder when scratched. Internal reflection as seen by inclined light is often reddish brown.

Description. C.—Ocher-yellow to brownish black. Str.—Yellowish brown. Never crystallized. Usually botryoidal, concretionary, mas-

sive, earthy, etc.

B. Infusible. Yields water when heated in the closed tube. Other-B.B. Infusible. wise like hematite.

(Note.—Göthite, Fe₂O₃.H₂O, and Turgite, 2Fe₂O₃.H₂O, behave chemically like Limonite, but Turgite is very much lighter in color.)

FeCrOO GRAY CHROMITE Microchem. Negative with all reagents.

Hardness, High. 5.5.

Description. C.—Iron-black to brownish black; various. Str.—Brown. Commonly massive; fine granular to compact.

B.B. Infusible in O.F., but in R.F. is slightly rounded on edges and becomes magnetic. For tests for chromium see IV, 4.

GRAYISH WHITE Rare Earths Columbite, Tantalite, Samarskite, etc., are all chemically inert with the reagents used and are indistinguishable on polished sections.

MANGANESE OXIDES GRAYISH WHITE MANGANITE, Mn₂O₃.H₂O, HAUSMANNITE, MnO.Mn₂O₃, and BRAUNITE, 3Mn₂O₃.MnSiO₃, are all chemically inert with the reagents used.

KCN-N High FeC1-N

HITE Sperrylite PtAs₂ (Very Rare)

Microchem. HNO₃, Neg. HCl, Neg. KCN, Neg. FeCl₃, Neg.

HgCl₂, Neg. KCN, Neg. FeCl₃, Neg.

Hordness High 6.7, Poittle

Hardness, High. 6-7. Brittle. Description. C.—Tin-white.

Str.—Black. In minute isometric crystals.

B.B. Decrepitates slightly. Unchanged in the closed tube. Yields white arsenic trioxide sublimate in the open tube. Dropped on redhot platinum foil, melts, gives off arsenic trioxide fumes, and deposits porous platinum on the foil. Fus.-2.

PINKISH WHITE Cobaltite CoAsS
Microchem. HNO₃, Neg. HCl, Neg. KCN, Neg. (Sometimes slowly faint tarnish rubs clean.) FeCl₂, Neg. HgCl₂, Neg. KOH, Neg. Hardness, High. 5.5. Brittle.

Description. C.—Silver-white, inclined to pinkish. Str.—Grayish black.

Good cubic cleavage. Often in cubic crystals.

B.B. Unaltered in the closed tube. On charcoal yields an arsenic coat and fuses to a magnetic globule. When well roasted it yields a blue bead with borax. Fus.—2–3.

CREAMY WHITE Hematite Fe₂O₃ Microchem. Negative with all reagents.

Hardness, High. 5.5-6.5. Brittle. Brownish red to gray powder when scratched.

Description. C.—Reddish brown, steel-grav, to iron-black. Str.— Cherry-red.

B.B. Infusible. On charcoal in R. F. becomes magnetic.

GRAYISH WHITE Magnetite Fe₃O₄
Microchem. Negative with all reagents. Hardness, High. 5.5-6.5. Brittle.

Description. C .- Iron-black. Str.-Black, Naturally strongly magnetic.

B.B. Nearly infusible. In the O.F. loses its magnetism. With the fluxes reacts like hematite.

Grayish White Ilmenite FeTiO₃
Microchem. Negative with all reagents.

Hardness, High. 5-6. Brittle. Description. C.—Iron-black. Str.—Black to brownish.

B.B. Infusible in O.F., but slightly rounded on edges in hottest R.F. For wet test for titanium see (IV, 24, b and c).

GRAYISH WHITE Rutile TiO, Microchem. Negative with all reagents.

Hardness, High. 6-6.5.

Internal reflection as seen by inclined light sometimes is reddish.

Description. C.-Reddish brown to nearly black. Str.-Pale brown. Occurs usually in prismatic crystals. Knee-like twins.

Infusible. Yields bead and wet tests for titanium (IV, 24).

GRAYISH WHITE Franklinite (FeZnMn)O.(FeMn)₂O₃ (Very Rare)
Microchem. Negative with all reagents.
Hardness, High. 5.5-6.5. Brittle.
Description. C.—Iron-black. Str.—Very dark brown.
B.B. Infusible. With soda gives a green manganate bead and on charcoal a coating of zinc oxide (IV, 29).
(Note.—Chalcophanite (Mn,Zn)O.2MnO₂.2H₂O, is also grayish white and

behaves chemically like Franklinite.)

Löllingite See page 91. WHITE

RAY Voltzite Zn₅S₄O (Very Rare) Microchem. Negative with all reagents. (HNO₃, fumes sometimes GRAY tarnish very faintly.) Hardness, Medium. 4-4.5.

Internal reflection as seen by inclined light is reddish yellow or brown. Description. C.—Dirty rose-red, yellowish, or brownish. Str.—Light.

Occurs thin curved, lamellar, etc.

B.B. Nearly infusible. Reduced with soda on charcoal yields white zinc oxide coat, which when moistened with cobalt nitrate solution and again heated in the O.F. becomes green (IV, 29, a)

(MnZn)S (Very Rare) Erythrozincite* and fuses to a maigners of Microchem. Negative with all reagents.

Hardness, Medium to low.

Description. C.—Red. Str.—Pale yellow. Occurs in thin plates. Yields green manganate bead with soda. Also usual tests for zinc.

Michael High. 5 d. Brinke
Description C.—Iron-Deck. Str.—Black to brownish.
B.R. Irinabic in O.F. and slightly bounded on ellips in horself.
Francis last for plantum see (IV, 24, 4, and a).

Legan reported as seen to under the first and the first land of the brown to unserfy land for the brown of course smalls in generating exystals. Instable to the first land the first land of th

KCN-N Med. FeCl₃-N

Chalcopyrite CuFeS₂

Microchem. HNO3, Neg. (Sometimes tarnishes brown; rubs faint. Fumes also tarnish in such cases.) HCl, Neg. KCN, Neg. (Rarely tarnishes iridescent with development of scratches.) FeCl₂, Neg. Hardness, Medium. 3.5-4. Brittle.

Description. C.—Brass-yellow. Str.—Greenish.

B.B. On charcoal fuses to a magnetic globule in R. F. Decrepitates in closed tube and gives sulphur sublimate. Roasted and reduced with soda, yields copper buttons. Fus.—2.
ENA WHITE Chalcostibite* CuSb

GALENA WHITE CuSbS₂ (Very Rare)

Microchem. Negative with all reagents.

Microchem. Negative with all reagents.

Hardness, Medium. 3-4. Brittle,
Description. C.—Blackish gray. Str.—Black. Perfect basal cleavage.

B.B. Yields antimony flame and coat on charcoal. Reduced with soda gives a globule of metallic copper. Fus.—1.5.

GALENA WHITE Berthierite FeSb₂S₄ (Very Rare)
Microchem. HNO₃, Neg. HCl, Neg. KCN, Neg. FeCl₃, Neg.
KOH, Slowly tarnishes brownish; rubs faint or clean.

Hardness, Medium to low. 2-3.

Description. C.—Steel-grav. Str.—Black. Elongated prisms or fibrous massive.

B.B. Fuses easily, yielding an antimony flame and coat on charcoal, and a magnetic residue. Fus.—2.

Pb4As6S13 (Very Rare) GRAYISH WHITE Baumhauerite

Microchem. HNO₃, Neg. (Sometimes tarnishes along cracks; rubs clean.) HCl, Neg. KCN, Neg. (Sometimes tarnishes along cracks.) FeCl₃, Neg. HgCl₂, Slowly tarnishes brown; rubs to pale brown. KOH, Tarnishes iridescent; rubs clean.

Hardness, Medium to low. 3. Brittle.

Internal reflection as seen by inclined light is often red.

Description. C.—Lead-gray. Str.—Brown. One perfect cleavage. B.B. Yields arsenic odor and coat on charcoal; lead coat near the assay. With KI & S flux gives lemon-yellow lead iodide coat (IV, 10, a).

GRAYISH (BROWNISH) WHITE Tetrahedrite Cu₈Sb₂S₇

Microchem. HNO3, Neg. (Fumes sometimes tarnish faint brown; rubs clean.) HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Neg.

Hardness, Medium. 3-4.5. Very brittle. Description. C.—Gray to black. Str.—Brown to black.

B.B. Reacts for copper, antimony, arsenic, silver, and often mercury, etc. Almost impossible to distinguish between tetrahedrite and tennantite. Fus.—1.5.

GRAYISH (GREENISH) WHITE Tennantite Cu₈As₂S₇ Like tetrahedrite into which it grades chemically.

PALE YELLOW MILLERITE See page 95. CREAM Pyrrhotite See page 95. CREAM Chalmersite See page 95. CREAMY WHITE PENTLANDITE See page 95. GRAYISH WHITE BOURNONITE See page 94. tarnishes reidescent with development of seratebes.) NeCl., Neg.

GRAYISH WHITE Cinnabar HgS
Microchem. Negative with all reagents used.

Hardness, Low. 2-2.5. Slightly sectile. Carmine-red powder when scratched.

Microchem, HND, Nog. (Sometimes tarnishes brown; tube faint. Funct also tarnish in such cases.) HCB, Nog. KCN, Neg. (Barely

Internal reflection as seen by inclined light is carmine-red.

Description, C.—Cochineal-red, inclining to brownish and lead gray. Perfect prismatic cleavage.

B.B. On charcoal entirely volatile when pure. In closed tube alone gives a black sublimate of mercuric sulphide, but with soda, one of metallic mercury. Fus.-1.5.

GRAYISH WHITE Metacinnabarite HgS (Very Rare)
Microchem. Negative with all reagents used. (HNO₃ sometimes Metacinnabarite HgS (Very Rare) tarnishes faintly.)
Hardness, Low. 3. Slightly brittle.
Description. C.—Grayish black. Str.—Black.

B.B. Like cinnabar.

Grayish White Patronite VS4(?) (Very Rare)

Microchem. HNO3, Neg. HCl, Neg. KCN, Neg. FeCl3, Neg.

HgCl2, Neg. KOH, Tarnishes iridescent; rubs to paler iridescence.

Hardness. Very low. Sectile.

Description. C.—Bluish black. Str.—Bluish gray. Occurs massive

and amorphous.

B.B. Gives test for vanadium with S. Ph. bead. Also wet tests.

RAY Lorandite* TlAsS₂ (Very Rare)
Microchem. HNO₃, Neg. HCl, Neg. KCN, Neg. FeCl₃, Neg. KOH, Quickly develops coating of orange; rubs clean to rough surface. Hardness, Low. 2-2.5. Dark red powder when scratched. Internal reflection as seen by inclined light is orange-red.

Description. C.—Carmine-red, often tarnishes gray on the surface. Str.—Cherry-red. Perfect pinacoidal cleavage yielding flexible lamellæ.

B.B. For tests for the rare element thallium see Chapter IV, 21.

GALENA WHITE Freieslebenite See page 98.
See page 117. GALENA WHITE Berthierite GALENA WHITE See page 99. Lengenbachite See page 99. Rathite GALENA WHITE See page 117. GRAYISH WHITE Baumhauerite See page 97. GRAYISH WHITE Molybdenite GRAY Erythrozincite See page 116.

GALENA WHITE

Microchem. HNO₃, Neg. HCl, Neg. KCN, Neg. FeCl₃, Neg. HgCl₂, Neg. KOH, Tarnishes iridescent and darkens; rubs to faint gray, etched surface.

Hardness, Low. 3. Brittle.

Description, C.—Blackish gray, Str.—Reddish brown, Perfect basal

cleavage.

B.B. On charcoal decrepitates, fuses, and yields a globule of lead which gives trace of silver on cupellation. Also gives arsenic coat on charcoal. Fus.—1.

GALENA WHITE Matildite* AgBiS2 (Very Rare)

Microchem. Negative with all reagents used.

Hardness, Low.

Description. C.-Gray. Str.-Light gray. Often as slender striated

B.B. Fuses easily on charcoal, giving a coating of bismuth oxide and on

long heating a globule of silver.

GALENA WHITE Lehrbachite PbSe + HgSe Microchem. Negative with all reagents used.

Hardness, Low. Quite brittle.

Description. C.—Lead-gray to iron-black. Occurs massive, granular, etc.

B.B. On charcoal yields to a strong odor of selenium and partly fuses. In the closed tube gives a lustrous metallic gray sublimate of mercury selenide, with sodium carbonate a sublimate consisting of globules of mercury.

Tiemannite BLUISH WHITE HgSe (Very Rare) Microchem. Negative with all reagents used.

Hardness, Low. 2.5. Sectile to slightly brittle.

Description. C.—Blackish gray. Str.—Black.

B.B. Decrepitates in the closed tube and when pure entirely sublimes, giving a black sublimate with the upper edge reddish brown. On charcoal yields selenium odor and blue flame and deposits a white coat with a metallic-like luster.

TlAs₂SbS₅ (Very Rare) BLUISH WHITE Vrbaite* Microchem. HNO3, Neg. HCl, Neg. KCN, Neg. FeCl3, Neg. KOH, Tarnishes iridescent; rubs to gray.

Hardness, Low. Internal reflection by inclined light is red. Yellowish red powder when scratched.

Description. C.-Gray-black. Str.-Light yellowish red.

Ag₄Te? (Very Rare) BLUISH WHITE Stützite* Microchem. Negative with all reagents used.

Hardness, Low.

Description. C.—Lead-gray with reddish tinge. Str.—Blackish lead-

B.B. Easily fusible to a dark bead from which a silver globule is obtained by reduction with soda. Yields tellurium oxide in the open tube. (IV, 20, c).

Cu7As2S12 GRAYISH WHITE Regnolite (Very Rare)

Microchem. Negative with all reagent used. (HNO3 fumes sometimes tarnish faint brown; rubs clean.)

Hardness, Low.

Resembles tetrahedrite and tennatite very closely.

Microchem. Seligmannite CuPbAsS₃ (Very Rare)
Microchem. HNO₃, Neg. HCl, Neg. KCN, Neg. FeCl₃, Neg.
HgCl₂, Neg. KOH, Slowly tarnishes to iridescence; rubs clean.
Hardness, Low. Sectile to slightly brittle.
Description. C.—Blackish gray. Str.—Brownish black. GRAYISH WHITE

B.B. Like bournonite except tests for arsenic instead of antimony.

CHAPTER IV

SUPPLEMENTARY TESTS

TABULATED PROPERTIES OF ORE MINERALS

Some few of the opaque minerals when viewed on a polished surface with vertical illumination show colors other than shades of white or gray. The following table will often be helpful in immediately identifying these minerals.

Table 7

Color	Mineral	Formula	Page
Purple	Umangite	Cu ₃ Se ₂	77
Purple	Rickardite	Cu ₄ Te ₃	35
Blue	Covellite	CuS	111
Yellow	Chalcopyrite	CuFeS ₂	117
Yellow	Gold	Au	111
Pale yellow	MILLERITE	NiS	95
Cream	(Pyrite)	FeS ₂	57
Cream	(Marcasite)	FeS_2	57
Cream	Pyrrhotite	FeS(S) _x	95
Cream	PENTLANDITE	(FeNi)S	95
Cream	Chalmersite	$CuFe_2S_3$	95
Cream	Whitneyite	Cu ₉ As	33
Cream	Maucherite	Ni ₃ As ₂	55
Cream	Hauchecornite	(NiCo) ₇ (Bi,S,Sb) ₈	91
Cream	Sulvanite	Cu ₈ VS ₄	65
Creamy pink	Niccolite	NiAs	55
Coppery pink	Copper	Cu	51
Coppery pink	Breithauptite	NiSb	93
Brown	Bornite	$\mathrm{Cu}_5\mathrm{FeS}_4$	53
Cream Creamy pink Coppery pink Coppery pink	Sulvanite Niccolite Copper Breithauptite	Cu _s VS ₄ NiAs Cu NiSb	65 55 51

When the vertical illumination is cut out and the light from some strong source is allowed to strike the polished surface at an inclination, a number of the ore minerals reveal more or less brilliantly colored internal reflections. These colors are quite characteristic of certain minerals and should always be observed in the course of an identification. Table 8 lists those minerals in which such colors are commonly seen.

TABLE 8

C	Mineral	n .	-
Color of internal reflection	Mineral	Formula	Page
Red	Baumhauerite	Pb4As6S13	117
Red	Cinnabar	HgS	118
Red	Cuprite	Cu ₂ O	33
Red	Jalpaite	3Ag ₂ S.Cu ₂ S	67
Red	KERMESITE	Sb ₂ S ₂ O	87
Red	Livingstonite	HgSb ₄ S ₇	111
Red	Miargyrite	AgSbS ₂	110
Red	POLYBASITE	Ag ₉ SbS ₆	87
Red	Proustite	Ag ₃ AsS ₃	109
Red	PYRARGYRITE	Ag ₃ SbS ₃	111
Red	(Rutile?)	TiO ₂	115
Red	Vrbaite	TlAs ₂ SbS ₅	119
Reddish brown	Limonite	$2\mathrm{Fe}_2\mathrm{O}_3.3\mathrm{H}_2\mathrm{O}$	114
Reddish brown	Hübnerite	MnWO ₄	114
Brown or yellow	(CASSITERITE?)	SnO ₂	114
Brown or yellow	Sphalerite	ZnS	94
Brown or reddish yellow	Voltzite	Zn ₅ S ₄ O	116
Brownish or greenish	Cuprodescloizite	(PbZnCu) ₄ V ₂ O ₉ .H ₂ O	75
Olive green	ALABANDITE	MnS	41
Orange red	Lorandite	TlAsS ₂	118
Orange	REALGAR	AsS	62
Yellow	(Onofrite?)	Hg(SSe)	111
Yellow	ORPIMENT	As ₂ S ₃	110

When the polished surface of an ore mineral is deeply scratched or gouged with a sharp needle a powder is usually produced, and although this is gray or black in the majority of minerals, a few yield a powder or scratch with distinct colors as seen under the microscope with vertical illumination. This property may often be used as a valuable aid in mineral identification. The minerals giving powders of characteristic colors in this way are grouped in Table 9 which follows:

122 MICROSCOPIC EXAMINATION OF THE ORE MINERALS

TABLE 9

Color of powder	Mineral	Formula	Page
Carmen red	Cinnabar	"HgS	118
Blood red	Cuprite	Cu ₂ O	33
Blood red	Jalpaite	3Ag ₂ S.Cu ₂ S?	67
Blood red	Proustite	Ag_3AsS_3	109
Blood red	PYRARGYRITE	Ag_3SbS_3	111
Red	KERMESITE	Sb ₂ S ₂ O	87
Red	Livingstonite	HgSb ₄ S ₇	111
Red	Lorandite	TlAsS ₂	118
Red	Miargyrite	AgSbS ₂	110
Reddish brown	Hauerite	MnS_2	94
Reddish brown	Hematite	Fe_2O_3	115
Reddish brown	Regnolite	$Cu_7As_2S_{12}$	119
Pink	Copper	Cu	51
Golden brown	Bornite	Cu_5FeS_4	53
Brown to yellow	Sphalerite	ZnS	94
Orange	REALGAR	AsS	62
Reddish yellow	Cuprodescloizite	(PbZnCu) ₄ V ₂ O ₉ .H ₂ O	75
Yellow	CHROMITE	FeCr ₂ O ₄	114
Yellow	Gold	Au	111
Yellow	Limonite	$2\mathrm{Fe}_2\mathrm{O}_3.3\mathrm{H}_2\mathrm{O}$	114
Yellow	ORPIMENT	As_2S_3	110
Olive-green	ALABANDITE	MnS	41

Table 10.—Classification According to Electrical Conductivity,
Measured with Two Dry Cells with Voltmeter, and using
Sharp's No. 9 Sewing Needles for Terminals

Electrical conductivity equal to or greater than copper, voltmeter reads 150	Average voltmeter readings	Apparently non-conductors voltmeter reads 0
Arsenic (native)	147 Onofrite	Aikinite
Algodonite	145 Löllingite	Alabandite
Antimony (native)	142 Petzite	Andorite
Bismuth (native)	142 Bornite	Argyrodite
Calaverite	142 Tiemannite	Baumhauerite
Chalcopyrrhotite	140 Clausthalite	Boulangerite
Chloanthite	137 Arsenopyrite	Bournonite
Coloradorite	137 Eucairite	Brongniardite
Copper (native)	135 Chalcocite	Cassiterite
Covellite	130 Metacinnabarite	Chromite
Dyscrasite	130 Ploydymite	Cinnabar
Geradorffite	126 Kalgoorlite	Cuprite
Glaucodot	126 Altaite	Cuprodescloisite
Harrisite	124 Chalcopyrite	Cylindrite
Hauchecornite	120 Galena	Delafossite
Hessite	120 Stutzite	Dufrenoysite
Huntilite	120 Luzonite	Emplectite
Kallilite	120 Tennantite	Franklinite
Krennerite	120 Aguilarite	Geocronite
Linnæite	109 Steinmannite	Hauerite
Magnetite	85 Berzellianite	Horsfordite
Maucherite	80 Naumannite	Jalpaite
Melonite	70 Nagyagite	Jordanite
Millerite	57 Polytelite	Kermesite
Mohawkite	55 Stromeyerite	Legenbachite
Niccolite	50 Pearceite	Limonite
Pentlandite	37 Cobaltite	Lorandite
Pyrrhotite	25 Guanajuatite	Matildite
Rammelsbergite	15 Chivatite	Meneghinite
Safflorite	15 Enargite	Miargyrite
Silver (native)	12 Marcasite	Orpiment
Skutterudite	7 Regnolite	Plagionite
Smaltite	7 Lillianite	Polyargyrite
Sternbergite	7 Rezbanyite	Proustite
Sylvanite	7 Pyrite	Pyrargyrite
Tellurium (native)	7 Ilmenite	Rathite
Ullmannite	5 Psilomelane	Realgar
Whitnevite	5 Jamesonite	Rutile
Willyamite	3 Plenargyrite	Seligmannite
	3 Chalmersite	Semseyite
	3 Famatinite	Sphalerite
	3 Cosalite	Stephanite
	2 Bismuthinite	Stibnite
	2 Argentite	Sulvanite
	2 Stannite	Tenorite
	1 Stylotypite	Tetrahedrite
	1 Teallite	Uraninite
	1 Frankeite	Voltzite
	1 Polybasite	Wittichenite
	1 Molybdenite	Wurtzite
	1 Hematite	

MINERALS
ORE
OF
.—ELECTRO-POTENTIALS
3LE 11
TABLE

	50 per cent. Au- 50 per cent. Cu to 60 per cent. Au-40percent. Cu	(Pyrite) Smaltite Cobaltite Pyrolusite
	5 per cent. Au-95 10 per cent. Au - 20 per cent. Au-80 30 per cent. Au-70 40 per cent. Au-60 per cent. Au-90 per cent. Cu to 10 90 per cent. Cu to 20 per cent. Au-70 per cent. Au-80 per cent. Au-80 per cent. Cu per cent. Au-80 per cent. Cu	(Famatinite) Arsenopyrite Millerite Covellite (Hessite) Metacinnabarite Coloradoite (Enargite) Pyrite
JEE MINEMANS	30 per cent. Au-70 per cent. Cu to 40 per cent. Au-60 per cent. Cu	Linnæite (Magnetite) Gersdorffite Hessite Enargite (Pyrite) Famatinite Löllingite Luzonite Lehrbachite Psilomelane
TABLE II ELECTRO-POTENTIALS OF ORE MINERALS	20 per cent, Au-80 per cent, Cu to 30 per cent. Au-70 per cent, Cu	Chloanthite Bornite Chalcocite Galena Galena Tetradymite Dyscrasite Magnetite Marcasite Nagyagite Native silver Stromeyerite Maucherite Tennantite Tellurium
I.—ELECTRO-PO	10 per cent. Au- 90 per cent. Cu to 20 per cent. Au- 80 per cent. Cu	Niccolite
LABLE 1	5 per cent. Au-95 per cent. Cu to 10 per cent. Au-90 per cent. Cu	Pyrrhotite (Domeykite)
	Between 5 per cent. Au-95 per cent. Cu and 100 per cent. Cu	Mohawkite Domeykite
	Potential Less than 100 per cent. Cu	Arsenic

TESTS FOR THE ELEMENTS9

1. Antimony, Sb

ANTIMONY MINERALS

Minera	Formula	Page
Andorite	PbAgSb ₃ S ₆	95
Berthierite	$FeSb_2S_4$	117
Boulangerite	$Pb_3Sb_2S_6$	63
BOURNONITE	(Cu2Pb)3Sb2S6	94
Breithauptite	NiSb	93
Brongniardite	PbAg ₂ Sb ₂ S ₅	69
Chalcostibite	CuSbS ₂	117
Cylindrite	$Pb_6Sb_2Sn_6S_{21}$	77
Dyscrasite	Ag ₆ Sb, etc.	67
Epiboulangerite	Pb ₃ Sb ₂ S ₈	99
FAMATINITE	Cu ₃ SbS ₄	83
Franckeite	$Pb_{\delta}Sn_{2}Sb_{2}S_{12}$	79
Freibergite	$(CuAg)_8Sb_2S_7$	82
Freieslebenite	(Pb,Ag ₂) ₅ Sb ₄ S ₁₁	98
Geocronite	$Pb_{5}Sb_{2}S_{8}$	79
Guejarite	$\text{Cu}_2\text{Sb}_4\text{S}_7$	83
Hauchecornite	(NiCo) ₇ (BiSbS) ₈	91
Horsfordite	Cu ₆ Sb	63
JAMESONITE	Pb ₂ Sb ₂ S ₅	62
Kallilite	Ni(SbBi)S	57
KERMESITE	Sb ₂ S ₂ O	87
Livingstonite	HgSb ₄ S ₇	111
Meneghinite	Pb ₄ Sb ₂ S ₇	79
Miargyrite	$AgSbS_2$	110
Nagyagite	Au ₂ Pb ₁₀ Sb ₂ Te ₆ S ₁₅	98
Plagionite	Pb 5Sb 8S17	43
Polyargyrite	Ag24Sb2S15	109
POLYBASITE	Ag_9SbS_6	87
PYRARGYRITE	Ag_3SbS_3	111
Rathite	Pb(As,Sb), S	99
Semseyite	Pb7Sb6S16	45
STEPHANITE	Ag_5SbS_4	101
Stibnite	$\mathrm{Sb}_2\mathrm{S}_3$	87
Stylotypite	3(Cu2Ag2Fe)S.Sb2S3	94
Tetrahedrite	Cu ₈ Sb ₂ S ₇	117
Ullmannite	NiSbS	91
Vrbaite	TlAs ₂ SbS ₅	119
Willyamite	(CoNi)SbS	57
Zinkenite	PbSb ₂ S ₄	62

⁹ Reference has been made to standard works on mineralogy and blowpipe analysis by A. H. Phillips, Moses and Parsons, Brush and Pen-FIELD, etc.

126 MICROSCOPIC EXAMINATION OF THE ORE MINERALS

- (a) Coat on Charcoal.—Antimony minerals, when heated on charcoal in the O.F. yield a white oxide coat which settles fairly near the assay. This coat is volatile and may be completely driven off with either flame. The powdered mineral, when fused with KI & S flux on charcoal, yields a faint yellow coat
- (b) Flame Test.—When the above coat is quickly volatilized in the O.F. the flame is colored a pale yellowish-green. (Arsenic coat colors the flame faint violet.)
- (c) Closed Tube Reaction.—Most minerals containing both antimony and sulphur, when heated in the closed tube, yield a black sublimate when hot, which becomes reddish-brown upon cooling.
- (d) Open Tube Reaction.—Minerals containing antimony and sulphur, when heated in the open tube, yield dense white fumes which settle along the lower half of the tube. This sublimate is volatile and can be entirely driven off.

2. Arsenic, As

ARSENIC MINERALS

Mineral	. Formula	Page
Arsenic	As	59
Arsenopyrite	FeAsS	57
Baumhauerite	$Pb_4As_6S_{13}$	117
Chloanthite	NiAs ₂	89
Cobaltite	CoAsS	115
Domeykite	Cu ₃ As	35
Dufrenoysite	$Pb_2As_2S_5$	119
Enargite	Cu ₃ AsS ₄	83
GERSDORFFITE	NiAsS	89
GLAUCODOT	(CoFe)AsS	91
Guitermanite	Pb ₃ As ₂ S ₆	99
Jordanite	$Pb_4As_2S_7$	99
Lengenbachite	$Pb_6(AgCu)_2As_4S_{13}$	99
Löllingite	FeAs_2	91
Lorandite	TlAsS ₂	118
Luzonite	Cu ₃ AsS ₄	83
Maucherite	Ni ₃ As ₂	55
Niccolite	NiAs	55
ORPIMENT	$\mathrm{As_2S_3}$	110
Pearcite	Ag_9AsS_6	85
Proustite	Ag_3AsS_3	109
Rammelsbergite	NiAs ₂	89
Rathite	Pb(AsSb)S	99
REALGAR	AsS	62

Mineral	Formula	Page
Regnolite	$Cu_7As_2S_{12}$	119
Safflorite	CoAs ₂	55
Seligmannite	CuPbAsS ₃	119
Smaltite	CoAs ₂	55
Sperrylite	PtAs ₂	115
Tennantite	$\mathrm{Cu_8As_2S_7}$	117
Vrbaite	TlAs ₂ SbS ₅	119
Whitneyite	$\mathrm{Cu}_{9}\mathrm{As}$	33

- (a) Coat on Charcoal.—Arsenic minerals, when heated on charcoal in the O.F. yield a white oxide coat which settles at a distance from the assay. (Beyond the antimony coat.) This coat is extremely volatile in either flame and, with the R.F. especially, strong characteristic garlic-like odors are given off.
- (b) Flame Test.—When arsenic minerals are heated on charcoal in the R.F. the flame is colored a faint violet. (Antimony yields a pale, yellowish green flame.)
- (c) Closed Tube Reaction.—Fusible arsenic minerals mixed with coal dust are placed in the bottom of a narrow closed tube and covered with a small splinter of charcoal. First heat the coal to glowing and then the mineral and coal dust mixture. Any arsenic present, reduced in passing over the hot carbon, deposits as a mirror on the cold walls of the tube. The mirror may be tested by breaking off the bottom of the tube and heating in the Bunsen flame. The characteristic garlic-like odor of arsenic can now be detected as the fumes escape from the mouth of the tube. These fumes also impart a faint violet tinge to the flame if allowed to escape in it. Most arsenic minerals when heated in the closed tube without a flux yield a sublimate which is dark red when hot and reddish-yellow when cold.
- (d) Open Tube Reactions.—Arsenic minerals, when very slowly heated in the open tube, yield a ring of white crystals which are very volatile and may be completely driven off from the tube upon heating. No arsenic odor is usually noticed in this test.

3. Bismuth, Bi

BISMUTH MINERALS

Mineral	Formula	Page
Aikinite	PbCuBiS ₃	63
Beegerite	$Pb_6Bi_2S_9$	98
Bismuth	Bi	43
Bismuthinite	$\mathrm{Bi}_2\mathrm{S}_3$	62
Chilenite	Ag_6Bi	35
Chiviatite	$\mathrm{Pb}_{2}\mathrm{Bi}_{2}\mathrm{S}_{11}$	63
Cosalite	$Pb_2Bi_2S_5$	59
Dognacskaite	Cu, Bi, and S	63
Emplectite	CuBiS ₂	63
Guanajuatite	$\mathrm{Bi}_{2}\mathrm{Se}_{3}$	98
Hauchecornite	(NiCo) ₇ (BiSSb) ₈	91
Kallilite	Ni(SbBi)S	57
Lillianite	$\mathrm{Pb_3Bi_2S_6}$	77
Matildite	$AgBiS_2$	119
Rezbanyite	$Pb_4Bi_{10}S_{19}$	61
Tapalpaite	$3Ag_2(STe).Bi_2(STe)_3$	43
Tetradymite	$\mathrm{Bi_2(Te,S)_3}$	61
Wittichenite	$\mathrm{Cu}_3\mathrm{BiS}_3$	93

(a) Coat on Charcoal.—Bismuth minerals, finely powdered and mixed with 2 or 3 parts of sodium carbonate, when heated in the R.F., yield metallic globules which are brittle instead of malleable (as in the case of lead). If the heating is continued, oxide forms and volatilizes, depositing a yellow coat close to the assay. This coat is very similar to that of lead and is best distinguished from it by means of the iodide reaction. The above coat moistened with hydriodic acid and heated gently in the O.F., or the powdered mineral mixed with 2 or 3 parts of KI & S flux and similarly heated, yields a brick-red bismuth iodide coat at some distance from the assay, inside of which there is often a yellow oxide coat.

4. Chromium, Cr

Chromite FeCr₂O₄ Page 114

(a) Bead Tests.—The bead tests for chromium, as for most other elements are only satisfactory when other substances do not interfere. The colors of the borax and S.Ph. beads are given in Table 17, page 149.

(b) Wet Test.—Fuse the finely ground chromium mineral mixed with 4 parts sodium carbonate and 2 parts of potassium nitrate

on a platinum wire. The fusion is dissolved in 2 or 3 c.c. of water, acidified with acetic acid, and filtered if the solution is not clear. If 2 or 3 drops of lead acetate are now added, any chromium present will be precipitated as yellow lead chromate. This may be filtered off and tested as in (a).

5. Cobalt, Co

COBALT MINERALS

Minera	Formula .	Page
Cobaltite	CoAsS	115
GLAUCODOT	(CoFe)AsS	91
Hauchecornite	(NiCo)7(BiSSb)8	91
Linnæite	Co ₃ S ₄	91
Safflorite	CoAs ₂	55
Smaltite	CoAs ₂	55
Willyamite	(CoNi)SbS	57

(a) Bead Tests.—Cobalt minerals, when dissolved in S.Ph. or borax, after roasting on charcoal, yield a deep blue bead in all flames. This test is quite sensitive, but if very large amounts of copper or nickel are present the borax bead should be taken from the wire and reduced beside tin on charcoal. The copper and nickel are absorbed by the tin and the bead will remain blue.

6. Copper, Cu

COPPER MINERALS

	COLLEGE MILITERALIS	
Mineral	Formula	Page
Aikinite	PbCuBiS ₃	63
Berzelianite	· Cu ₂ Se	97
Bornite	$\mathrm{Cu}_5\mathrm{FeS}_4$	53
BOURNONITE	(PbCu2)3Sb2S6	94
Chalcocite	Cu ₂ S	51
Chalcopyrite	CuFeS ₂	117
Chalcostibite	$CuSbS_2$	117
Chalmersite	CuFe ₂ S ₃	95
Copper	Cu	51
Covellite	CuS	111
Crookesite	(CuTlAg) ₂ Se	94
Cuprite	Cu ₂ O	33
Cuprodescloizite	$(PbZnCu)_4V_2O_9.H_2O$. 75
Delafossite	CuO,Fe ₂ O ₃	103
Dognacskaite	Cu, Bi, and S	63
Domeykite	Cu ₃ As	35
Emplectite	CuBiS ₂	63
Enargite	Cu ₃ AsS ₄	83,

130 MICROSCOPIC EXAMINATION OF THE ORE MINERALS

Mineral	Formula	Page
Eucairite	Cu ₂ Se.Ag ₂ Se	97
FAMATINITE	Cu_3SbS_4	83
Freibergite	$(CuAg)_{\delta}Sb_{2}S_{7}$	82
Guejarite	. Cu ₂ Sb ₄ S ₇	83
Horsfordite	Cu ₆ Sb	63
Jalpaite	Cu ₂ S.3Ag ₂ S	67
Lengenbachite	$Pb_6(AgCu)_2As_4S_{13}$	99
Luzonite	Cu_3AsS_4	83
Regnolite	$\mathrm{Cu_7As_2S_{12}}$	119
Rickardite	$\mathrm{Cu_4Te_3}$	35
Seligmannite	CuPbAsS ₃	119
Stannite	$\mathrm{SnCu}_{2}\mathrm{FeS}_{4}$	94
Stromeyerite	(Ag,Cu) ₂ S	67
Stylotypite .	$3(\mathrm{Cu_2Ag_2Fe})\mathrm{S.Sb_2S_3}$	94
Sulvanite	Cu_3VS_4	65
Tennantite	$Cu_8As_2S_7$	117
TENORITE	CuO	73
Tetrahedrite	$\mathrm{Cu_8Sb_2S_7}$	117
Umangite	$\mathrm{Cu}_3\mathrm{Se}_2$	77
Whitneyite	Cu ₉ As	33
Wittichenite	$\mathrm{Cu}_3\mathrm{BiS}_3$	95

- (a) Reduction on Charcoal.—Copper minerals, roasted in O.F. on charcoal, then finely ground and mixed with two or three parts of sodium carbonate and borax, when treated in a strong R.F. on charcoal, yield malleable copper buttons. It may sometimes be necessary to crush and wash the charge in the mortar to obtain the buttons if small.
- (b) Flame Tests.—Copper minerals heated in O.F. on charcoal; moistened with HCl and then reheated in the R.F., yield a brilliant azure-blue copper chloride flame, which may be tinged with the green flame of copper oxide. This azure-blue flame is very sensitive and will detect a fraction of 1 per cent. of copper. Copper oxide and a few copper minerals when powdered and heated directly in the O.F. yield an emerald-green flame.
- (c) Bead Tests.—Copper minerals, when roasted in O.F. on charcoal, and dissolved in S.Ph. or borax, yield a green bead while hot, which becomes blue when cold. In the R.F. if much oxide is present, the cold bead in reflected light is an opaque red due to cuprous oxide, Cu₂O.
- (d) Wet Test.—Copper salts color all acid solutions blue or green. With an excess of ammonium hydroxide the solution turns deep blue. Iron, if present, may be held in solution by adding tartaric acid before introducing the ammonia.

7. Germanium, Ge

Argyrodite Ag₆GeS₆ Page 110

(a) Coat on Charcoal.—Argyrodite, when heated in the R.F. and O.F. on charcoal, yields a glazy white coat near the assay, which assumes a yellowish color at a distance from it.

8. Gold, Au

GOLD MINERALS

Mineral	Formula	Page
CALAVERITE	$AgAuTe_2$	61
Gold	Au	111
Kalgoorlite	HgAu ₂ Ag ₆ Te ₆	97
KRENNERITE	AgAuTe ₂	63
Nagyagite	$Au_2Pb_{10}Sb_2Te_6S_{15}$	98
Petzite	(AgAu)₂Te	97
Sylvanite	AgAuTe ₂	98

Gold is usually present in such small amounts that ordinary blowpipe methods are not of much value in detecting it. It is present as a major constituent only in the tellurides, and reducing these minerals with sodium carbonate on charcoal in the R.F. yields a malleable button containing gold and silver. After dissolving with nitric acid the black residue is ignited and turns gold yellow.

9. Iron, Fe

IRON MINERALS

Mineral	Formula	Page
Arsenopyrite	FeAsS	57
Berthierite	FeSb ₂ S ₄	117
Bornite	$\mathrm{Cu}_5\mathrm{FeS}_4$	53
Chalcopyrite	$CuFeS_2$	117
Chalmersite	$CuFe_2S_3$	95
CHROMITE	$FeCr_2O_4$	114
Delafossite	CuO,Fe ₂ O ₃	103
Ferberile	$FeWO_4$	114
GLAUCODOT	(CoFe)AsS	91
Göthite	$\mathrm{Fe_2O_3.H_2O}$	114
Franklinite	(FeZnMn)O.(FeMn) ₂ O ₃	115
Hematite	${ m Fe}_2{ m O}_3$	115
Ilmenite	FeTiO_3	115
Limonite	$2\mathrm{Fe_2O_3.3H_2O}$	114

132 MICROSCOPIC EXAMINATION OF THE ORE MINERALS

Mineral	Formula	Page
Löllingite	FeAs ₂	91
Magnetite	Fe ₃ O ₄	115
Marcasite	FeS ₂	57
PENTLANDITE	(FeNi)S	95
Pyrite	FeS ₂	57
Pyrrhotite	$FeS(S)_x$	95
Stannite	$SnCu_2FeS_4$	94
Sternbergite	$AgFe_2S_3$	99
Stylotypite	3(Cu2Ag2Fe)S.Sb2S3	94
Turgite	$2\mathrm{Fe}_{2}\mathrm{O}_{3}.\mathrm{H}_{2}\mathrm{O}$	114
Wolframite	(FeMn)WO ₄	114

- (a) Magnetic Test.—Iron minerals when treated on charcoal in the R.F. become magnetic after cooling. Cobalt and Nickel also become magnetic when so treated and, when their presence is suspected, may be tested for as on pages 129 and 135.
- (b) Bead Tests.—The colors obtained upon dissolving iron minerals after roasting in S.Ph. or borax are not very satisfactory and should not be depended upon alone for identifications. For these tests see Table 17, page 149.
- (c) Wet Test.—When ammonium hydroxide is added in excess to a solution obtained by boiling any iron mineral in nitric acid, a heavy precipitate of reddish-brown ferric hydroxide is thrown down. In this way iron may be quantitatively separated from the solution. The precipitate filtered off may be tested in the S.Ph. or borax bead or it may be ignited on charcoal and tested for magnetism.

10. Lead, Pb

LEAD MINERALS

Mineral	Formula	Page
Aikinite	PbCuBiS ₃	63
Altaite	PbTe	43
Andorite	PbAgSb ₃ S ₆	95
Baumhauerite	Pb4As6S13	117
Beegerite	$Pb_6Bi_2S_9$	98
Boulangerite	$Pb_3Sb_2S_6$	63
BOURNONITE	(PbCu ₂) ₃ Sb ₂ S ₆	94
Brongniardite	$PbAg_2Sb_2S_5$	69
Chiviatite	$Pb_2Bi_2S_{11}$	63
Clausthalite	PbSe	77
Cosalite	$Pb_2Bi_2S_6$	59
Cuprodescloizite	(PbZnCu) ₄ V ₂ O ₉ .H ₂ O	75

Mineral	Formula	Page
Cylindrite	$Pb_6Sb_2Sn_6S_{21}$	77
Dufrenoysite	Pb ₂ As ₂ S ₅	119
Epiboulangerite	Pb ₃ Sb ₂ S ₈	99
Franckeite	$Pb_{5}Sn_{2}Sb_{2}S_{12}$	79
Freieslebenite	$(PbAg_2)_5Sb_4S_{11}$	98
Galena	PbS	77
Geocronite	Pb ₅ Sb ₂ S ₈	79
Guitermanite	Pb ₃ As ₂ S ₆	99
JAMESONITE	Pb ₂ Sb ₂ S ₅	62
Jordanite	Pb ₄ As ₂ S ₇	99
Lehrbachite	PbSe + HgSe	119
Lengenbachite	$Pb_6(AgCu)_2As_4S_{13}$	99
Lillianite	$Pb_3Bi_2S_6$	77
Meneghinite	Pb ₄ Sb ₂ S ₇	79
Nagyagite	$Au_2Pb_{10}Sb_2Te_6S_{16}$	98
Naumannite	(Ag ₂ Pb)Se	43
Plagionite	Pb ₅ Sb ₈ S ₁₇	43
Rathite	Pb(As,Sb),S	99
Rezbanyite	Pb ₄ Bi ₁₀ S ₁₉	61
Seligmannite	CuPbAsS ₃	119
Semseyite	Pb7Sb6S16	45
Teallite	$PbSnS_2$	77
Uraninite	Uranate of U, Pb, Th, etc.	113
Zinkenite	PbSb ₂ S ₄	62

- (a) Coat on Charcoal.—Lead minerals when slowly heated on charcoal yield a volatile yellow oxide coat which deposits close to the assay. (If much sulphur is present and the heating is rapid, a white coat similar to the antimony coat is formed—this does not occur when the heating is done slowly.) This yellow coat, moistened with hydriodic acid and heated gently in the O.F., or the powdered mineral mixed with 2 or 3 parts of KI & S flux and similarly heated, yields a lemon-yellow lead iodide coat. (Similarly treated, Bismuth yields a brick-red coat.)
- (b) Reduction on Charcoal.—Lead minerals powdered and roasted in a very small O.F., then mixed with 4 parts sodium carbonate, 1 part borax, and 1 part charcoal dust, and treated with the R.F. on charcoal, yield soft, highly malleable metallic lead buttons. (Bismuth buttons are brittle.)
- (c) Wet Test.—Sulphuric acid added to a nitric acid solution of lead minerals, brings down a white powdery precipitate of lead sulphate. This, when filtered off, may be tested on charcoal as in (a) and (b).

11. Manganese, Mn

MANGANESE MINERALS

Mineral	Formula	Page
ALABANDITE	MnS	41
BRAUNITE	3Mn ₂ O ₃ .MnSiO ₃	114
Erythrozincite	(MnZn)S	116
Franklinite	$(FeZnMn)O.(FeMn)_2O_3$	115
Hauerite	MnS_2	94
HAUSMANNITE	MnO.Mn ₂ O ₃	114
Hübnerite	MnWO ₄	114
MANGANITE	$Mn_2O_3.H_2O$	114
PSILOMELANE	H_4MnO_5	71
Pyrolusite	MnO_2	101
WOLFRAMITE	(FeMn)WO ₄	114

- (a) Sodium Carbonate and Niter Bead.—Any manganese mineral and any mineral containing as much as 0.1 per cent. of manganese will give a decisive test with this method, which, moreover, is not interfered with by the presence of any other substances. The finely powdered mineral, after roasting on charcoal, is fused with sodium carbonate on a platinum wire in the O.F. and again fused with a small grain of potassium nitrate in the O.F. The resulting bead will be green to dark blue, depending upon the amount of manganese present.
- (b) Common Bead Tests.—Manganese imparts characteristic colors to the borax bead, and to a lesser extent, to the S.Ph. bead. See Table 17, page 149, for these colors.

12. Mercury, Hg

MERCURY MINERALS

Mineral	Formula	Page
Cinnabar	HgS	118
Coloradoite	HgTe	97
Kalgoorlite	$\mathrm{HgAu_{2}Ag_{6}Te_{6}}$	97
Lehrbachite	PbSe + HgSe	119
Livingstonite	· HgSb ₄ S ₇	111
Metacinnabarite	HgS -	118
Onofrite	Hg(SSe)	111
Tiemannite	HgSe	119

(a) Closed Tube Reaction.—Mercury minerals, powdered and mixed with 3 parts sodium carbonate, placed in a closed tube with a little sodium carbonate on top of the charge, and heated, yield a gray sublimate of metallic mercury globules on the walls of the tube. The common mercury mineral, cinnabar (and

metacinnabarite) when heated alone in the closed tube, yields a black sublimate on the cold walls of the tube.

(b) Open Tube Reaction.—Mercury minerals, when heated very slowly in the open tube, yield a gray sublimate of metallic mercury.

13. Molybdenum, Mo

Molybdenite

MoS₂

- (a) Coat on Charcoal.—Molybdenite, strongly heated in the O.F. on charcoal, yields a volatile oxide coat which is yellowish while hot and white when cold. If this coat is touched instantaneously with the R.F. it turns deep blue. Close about the assay a non-volatile film of copper-red MoO₂ may sometimes be seen.
- (b) Bead Tests.—After roasting on charcoal, molybdenite imparts characteristic colors to the S.Ph. and borax beads. See Table 17, on page 149.

14. Nickel, Ni

	NICKEL MINERALS	
Mineral	Formula	Page
Briethauptite	NiSb	93
Chloanthite	NiAs ₂	. 89
GERSDORFFITE	NiAsS	89
Hauchecornite	(NiCo) ₇ (BiSbS) ₈	91
Kallilite	Ni(SbBi)S	57
Maucherite	Ni ₃ As ₂	55
Melonite	Ni ₂ Te ₃	61
MILLERITE	NiS	95
Niccolite	NiAs	55
PENTLANDITE	(FeNi)S	95
Polydymite	Ni ₄ S ₅	57
Rammelsbergite	NiAs ₂	89
Ullmannite	NiSbS	91
Willyamite	(CoNi)SbS	57

(a) Bead Tests.—For the colors imparted by nickel to the borax and S.Ph. beads see Table 17, page 149. Iron, cobalt, and copper, etc. will often entirely obscure the nickel color. It may often be detected in the presence of these elements by the following procedure: The mineral is fused to a globule and most of the arsenic, antimony, or sulphur roasted off. A piece of borax twice the size of the globule is placed beside it on the charcoal and heated in the O.F. for a short time, and the color of the bead observed. Iron, cobalt, nickel, and copper oxidize in

the order named, and if successive charges of borax are each treated briefly in the O.F. beside the globule, each element will in turn impart its color to the bead. The amount of each present may be roughly estimated from the number of fresh charges of borax required to absorb it. For example, if it takes two or three beads to remove the cobalt it is present only as a minor constituent and after the cobalt blue has disappeared, the borax will be colored reddish brown by any nickel present. Even with this procedure the results are not always satisfactory, in which case the following wet reaction must be resorted to.

(b) Wet Test.—The powdered mineral is dissolved in 4 or 5 e.c. of nitric acid, an equal amount of tartaric acid is added, and ammonium hydroxide to excess. The tartaric acid holds the iron in solution. The liquid may be filtered if not clear and then made neutral or very slightly acid with HCl. If 3 or 4 drops of a 1 per cent. solution of dimethyl glyoxime in alcohol are now added, any nickel present will be thrown down as a brilliant red precipitate. This precipitate, when filtered off, may be tested for nickel in the beads as in (a). This test is very sensitive and is not interfered with by other elements provided the iron is held in solution by sufficient tartaric acid.

15. Oxygen, O

	OXYGEN MINERALS	
Mineral	Formula	Page
CASSITERITE	SnO_2	114
CHROMITE	$\mathrm{FeCr}_2\mathrm{O}_4$	114
Cuprite	Cu_2O	33
Cuprodescloizite	$(PbZnCu)_4V_2O_9.H_2O$	75
Delafossite	$\mathrm{CuO.Fe_2O_3}$	103
Franklinite	$(\text{FeZnMn})\text{O.}(\text{FeMn})_2\text{O}_3$	115
Ferberite	FeWO ₄	114
Hematite	$\mathrm{Fe_2O_3}$	115
Hübnerite	$MnWO_4$	114
Ilmenite	${ m FeTiO_3}$	115
KERMESITE	$\mathrm{Sb}_{2}\mathrm{S}_{2}\mathrm{O}$	87
Limonite	$2\mathrm{Fe}_2\mathrm{O}_3.3\mathrm{H}_2\mathrm{O}$	114
Magnetite	$\mathrm{Fe}_3\mathrm{O}_4$	115
PSILOMELANE	H ₄ MnO ₅	71
Pyrolusite	MnO_2	101
Rutile	${ m TiO_2}$	115
TENORITE	CuO	73
Uranninite	Uranate of U, Pb, Th, etc.	113
Voltzite	$\mathrm{Zn}_{5}\mathrm{S}_{4}\mathrm{O}$	116
WOLFRAMITE	$(\text{FeMn}) \text{WO}_4$	114

Oxygen usually cannot be directly tested for in the minerals, but its presence is inferred from a knowledge of the character and behavior before the blowpipe of the other constituents.

16. Platinum, Pt

NATIVE PLATINUM Pt

Sperrylite

PtAs2

Platinum is usually recognized from its physical properties and insolubility in acids. If present it is collected in the reduction and cupellation for silver and gold. (See page 139.) If the button so obtained, or the residue after parting with nitric acid, is dissolved in aqua regia, evaporated nearly to dryness, a little hydrochloric acid added, and again almost evaporated, diluted with a little water, and concentrated ammonium chloride added, a precipitate of yellow ammonium platinic chloride is thrown down. Platinum tests are usually delicate operations and the standard references on qualitative analysis should be consulted.

17. Selenium, Se

SELENIUM MINERALS

	CHAMITOM MAINTENANCE	
Mineral	Formula	Page
Aguilarite	Ag ₂ S.Ag ₂ Se	76
Berzelianite	Cu ₂ Se	97
Clausthalite	PbSe	77
Crookesite	(CuTlAg) ₂ Se	94
Eucairite	Cu ₂ Se.Ag ₂ Se	97
Guanajuatite	$\mathrm{Bi}_{2}\mathrm{Se}_{3}$	98
Lehrbachite	PbSe + HgSe	119
Naumannite	(Ag ₂ Pb)Se	43
Onofrite	Hg(SSe)	111
Tiemannite	HgSe	119
Umangite	Cu ₃ Se ₂	77

- (a) Coat on Charcoal.—Selenium minerals, when heated on charcoal, yield a white oxide coat with a metallic-like luster, sometimes reddish at the edges.
- (b) Flame Test.—When the above coat is heated in the R.F. the flame is colored an intense azure-blue and a disagreeable characteristic odor is given off. This odor has been likened to that of horse radish, but really must be experienced in order to be recognized. It is noticed when even very small amounts of selenium are present.

- (c) Closed Tube Reaction.—Some selenium minerals, when heated in the closed tube, yield fused brownish red globules of selenium on the walls of the tube.
- (d) Open Tube Reaction.—Selenium minerals, when heated in the open tube, yield colorless globules of selenous oxide, which crystallize and whiten when cold. The characteristic azure-blue color will be obtained if the volatile oxide fumes are allowed to escape into the Bunsen flame.

18. Silver, Ag

SILVER MINERALS

Mineral	Formula	Page
Aguilarite	Ag ₂ S.Ag ₂ Se	76
Andorite	PbAgSb ₃ S ₆	95
Argentite	Ag ₂ S	67
Argyrodite	$\mathrm{Ag_6GeS_5}$	110
Brongniardite	$PbAg_2Sb_2S_5$	69
CALAVERITE	$AgAuTe_2$	61
Cerargyrite	AgCl	. 109
Chilenite	Ag_6Bi	35
Crookesite	(CuTlAg) ₂ Se	94
Dyscrasite	Ag ₆ Sb, etc.	67
Eucairite	Cu ₂ Se.Ag ₂ Se	97
Freieslebenite	$(PbAg_2)_5Sb_4S_{11}$	98
Freibergite	$(CuAg)_8Sb_2S_7$	82
HESSITE	Ag ₂ Te	66
Jalpaite	$3Ag_2S.Cu_2S$	67
Kalgoorlite	$\mathrm{HgAu_{2}Ag_{6}Te_{6}}$	97
Lengenbachite	Pb ₆ (AgCu) ₂ As ₄ S ₁₃	99
Matildite	$AgBiS_2$	119
Miargyrite	$AgSbS_2$	110
Naumannite	(Ag ₂ Pb)Se	43
Pearcite	Ag_9AsS_6	85
Petzite	(AgAu)₂Te	97
Polyargyrite	Ag 24 Sb 2 S15	109
POLYBASITE	Ag_9SbS_6	86
Proustite	Ag_3AsS_3	109
Pyrargyrite	Ag_3SbS_3	111
Silver	Ag	43
STEPHANITE	Ag_5SbS_4	101
Sternbergite	$AgFe_2S_3$	99
Stromeyerite	(AgCu)₂S	. 67
Stützite	Ag ₄ Te	119
Stylotypite	$3(\mathrm{Cu_2Ag_2Fe})\mathrm{S.Sb_2S_3}$	94
Sylvanite	AuAgTe ₂	98

(a) Reduction on Charcoal.—Silver minerals, when powdered and well roasted in O.F., then mixed with 3 or 4 parts of sodium carbonate and fused on charcoal in the R.F., yield metallic silver, which should be collected as much as possible into one button. If the button is not bright it should be heated beside borax on charcoal in the O.F. The base metals are oxidized first and dissolve in the borax, leaving a bright, malleable silver button, which may be further tested by dissolving in nitric acid and precipitating the silver as white silver chloride by adding hydrochloric acid. This silver chloride precipitate, when filtered off is insoluble in hot water, while a similar lead precipitate is dissolved by boiling water. Mercurous mercury also yields a white chloride precipitate which is blackened by ammonium hydroxide, but mercury should not be found in a button treated as in the above case.

When the suspected silver mineral occurs in very small amount and cannot be separated, conclusive tests can be applied providing the microscope reveals no other mineral likely to contain silver. The powdered sample is mixed with an equal volume each of pure test lead and borax glass, and fused and reduced by the R.F. in a deep cavity on charcoal. Manipulate the assay to collect the lead in a single button. The O.F. is now applied to oxidize impurities of arsenic, antimony, etc., and continued until the globule boils freely. It is now allowed to cool and is freed of slag by hammering into a small cube. A cupel is now prepared by compacting dry bone ash in a cavity in charcoal about a centimeter in diameter and one-half centimeter deep. The agate pestle is conveniently used in this operation and by finishing up with a twirling motion the cupel will have a hard, smooth, concave surface. Any loose bone ash is blown off and the cupel is strongly ignited in the O.F. to drive off all moisture, The button is now placed on the cupel and fused in the R.F. for a few moments: then the O.F. is applied and continued without interruption until all the lead is oxidized and absorbed by the bone ash, the end point being marked by a distinct change in color and brightening of the button. If very little silver is present the bead will appear to disappear entirely, but the spot should always be carefully examined with the lens. The residual button will contain any silver, gold, or metals of the platinum group present in the sample. If the bead is treated with a few drops of nitric acid and hydrochloric acid added to the liquid, any

silver present will be thrown down as insoluble white silver chloride.

19. Sulphur, S

Sulphur is present in most metallic ores and tests for the element seldom aid determinations in mineragraphic work.

- (a) Roasting on Charcoal.—Sulphur in sulphides, heated on charcoal in the O.F., yields sulphur dioxide fumes which are recognized by their odor.
- (b) Sodium Carbonate Test.—Powdered sulphide, fused with about 3 parts of sodium carbonate, when placed on a bright silver coin and moistened with a little water, stain the coin brown or black. (Since very faint reactions are sometimes due to the sulphur in the gas used, the fusion may be made in a closed tube in cases of doubt.)

20. Tellurium, Te

TELLURIUM MINERALS

Mineral	Formula	Page
Altaite	PbTe	43
CALAVERITE	AgAuTe ₂	61
Coloradoite	HgTe	97
HESSITE	Ag ₂ Te	66
Kalgoorlite	HgAu ₂ Ag ₆ Te ₆	97
KRENNERITE	AgAuTe ₂	63
Melonite	Ni ₂ Te ₂	61
Nagyagite	$Au_2Pb_{10}Sb_2Te_6S_{15}$	98
Petzite	$(AgAu)_2$ Te	97
Rickardite	Cu ₄ Te ₃	35
Stützite	Ag₄Te	119
Sylvanite	AuAgTe ₂	98
Tellurium	Te	61
Tetradymite	$\mathrm{Bi}_2(\mathrm{Te.S})_3$	61

- (a) Coat on Charcoal.—Tellurium minerals, when heated on charcoal in the R.F., yield a white oxide coat resembling the antimony coat, which also colors the flame pale greenish.
- (b) Closed Tube Reaction.—Tellurium minerals, fused in the closed tube with 3 parts of sodium carbonate and some charcoal dust, when dissolved in water after cooling, yield a reddish violet colored solution which gives a gray tellurium precipitate if poured out and exposed to the air.

- (c) Open Tube Reaction.—Tellurium minerals, when heated in the open tube, yield heavy white oxide fumes which condense close to the heated portion of the tube. This sublimate is volatilized with difficulty and fuses to yellow globules which become colorless on cooling.
- (d) Sulphuric Acid Test.—Tellurium minerals, powdered and heated in a test tube with 2 or 3 c.c. of concentrated sulphuric acid, yield a reddish violet solution which gives a precipitate as in (b) when cooled and diluted with a little water.

21. Thallium, Tl

	THALLIUM MINERALS	
Mineral	Formula	Page
Crookesite	(CuTlAg)₂Se	94
Lorandite	TlAsS ₂	118
Vrbaite	TlAs ₂ SbS ₅	119

(a) Coat on Charcoal and Flame.—Thallium minerals, when heated on charcoal in the R.F., yield a white oxide coat and color the flame bright green. This coat moistened with hydriodic acid and heated gently in the O.F., or the powdered mineral mixed with 2 or 3 parts of KI & S flux and similarly heated, yields a lemon-yellow coat very similar to that of lead. The bright green flame, however, will serve to distinguish it from lead.

22. Thorium and the Rare Earths

These rare elements which occur in uraninite, columbite, tantalite, samarskite, etc., are detected by somewhat complicated wet methods. For their application reference should be had to complete works on analytical chemistry.

23. Tin, Sn

TIN MINERALS

Mineral	Formula	Page
CASSITERITE	SnO_2	114
Cylindrite	Pb ₆ Sb ₂ Sn ₆ S ₂₁	77
Franckeite	$Pb_5Sb_2Sn_2S_{12}$	79
Stannite	SnCu ₂ FeS ₄	94
Teallite	$PbSnS_2$	77

(a) Reduction Test and Coat on Charcoal.—Tin minerals, powdered and roasted, then mixed with 4 parts sodium carbonate, 1 part borax, and 1 part charcoal dust, and treated with the R.F.

on charcoal, yield white malleable metallic tin globules which give a white insoluble precipitate on heating in a test tube with nitric acid. (The charge should not be heated long after reduction as metallic tin is easily volatile.) An oxide coat is usually formed very near the assay. This coat, which is yellow while hot and white when cold, is very like the zinc coat, and like it, is volatilized with difficulty. If the tin coat is moistened with cobalt nitrate solution and heated in the O.F. it turns blue or bluish green when cold. (A zinc coat similarly treated is grass green.)

24. Titanium, Ti

TITANIUM MINERALS

Mineral	Formula	Page
Ilmenite	FeTiO ₃	115
Rutile	TiO ₂	115

- (a) Bead Tests.—The bead reactions for titanium are not very decisive and are interfered with by other elements. They will be found in Table 17, page 149.
- (b) Wet Test with Metallic Tin.—A charge containing not less than 3 per cent. titanium may be treated as follows: The finely powdered mineral mixed with 6 parts of sodium carbonate and a little borax is strongly fused on charcoal. The fusion is dissolved in 2 or 3 c.c. of concentrated hydrochloric acid, granulated tin added and the solution heated. The liquid takes on a violet color especially upon standing a few minutes.
- (c) Hydrogen Peroxide Test.—For charges containing only a very small amount of titanium the fusion is carried out as directed in the foregoing paragraph, but is boiled in a test tube with 2 or 3 c.c. of dilute sulphuric acid. When dissolved, dilute with about 10 c.c. water and add about 2 c.c. hydrogen peroxide, which turns the solution yellow to orange depending on the amount of titanium present.

25. Tungsten, W

TUNGSTEN MINERALS

Mineral	Formula	Page
Ferberite	FeWO ₄	114
Hübnerite	MnWO ₄	114
Tungstenite	WS_2	62
WOLFRAMITE	(FeMn)WO ₄	114

- (a) Bead Tests.—The bead colors for tungsten will be found in Table 17, page 149.
- (b) Wet Test.—Tungstates, dissolved in the S.Ph. bead, then reduced beside tin on charcoal, powdered, and boiled with 1 or 2 c.c. of dilute hydrochloric acid and a little granulated tin, yield a characteristic blue solution.

26. Uranium, U

Uraninite

Uranate of U, Pb, Th, etc.

Page 113

- (a) Bead Tests.—The colors which uranium gives when dissolved in the S.Ph. bead usually serve to identify it. See Table 17, page 149.
- (b) Wet Test.—The powdered mineral is fused with sodium carbonate and dissolved in hydrochloric acid, nearly neutralized with ammonium hydroxide, a solution of sodium carbonate added until precipitation is complete, then half as much more. Let stand and filter. Acidify the filtrate with hydrochloric acid, boil to expel CO₂, and add an excess of ammonium hydroxide. The precipitate of yellow ammonium urinate may be filtered off and tested in the S.Ph. bead as in (a).

27. Vanadium, V

VANADIUM MINERALS

Mineral	Formula	Page
Cuprodescloizite	(PbZnCu) ₄ V ₂ O ₉ .H ₂ O	75
Patronite	VS_4	118
Sulvanite	$\mathrm{Cu_3VS_4}$	65

- (a) Bead Tests.—Vanadium minerals yield characteristic colors with the beads, especially S.Ph. See Table 17, page 149.
- (b) Wet Test.—The well roasted vanadium mineral is fused with 4 parts of sodium carbonate and 2 parts of potassium nitrate, the fusion is powdered and dissolved in boiling water and the insoluble residue filtered off. The alkali vanadate formed will be found in the filtrate, which is acidified with acetic acid and lead acetate added. A light yellow precipitate of lead vanadate is formed and turns white on standing. (Lead chromate so formed is of a brighter yellow color.) The precipitate may be filtered off and tested in the S.Ph. bead as in (a).

144 MICROSCOPIC EXAMINATION OF THE ORE MINERALS

28. Water, H2O

MINERALS YIELDING WATER

Mineral	Formula	Page
Cuprodescloizite	(PbZnCu) ₄ V ₂ O ₉ .H ₂ O	75
Göthite	$Fe_2O_3.H_2O$	114
Limonite	$2\mathrm{Fe}_2\mathrm{O}_3.3\mathrm{H}_2\mathrm{O}$	114
PSILOMELANE	H_4MnO_5	71
Turgite	$2\mathrm{Fe}_2\mathrm{O}_3.\mathrm{H}_2\mathrm{O}$	114

When a powdered hydrated mineral is heated in the closed tube, water of crystallization is expelled and condenses upon the cold walls of the tube.

29. Zinc, Zn

ZINC MINERALS

Mineral	Formula	Page
Cuprodescloizite	(PbZnCu) ₄ V ₂ O ₉ .H ₂ O	75
Erythrozincite	(ZnMn)S	116
Franklinite	$(FeZnMn)O.(FeM)_2O_3$	115
Sphalerite	ZnS	94
Voltzite	$\mathrm{Zn}_5\mathrm{S}_4\mathrm{O}$	116
Wurtzite	ZnS	94

(a) Coat on Charcoal.—Zinc minerals, when intensely heated in the R.F. on charcoal, yield a zinc oxide coat which deposits close to the assay. This coat is pale yellow while hot and white when cold. It is non-volatile in the O.F. and difficultly volatile in the R.F. When the powdered zinc mineral is fused with an equal part of sodium carbonate and a little charcoal dust the coat is usually heavier and more satisfactory. This coat, if moistened with cobalt nitrate solution and heated in the O.F. turns grass-green, at least in spots. (The tin oxide coat similarly treated is blue or bluish green.)

TABLES OF IMPORTANT CHEMICAL AND BLOWPIPE REACTIONS

TABLE 12.—MICROCHEMICAL REACTIONS10

¹⁰ From W. L. WHITEHEAD'S condensation of the complete tables of microchemical tests on the opaque minerals found in the second volume of "Behrens-Kley Mikrochemische Analyse," Kley, P. D. C., 1915, pp. 109–130.

Metal	Reagent	Precipitate	Remarks
Arsenic	Silver nitrate	Lemon yellow	Solution in HCl. Arsenic must be as arsenite
Antimony	Cesium chloride	Hexagonal plates	
Bismuth		Rhombic plates	
Cobalt	Ammonium mercuric sulphocyanate	Dark blue prisms	Neutral or slightly acid
	Potassium ferrocyanide	Amorphous red brown	Acetic acid solution
Gold	Thallium nitrate	Citron yellow needles	Solution must be strong and neutral
	Potassium ferrocyanide	Dark blue sol. in alk.	Much Cu interferes
Lead	Potassium iodide	Bright yellow hex.	Slightly acid (nitric) so- lution
Manganese	Potassium chromate	Yellow brown crystals	Solution neutral
Mercury	Potassium iodide	Mercuric-vermilion Mercurous-amorphous	Reagent added solid
Nickel	Dimethyl glyoxime	bright yellow Acicular magenta colored	In ammoniacal solution
Selenium	Potassium iodide	Powdery brown red	HCl solution of sele- nates
Silver	Hydrochloric acid	Amorphous white sol- utle in	Nitric acid solution
Sulphur	Calcium acetate	White needles of CaSO ₄	Nitric acid solutions of sulphides give sul- phates
Tellurium	Cesium chloride	Citron yellow octahedra	HCl solution of tellu- rium dioxide
Tin	Cesium chloride	Colorless cctahedra and cubes	Interfering elements numerous
Titanium	Rubidium chloride	Hex. and octagonal plates	Reagent added to solu- tion of sodium fluro- titanate
Uranium	Sodium acetate	Tetrahedrons light yellow	Weak acetic acid solu- tion
Vanadium	Silver nitrate	Pointed yellow grains	Acid solution pyrovan- adate
Zinc	Ammonium mercuric	White feathery crystals	
	sulphocyanate	in crosses and aggregates	

TABLE 13.—STANDARD FUSIBILITIES

Fusibility	Standard	Character of fusion
1	Stibnite	Large fragments fuse in the yellow flame
2	Chalcopyrite	Small fragments fuse in the yellow flame
3	Pyrite	Coarse fragments globular in the O.F.
4	(Actinolite)	Coarse edges rounded in the O.F. No opaque
		representatives of this class
5	(Orthoclase)	Needle-like fragments become globular in the
		O.F. A few nearly infusible opaque minerals
		belong here

Table 14.—Heating on Charcoal (With or without fluxes)

Sublimate, reduction, etc.	Element	Remarks
White sublimate at a considerable distance from the assay. Very volatile	Arsenic	Often yields strong garlic odor
White sublimate nearer the assay than the above. Volatile	Antimony	
White sublimate with metal- lic-like luster. Very volatile. Sometimes reddish at the edges	Selenium	The sublimate touched with the R.F. imparts an azure- blue color to the flame
White sublimate like antimony. Volatile	Tellurium	The sublimate touched with the R.F. volatilizes and colors the flame green
Sublimate near the assay which is pale yellow when hot, white when cold. Not volatile in the O.F.	Zinc	This sublimate moistened with cobalt nitrate solution and ignited becomes green
Sublimate which is pale yellow when hot, white when cold. Copper-red close to the assay	Molybdenum	The sublimate if touched instantaneously with the R.F. becomes azure-blue
Sublimate which is faint yellow to white when hot, white when cold. Not volatile in the O.F.	Tin	The sublimate moistened with cobalt nitrate solution and ignited becomes bluish- green
Sublimate which is yellow when hot, pale yellow when cold. Volatile in the O.F. and R.F.	(Sulphur and Lead)	This sublimate resembles the antimony coat and forms when galena or other lead sulphides are heated very quickly and intensely
Sublimate close to assay which is deep yellow when hot, pale yellow when cold. Volatile in O.F. and R.F.	Lead	This sublimate moistened with HI and ignited forms lemon-yellow lead iodide coat
Sublimate which is deep yellow when hot, pale yellow when cold. Volatile in the O.F. and R.F.	Bismuth	This sublimate moistened with HI and ignited forms a brick-red bismuth iodide coat.
Reduction with soda yields brittle gray button as well as coat	Antimony	

TABLE 14.—Continued

Sublimate, reduction, etc.	Element	Remarks	
Reduction with soda yields gray infusible particles as well as coat	Molybdenum		
Reduction with soda yields malleable white button as well as coat.	Tin		
Reduction with soda yields gray malleable button as well as coat	Lead		
Reduction with soda yields reddish white brittle button as well as coat	Bismuth		
Reduction with soda yields	Copper,		
malleable buttons, but no coat	Silver, or Gold		
Reduction with soda yields gray magnetic particles, but no coat	Iron, Cobalt, or Nickel		

TABLE 15.—SUBLIMATES IN THE CLOSED TUBE

Nature of sublimate	Element	Remarks
Mirror-like; collects in glob-ules	Mercury	Mercury minerals fused with sodium carbonate
Black; turns red when rubbed	Mercury	Cinnabar alone in closed tube
Mirror-like; does not collect in globules	Arsenic and Tellurium	Arsenic minerals fused with charcoal dust
Deep red when hot; reddish yellow when cold	Arsenic	The sulpharsenides heated alone in closed tube
Black when hot; reddish brown when cold	Antimony	Some sulphantimonides alone in closed tube
Red when hot; yellow, cold. White if in small amount	Sulphur	Many sulphides
Red to black; becomes red when rubbed.	Selenium	Selenides


148 MICROSCOPIC EXAMINATION OF THE ORE MINERALS

TABLE 16.—REACTIONS IN THE OPEN TUBE

Nature of sublimate, etc.	Element	Remarks
Dense fumes, depositing white powder mostly on under side of the tube. Pale yellow while hot, white when cold. Non-volatile and infusible	Antimony	All sulphantimonides
White, volatile, and crystal- line sublimate	Arsenic	Sulpharsenides, etc.
White, non-volatile sublimate, fusible to colorless or pale yellow globules	Tellurium	
White, non-volatile sublimate, fusible to yellow globules; white when cold	Lead	Sulphides containing lead
White, non-volatile sublimate which is infusible	Bismuth	Sulphides containing bismuth
White, volatile, and crystal- line sublimate. Often shows some red at distance from the	Selenium	
assay Crystalline sublimate near the assay; yellow while hot, white when cold	Molybdenum	
Volatile metallic mirror of gray globules	Mercury	Globules will unite when rubbed

TABLE 17.—BEAD REACTIONS WITH BORAX AND SALT OF PHOSPHORUS

Bora	Borax		Salt of phosphorus	
O.F.	R.F.	O.F.	R.F.	Element
Hot, yellow to red; cold, yellow to	Green	Hot, yellow to red; cold, yel- low to colorless	Dirty brownish or greenish	Iron
Hot, yellow; cold, colorless	Brown	Yellowish green to colorless	Fine green	Molybdenun
Hot, pale yellow; cold, colorless	Yellow to brown	Yellow to color- less	Hot, dirty blue; cold, fine blue	Tungsten
Hot, pale yellow; cold, colorless	Grayish to brown	Pale yellow to	Hot, yellow; cold, violet	Titanium
Hot, yellow; cold, pale yellow	Colorless	Hot, yellow; cold, colorless	Colorless	Cerium
Hot, yellow; cold, yellowish green	Fine green	Fine green	Fine green	Chromium
Hot, yellow; cold, yellow to colorless	Fine green	Yellow	Fine green	Vanadium
Hot, orange; cold, yellow	Green	Greenish yellow	Fine green	Uranium
Hot, green; cold, blue	Colorless to opaque red	Green to blue	Colorless to opaque red	Copper
Blue	Blue	Blue	Blue	Cobalt
Hot, violet; cold, reddish brown	Opaque gray	Reddish yellow	Reddish yellow	Nickel
Hot, violet; cold, reddish violet	Colorless	Violet	Colorless	Manganese

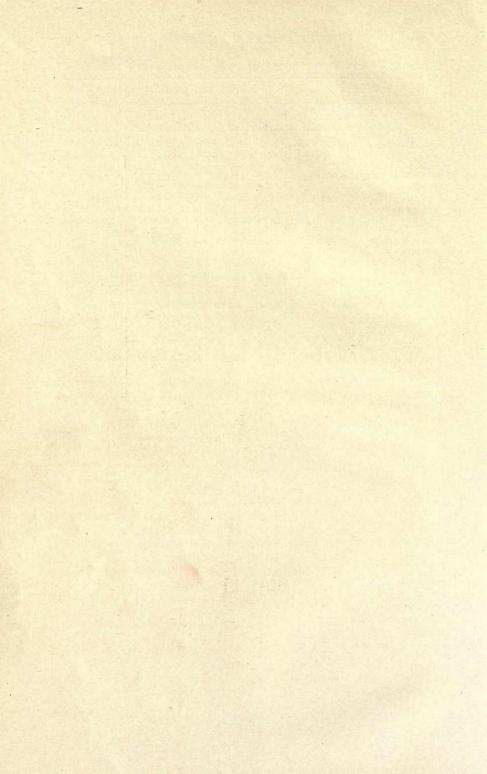

INDEX

Cerargyrite, 109 Abbreviations, table of, 22 Chalcocite, 51 Aguilarite, 76 Chalcophanite, 115 Aikinite, 63 Chalcopyrite, 117 Alabandite, 41 Chalcostibite, 117 Altaite, 43 Alundum, use in grinding and polish-Chalmersite, 95 Chamot, E. M., 11 ing, 2 Chilenite, 35 Andorite, 95 Chiviatite, 63 Antimony, native, 96 Chloanthite, 89 tests for the elements, 126 Chromic oxide, use in polishing, 3 table of minerals, 125 Chromite, 114 Argentite, 67 Chromium, tests for the element, 128 Argyrodite, 110 Cinnabar, 118 Arsenic, native, 59 Clausthalite, 77 table of minerals, 126 Closed tube, sublimates in, 147 tests for the element, 127 Coats on charcoal, table of, 146 Arsenopyrite, 57 Cobalt, tests for the element, 129 Bastin, E. S., 7 table of minerals, 129 Baumhauerite, 117 Cobaltite, 115 Bead colors, table of, 149 Color filters, need for, 13 Beegerite, 98 exposure factors for, 17 Berthierite, 117 range of transmission, 14 Berzelianite, 97 Color of internal reflection of min-Berzelius, J. J., vii erals, 121 Bismuth, native, 43 Color of mineral powders, 122 tests for the element, 128 Coloradoite, 97 table of minerals, 128 Colored minerals with vertical illu-Bismuthinite, 62 mination, 120 Bornite, 53 Conductivity, electrical; method of Bottles, reagent, 5, 7 testing, 8 Boulangerite, 63 table of mineral conductivity, Bournonite, 94 123 Braunite, 114 Copper, native, 51 Breithauptite, 93 table of minerals, 129 Brittleness, testing for, 7 tests for the element, 130 Bromyrite, 109 Cosalite, 59 Brongniardite, 69 Covellite, 111 Crookesite, 94 Calaverite, 61 Cuprite, 33 Calf skin, use in polishing, 3 Campbell, William, vii Cuprodescloizite, 75 Cylindrite, 77 Cassiterite, 114

Delafossite, 103
Determinative tables, 33
outline of, 23
use of, 20, 21
Dognacskaite, 63
Domeykite, 35
Dufrenoysite, 119
Dyscrasite, 67

Electrodes, standard copper and gold, 10
Electrolysis on polished surface, 9
Electro-potential of minerals, table of, 124

method of testing, 10

Embolite, 109
Emplectite, 63
Enargite, 83
Epiboulangerite, 99
Erythrozincite, 116
Eucairite, 97

Exposure, method of determining, 15 factors for color filter, 17 factors for magnification, 17 factors for numerical aperture, 16

factors for source of light, 16 graphical solution of, 18

Famatinite, 83
Ferberite, 114
Ferro-type plate, non-sticking solution for, 19
Field preparation of polished section, 4
Filter, color, 13, 14
factors for exposure, 17
Finder, use under miroscope, 5

Finder, use under miroscope, 5
Focusing for photography, 14
Franckeite, 79
Franklinite, 115
Freibergite, 82

Freieslebenite, 98

Fusibilies, standard, 145

Galena, 77 Galenobismutite, 98 Geocronite, 79 Germanium, tests for the element,
131
Gersdorffite, 89
Glass wheel, use in grinding, 2
Glaucodot, 91
Gold, native, 111
table of minerals, 131
Göthite, 114
Graton, L. C., x
Grinding, methods employed. 2
Guanajuatite, 98
Guejarite, 83
Guitermanite, 99

Hardness, testing for, 7
Hauchecornite, 91
Hauerite, 94
Hausmannite, 114
Hematite, 115
Hessite, 66
Horsfordite, 63
Hübnerite, 114
Huntilite, 33

Illumination, exposure factors for, 16 Ilmenite, 115 Iodobromite, 109 Iodyrite, 110 Internal reflection, table of colors,

Iron, tests for the element, 132 table of minerals, 131

Jalpaite, 67 Jamesonite, 62 Jordanite, 99

Kalgoorlite, 97 Kallilite, 57 Kermesite, 87 Krennerite, 63

Lead, tests for the element, 133 table of minerals, 132 Lehrbachite, 119 Lengenbachite, 99 Leveling cup, 5, 6 Light, exposure factors for, 16

Lillianite, 77 Onofrite, 111 Limonite, 114 Open tube, reactions in, 148 Lindgren; Waldemar, x Orpiment, 110 Oxygen, table of minerals, 136 Linen, use in polishing, 3 Linnaeite, 91 Livingstonite, 111 Patronite, 118 Löllingite, 91 Pearcite, 85 Pentlandite, 95 Lorandite, 118 Luzonite, 83 Petzite, 97 Photomicrography, 12 Magnetite, 115° Plagionite, 43 Magnification curves for Leitz micro-Platinum, tests for the element, 137 Polishing, method employed, 2 scope, 16 Polyargyrite, 109 exposure factors for, 17 Polybasite, 87 Manganese, tests for the element, Polydymite, 57 134 table of minerals, 134 Potential, electrical, method of test-Manganite, 114 ing, 10 table of electro-potential of Marcasite, 57 Matildite, 119 minerals, 124 Maucherite, 55 Printing paper, 19 Mees, C. E. Kenneth, 13 Proustite, 109 Melonite, 61 Psilomelane, 71 Meneghinite, 79 Pyrargyrite, 111 Mercury, tests for the element, 134 Pyrite, 57 table of minerals, 134 Pyrolusite, 101 Metacinnabarite, 118 Pyrrhotite, 95 Miargyrite, 110 Microchemical qualitative reactions, Qualitative microchemical tests, 145 145 Microscopes, Sauveur and Boyles-Rammelsbergite, 89 ton, 4, 5 Rare earths, 114 Leitz, 12 Rathite, 99 Millerite, 95 Reactions, features to be observed, 8 Mineragraphy, definition, x Reagents, method of applying, 7 Molybdenite, 97 table of, 11 Molybdenum, tests for the element, Realgar, 62 Reduction on charcoal, 146 Mounting, modelling clay for, 6 Regnolite, 119 Murdoch, Joseph, vii, ix Rezbanyite, 61 Rickardite, 35 Nagyagite, 98 Rutile, 115 Naumannite, 43 Needle, testing, 7 Safflorite, 55 Niccolite, 55 Sectility, testing for, 7 Nickel, tests for the element, 135 Selenium, tests for the element, 137 table of minerals, 135 table of minerals, 137 Numerical aperture, exposure factors Seligmannite, 119

Semseyite, 45

for, 16

Silver, native, 43 table of minerals, 138 tests for the element, 139 Smaltite, 55 Sperrylite, 115 Sphalerite, 94 Stannite, 94 Stephanite, 101 Sternbergite, 99 Stibnite, 87 Stromeyerite, 67 Stützite, 119 Stylotypite, 94 Sublimates, in the closed tube, 147 in the open tube, 148 Sulphur, tests for the element, 140 Sulvanite, 65 Sylvanite, 98

Tapalpaite, 43
Teallite, 77
Tellurium, native, 61
table of minerals, 140
tests for the element, 140
Temiskamite, 55
Tennantite, 117
Tenorite, 73
Tetradymite, 61
Tetrahedrite, 117
Thallium, tests for the element, 141
table of minerals, 141
Thorium, tests for the element, 141
Tiemannite, 119


Tin, tests for the element, 141
table of minerals, 141
Titanium, tests for the element, 142
table of minerals, 142
Tungsten, tests for the element, 143
table of minerals, 142
Tungstenite, 62
Turgite, 114

Ullmannite, 91 Umangite, 77 Uraninite, 113 Uranium, tests for the element, 143

Vanadium, tests for the element, 143 table of minerals, 143 Voltzite, 116 Vrbaite, 119

Water, tests for, 144
table of minerals, 144
Whitehead, W. L., x, 1
Whitneyite, 33
Willyamite, 57
Wittichenite, 95
Wolframite, 114
Wratten M plate, 13
Wurtzite, 94

Zinc, tests for the element, 144 table of minerals, 144 Zinkenite, 62

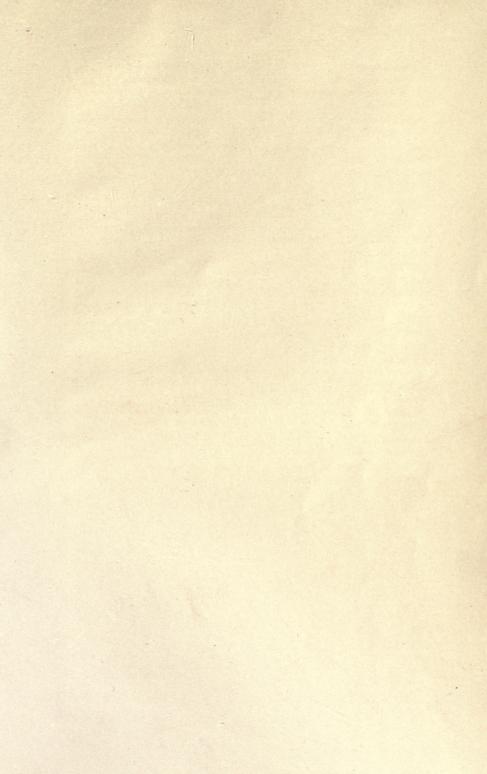

14 DAY USE RETURN TO DESK FROM WHICH BORROWED

EARTH SCIENCES LIBRARY

This book is due on the last date stamped below, or on the date to which renewed.

Renewed books are subject to immediate recall.

NOV 11 1967	
DEC 1 1 1967	
DEC 1 1 1967 DEC 1 7 1976	
DEG 27 1010	
AN ERK	
6 6 8	
SRARY 6 197 CALIF	
RLIB JEC OF	
L D C	
Ęź	
2	
	AND DESCRIPTION OF THE PERSON
	Conomil Library
LD 21-50m-6,'60 (B1321s10)476	General Library University of California Berkeley



